




BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 1

TABLE OF CONTENTS

SAMPLES SUBMITTED..... 2

PURPOSE OF TEST 3

PRODUCTS EVALUATED..... 4

SECTION A – CLEANING INTEGRALLY COLORED CMUs

DESCRIPTION OF PRODUCTS EVALUATED..... 5

TEST METHOD..... 5

TEST RESULTS 6

CONCLUSIONS 6

RECOMMENDATIONS 6

SECTION B – SURFACE ALTERATIONS

DESCRIPTION OF PRODUCTS EVALUATED..... 7

TEST METHOD..... 7

TEST RESULTS8-12

PHOTOGRAPHS (Surface Alterations)13

CONCLUSIONS14

RECOMMENDATIONS14

SECTION C - PROTECTIVE WATER REPELLENTS

DESCRIPTION OF PRODUCTS EVALUATED.....15

TEST METHODS.....15

TEST RESULTS16-19

PHOTOGRAPHS (Water Repellents).....20

CONCLUSIONS21

RECOMMENDATIONS21

ATTACHMENTS


Technical Services TECH Note RILEM Test Method No. II.4

Product Data literature for all products evaluated

Material Safety Data Sheets for all products evaluated



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 2

FOR: Mark Yaglowski
cc: Tony Evans
Richard Mirowski
Mike Dickey

SUBJECT: Young Block Company
2200 W. Gardner Lane
Tucson, AZ 85705

DATE: April 25, 2001

PROJECT: 0103-09 BP


SAMPLES SUBMITTED: 12 styles of double-sided (one side split-face, one side smooth) heavyweight CMUs, three of each style.

<u>Block</u>	<u>Color</u>	<u>Size</u>
Split-face CMU	"Fence Buff"	8" x 8" x 16"
Smooth CMU	"Fence Buff"	8" x 8" x 16"
Split-face CMU	"Chocolate"	8" x 8" x 16"
Smooth CMU	"Chocolate"	8" x 8" x 16"
Split-face CMU	"Red"	8" x 8" x 16"
Smooth CMU	"Red"	8" x 8" x 16"
Split-face CMU	"Light Mystic"	8" x 8" x 16"
Smooth CMU	"Light Mystic"	8" x 8" x 16"
Split-face CMU	"Terra Brown #1"	8" x 8" x 16"
Smooth CMU	"Terra Brown #1"	8" x 8" x 16"
Split-face CMU	"Terra Brown #2"	8" x 8" x 16"
Smooth CMU	"Terra Brown #2"	8" x 8" x 16"
Split-face CMU	"Santa Rosa"	8" x 8" x 16"
Smooth CMU	"Santa Rosa"	8" x 8" x 16"
Split-face CMU	"Sandstone"	8" x 8" x 16"
Smooth CMU	"Sandstone"	8" x 8" x 16"
Split-face CMU	"Buff #1"	8" x 8" x 16"
Smooth CMU	"Buff #1"	8" x 8" x 16"
Split-face CMU	"Buff #2"	8" x 8" x 16"
Smooth CMU	"Buff #2"	8" x 8" x 16"
Split-face CMU	"Charcoal"	8" x 8" x 16"
Smooth CMU	"Charcoal"	8" x 8" x 16"
Split-face CMU	"Dark Mystic"	8" x 8" x 16"
Smooth CMU	"Dark Mystic"	8" x 8" x 16"

Submitted by: Mike Dickey



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 3

PURPOSE OF TESTING:

Twelve colors of integrally colored concrete blocks (one side split-face, one side smooth) with large, small and fine aggregate were submitted for testing using PROSOCO's new construction cleaning and water repellent products.

A. Cleaning Concrete Masonry Units: Sure Klean[®] Custom Masonry Cleaner was evaluated for removal of laboratory applied mortar.

To simulate new construction soiling, all CMUs are placed on a bench with finished surface facing upward. Hollow cylinders measuring 50 mm in diameter and 75 mm tall are positioned on top of each CMU and filled with a wet mixture of Ash Grove[®] Type S cementitious mortar. The wet, mortar-filled cylinder is allowed to remain in contact with the CMU for 10 minutes before removal.

Soiled CMUs are allowed to dry before test cleaning.

Heavy deposits of mortar are removed with dry scraping after 24 hours. Prepared cleaning solutions are then evaluated for their effectiveness in removing residual Ash Grove[®] Type S mortar staining after 3 days, 7 days, and 14 days of curing.

Refer to “*Note: When cleaning integrally colored CMU” in the following section, “Surface Alteration Testing.”

B. Surface Alteration Testing - Sure Klean[®] Custom Masonry Cleaner was tested at various dilutions to determine if a cleaning program implemented to remove excess mortar and related new construction soiling would otherwise alter the appearance of cleaned surfaces. Surface Alteration was evaluated visually based upon perceived discoloration or erosion/etching of the masonry unit.

Aggregate Exposure is the visual examination of the CMU comparing aggregate exposure of the untreated control surface to surfaces cleaned with selected product(s) at given dilutions.

Surface Pigment Alteration/Removal* is the visual examination of the CMU comparing the surface pigmentation of the untreated control to surfaces cleaned with selected product(s) at given dilutions.

Matrix Erosion is the visual examination comparing the untreated control surface to surfaces cleaned with selected products at given dilutions looking for any potential erosion/digestion of the cementitious matrix of the CMU.

Staining is the visual examination for changes that are the result of a chemical reaction that leaves a staining precipitate.

The following is the scale used for reporting results of all categories:

0 – no change	3 – heavy
1 – slight	4 – excessive
2 – moderate	

*** NOTE: When cleaning integrally colored CMU.**


Integrally colored concrete masonry units (CMUs) frequently have high amounts of pigments concentrated on the surface of the cured concrete unit. Variation of surface pigment concentrations from one CMU to the next creates a blotchy appearance in the completed wall. Allowed to remain on the surface of the CMU, the weakly bound pigment will weather and streak, further detracting from the appearance of the completed CMU wall.

In addition to removing excess mortar and construction related soiling, the goal of any cleaning operation undertaken on integrally colored CMU should include removal of unnaturally high concentrations of surface pigment. By revealing the natural through-body color on the integrally colored unit, the overall color uniformity and weathering resistance of the completed CMU wall is improved.

C. Protective Water Repellents - Sure Klean[®] Custom Masonry Sealer and Sure Klean[®] Weather Seal Siloxane WB Concentrate were evaluated for their ability to provide water repellency to the submitted samples.



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 4

CLEANING PRODUCTS EVALUATED

BLOCK TYPE	Custom Masonry Cleaner
All Colors of Split-face and Smooth CMUs	1:2
	1:4
	1:6

SURFACE ALTERATION PRODUCTS EVALUATED


BLOCK TYPE	Custom Masonry Cleaner
All Colors of Split-face and Smooth CMUs	1:2
	1:4
	1:6

WATER REPELLENT PRODUCTS EVALUATED

BLOCK TYPE	Product	Dilution
All Colors of Split-face and Smooth CMUs	Custom Masonry Sealer	Concentrate
	Siloxane WB Concentrate	1:9



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 5

SECTION A – CLEANING INTEGRALLY COLORED CMUs

DESCRIPTION OF PRODUCTS EVALUATED

These cleaning trials were conducted to determine the optimal cleaning/cure time combination.

Sure Klean[®] Custom Masonry Cleaner – A general purpose, concentrated acidic cleaner for most custom masonry and colored concrete. Removes concrete splashes, excess mortar, mud, heavy efflorescence and surface soiling, leaving the masonry clean and uniform with no acid burning or streaking. Liquid concentrate for dilution with 2-6 parts water. Apply by brush or low-pressure spray.

TEST METHOD – Cleaning


Dilution ratios refer to mixtures of parts concentrated cleaner : parts fresh water. Chemical cleaners were evaluated using the following procedure:

1. Prewet the surface with water.
2. Apply the cleaner at the appropriate dilutions.
3. Allow 3-minute exposure time.
4. Reapply the products and moderately agitate with a brush.
5. Pressure rinse thoroughly.*
6. Allow the surface to dry for at least 18 hours and visually examine.

* Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 6

Test Results - Cleaning

Block Type	Cleaner	Dilution	Cure	Effectiveness
All Colors of Split-face and Smooth CMUs	Custom Masonry Cleaner	1:2	3 day	100%
		1:4		100%
		1:6		100%
		1:2	7 day	100%
		1:4		100%
		1:6		100%
		1:2	21 day	100%
		1:4		100%
		1:6		100%

CONCLUSIONS - Cleaning:

Based on the test data, all of the submitted block samples were efficiently cleaned with each dilution of the Sure Klean[®] Custom Masonry Cleaner. Use higher concentrations and surface agitation to maximize aggregate exposure. Use low concentration and surface agitation to minimize aggregate exposure.

All dilutions of Sure Klean[®] Custom Masonry Cleaner tested affected the substrate in a similar manner, removing heavy concentrations of pigmented matrix from the rough and smooth block faces, exposing small and large aggregate, and enhancing the natural appearance of the integrally colored concrete masonry unit.


RECOMMENDED PRODUCTS AND DILUTIONS - CLEANING:

Based on these evaluations, all of the dilutions of Sure Klean[®] Custom Masonry Cleaner tested can be recommended for job site testing on all samples submitted by Young Block Company, Tucson, AZ. They all are effective in removing excess mortar, and they all assist in improving the color and uniformity of these concrete blocks. The most appropriate cleaner and dilution should be determined on the specific job-site, and will be dependent primarily on the nature and severity of soiling present at that location.

NOTE: To remove excess mortar while minimizing aggregate exposure and color enhancement, clean within 7 days of completion using Custom Masonry Cleaner diluted with 6 parts fresh water.



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 7

SECTION B – Surface Alterations:

DESCRIPTION OF PRODUCTS EVALUATED – Surface Alterations:

Sure Klean® Custom Masonry Cleaner – A general purpose, concentrated acidic cleaner for most custom masonry and colored concrete. Removes concrete splashes, excess mortar, mud, heavy efflorescence and surface soiling, leaving the masonry clean and uniform with no acid burning or streaking. Liquid concentrate for dilution with 2-6 parts water. Apply by brush or low-pressure spray.

TEST METHOD – Surface Alteration Testing:

Dilution ratios refer to mixtures of parts concentrated cleaner : parts fresh water. Chemical cleaners were evaluated using the following procedure:

1. Prewet the surface with water.
2. Apply the cleaner at the appropriate dilutions.
3. Allow 3-minute exposure time.
4. Reapply the products and moderately agitate with a brush.
5. Pressure rinse thoroughly.*
7. Allow the surface to dry for at least 18 hours and visually examine.

* Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 8

Surface Alteration Results:

Substrate: Split-face CMU		Pigment Color: "Fence Buff"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Fence Buff"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	1	2	0
Custom Masonry Cleaner	1:4	1	1	1	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Split-face CMU		Pigment Color: "Chocolate"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	2	2	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Chocolate"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	2	2	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Split-face CMU		Pigment Color: "Red"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0

Scale used for reporting results of all categories

0 – no change
1 – slight
2 – moderate

3 – heavy
4 – excessive



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 9

Surface Alteration Results Continued:

Substrate: Smooth CMU		Pigment Color: "Red"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	2	1	2	0
Substrate: Split-face CMU		Pigment Color: "Light Mystic"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	1	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Light Mystic"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	2	2	0
Custom Masonry Cleaner	1:4	1	2	1	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Split-face CMU		Pigment Color: "Terra Brown #1"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	2	2	0
Custom Masonry Cleaner	1:4	1	1	1	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Terra Brown #1"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0


Scale used for reporting results of all categories

0 – no change
1 – slight
2 – moderate

3 – heavy
4 – excessive



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Surface Alteration Results Continued:

Substrate: Split-face CMU		Pigment Color: "Terra Brown #2"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Terra Brown #2"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Split-face CMU		Pigment Color: "Santa Rosa"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	1	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Santa Rosa"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	2	2	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Split-face CMU		Pigment Color: "Sandstone"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	2	1	2	0


Scale used for reporting results of all categories

0 – no change
1 – slight
2 – moderate

3 – heavy
4 – excessive



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 11

Surface Alteration Results Continued:

Substrate: Smooth CMU		Pigment Color: "Sandstone"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	1	2	0
Custom Masonry Cleaner	1:4	1	1	1	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Split-face CMU		Pigment Color: "Buff #1"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Buff #1"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Split-face CMU		Pigment Color: "Buff #2"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	2	2	0
Custom Masonry Cleaner	1:4	2	1	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Buff #2"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	2	2	0
Custom Masonry Cleaner	1:6	2	1	2	0



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 12

Surface Alteration Results Continued:

Substrate: Split-face CMU		Pigment Color: "Charcoal"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	2	2	0
Custom Masonry Cleaner	1:4	1	2	1	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Smooth CMU		Pigment Color: "Charcoal"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	1	2	0
Custom Masonry Cleaner	1:6	1	1	1	0
Substrate: Split-face CMU		Pigment Color: "Dark Mystic"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	3	2	3	0
Custom Masonry Cleaner	1:4	2	1	2	0
Custom Masonry Cleaner	1:6	2	1	2	0
Substrate: Smooth CMU		Pigment Color: "Dark Mystic"			
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/ Removal	Matrix Erosion	Staining
Custom Masonry Cleaner	1:2	2	1	2	0
Custom Masonry Cleaner	1:4	2	1	2	0
Custom Masonry Cleaner	1:6	1	1	1	0


Scale used for reporting results of all categories

0 – no change
1 – slight
2 – moderate

3 – heavy
4 – excessive




BLOCK PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 13

Photos of "Dark Mystic" after cleaning:

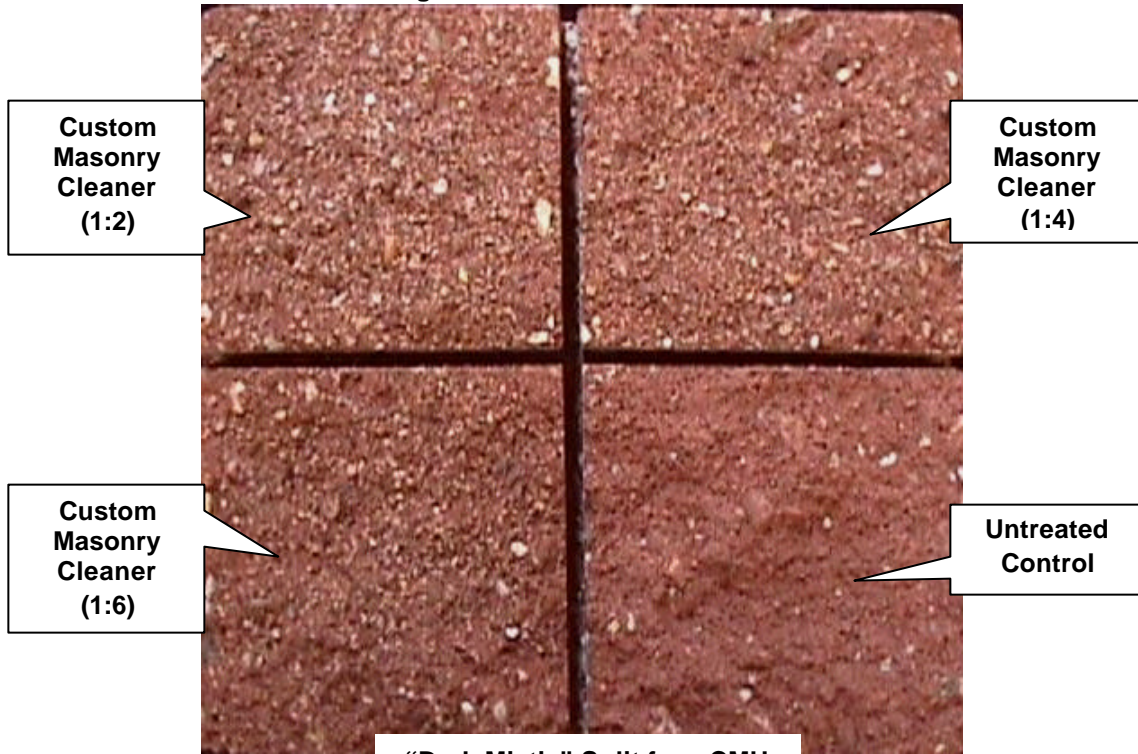


"Dark Mystic" Split-face CMU

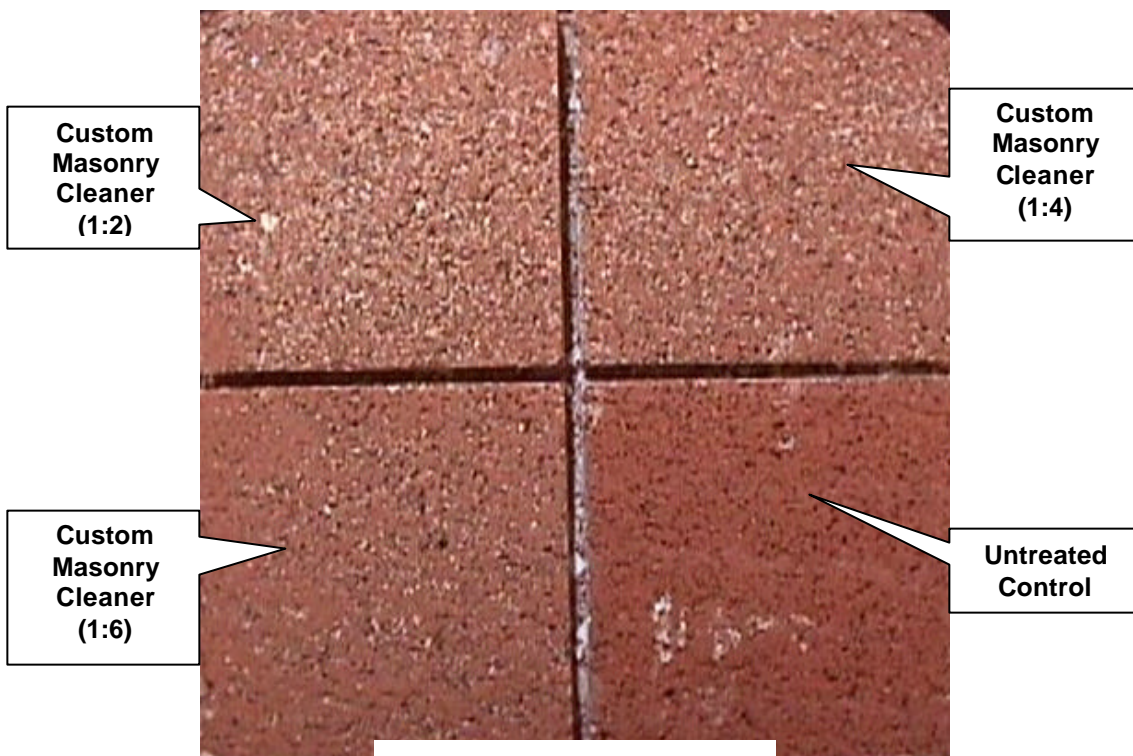

"Dark Mystic" Smooth CMU



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 14

CONCLUSIONS – Surface Alterations:

All dilutions of Sure Klean[®] Custom Masonry Cleaner tested affected the CMUs in a similar manner, removing heavy concentrations of pigmented matrix, exposing small and large aggregate, and enhancing the natural appearance of the integrally colored concrete masonry unit.


RECOMMENDATIONS – Surface Alterations:

Based on evaluations, Sure Klean[®] Custom Masonry Cleaner in all dilutions are recommended for job site testing on all types of the submitted CMUs from Young Block Company, Tucson, AZ. They all are effective in removing excess mortar, and they all assist in improving the color and uniformity of these concrete blocks. The most appropriate cleaner and dilution should be determined on the specific job-site, and will be dependent primarily on the nature and severity of soiling present at that location.

NOTE: To remove excess mortar while minimizing aggregate exposure and color enhancement, clean within 7 days of completion using Custom Masonry Cleaner diluted with 6 parts fresh water.



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 15

SECTION C - PROTECTIVE WATER REPELLENTS:

The testing described below evaluates the suitability of water repellent treatments.

The surface treatments evaluated were selected for their suitability for application based on the following selection criteria:

1. Weatherproofing properties
2. Color change
3. Ease of application

DESCRIPTIONS OF PRODUCTS EVALUATED - Protective Water Repellents:

Sure Klean® Custom Masonry Sealer - A clear, solvent-based silicone elastomer formulated to weatherproof custom masonry units, cast stone, and concrete block without altering the natural appearance. Custom Masonry Sealer penetrates and fills pores to prevent water penetration through exterior walls exposed to normal weathering as well as long-lasting protection against many types of graffiti.

Sure Klean® Weather Seal Siloxane WB Concentrate – A self-emulsifying water-repellent concentrate designed for dilution with fresh water at the jobsite. This solvent-free blend of silanes and oligomeric alkoxy siloxanes mixes easily with water to produce a penetrating water-repellent ideal for application to dense or porous masonry surfaces.

SAMPLE PREPARATION - Protective Water Repellents:

The submitted blocks were scored, allowed to dry, and to reabsorb atmospheric humidity for 24 hours prior to treatment. The treatment method consisted of a wet-on-wet brush application. All treatments were allowed to cure at least 14 days prior to testing.


TEST METHODS - Protective Water Repellents:

Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes

The water absorption tube test simulating wind driven rain conditions was performed. This test simulates 60 mile per hour wind driven rain conditions for a period of 20 minutes.



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 16


TEST RESULTS - Protective Water Repellents:

Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes

RESULTS	
“Fence Buff” Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	50 mph
Siloxane WB (1:9)	60 mph
“Fence Buff” Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
“Chocolate” Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	58 mph
Siloxane WB (1:9)	60 mph
“Chocolate” Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
“Red” Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
“Red” Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 17

Test Results Continued - Protective Water Repellents:

"Light Mystic" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
"Light Mystic" Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
"Terra Brown #1" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
"Terra Brown #1" Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	<40 mph
Siloxane WB (1:9)	60 mph
"Terra Brown #2" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	<40 mph
Siloxane WB (1:9)	60 mph
"Terra Brown #2" Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	<40 mph
Siloxane WB (1:9)	60 mph
"Santa Rosa" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	55 mph
Siloxane WB (1:9)	60 mph



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 18

Test Results Continued - Protective Water Repellents:

“Santa Rosa” Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	<40 mph
Siloxane WB (1:9)	60 mph
“Sandstone” Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
“Sandstone” Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	<40 mph
Siloxane WB (1:9)	60 mph
“Buff #1” Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	<40 mph
Siloxane WB (1:9)	60 mph
“Buff #1” Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	<40 mph
Siloxane WB (1:9)	60 mph
“Buff #2” Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
“Buff #2” Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 19

Test Results Continued - Protective Water Repellents:

"Charcoal" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	59 mph
Siloxane WB (1:9)	60 mph
"Charcoal" Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	55 mph
Siloxane WB (1:9)	60 mph
"Dark Mystic" Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph
"Dark Mystic" Smooth CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB (1:9)	60 mph



BLOCK PROGRAM LABORATORY REPORT




PROSOCO, Inc.


Page 20

Photos of "Dark Mystic" with water repellent:

"Dark Mystic" Split-face CMU

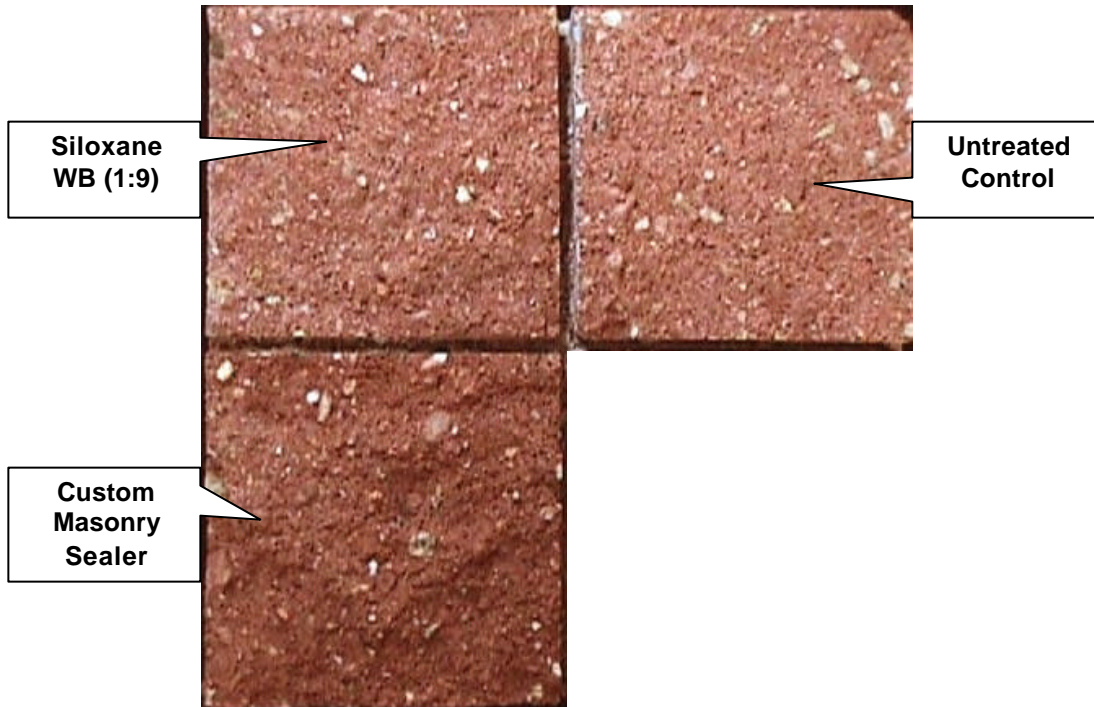


"Dark Mystic" Smooth CMU

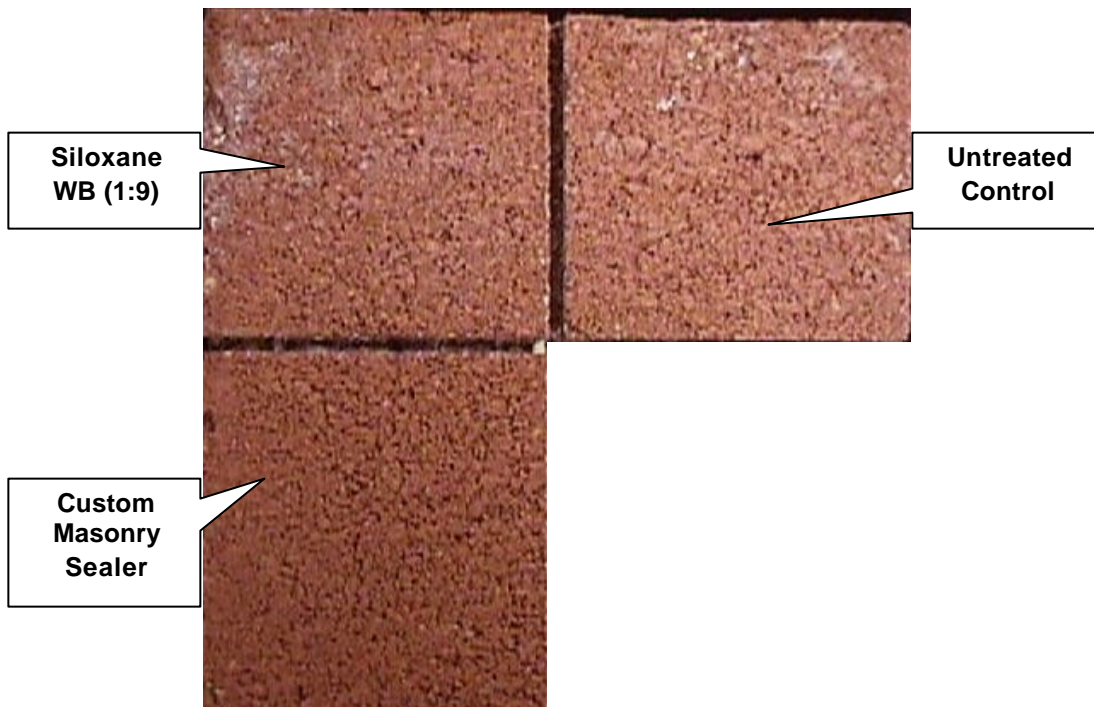



BLOCK PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 21

CONCLUSIONS - Protective Water Repellents:

Based upon laboratory evaluations, Sure Klean[®] Weather Seal Siloxane WB Concentrate diluted with nine parts water provided above average water repellency on all submitted samples. Sure Klean[®] Custom Masonry Sealer provided above average water repellency on all samples except for "Terra Brown #1", "Terra Brown #2", "Santa Rosa", "Sandstone", and "Buff #1". Sure Klean[®] Custom Masonry Sealer also enhanced the natural color of the submitted samples, while Sure Klean[®] Weather Seal Siloxane WB (1:9) did not change the appearance of the CMU.


RECOMMENDATIONS - Protective Water Repellents:

Based on evaluations, Sure Klean[®] Weather Seal Siloxane WB Concentrate diluted with nine parts water can be recommended for jobsite testing on all samples submitted by Young Block Company, Tucson, AZ.

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate water-repellent product and procedures for a particular project. See product literature for additional application and product information.

Jason L. Anderson
Materials Testing Technician

JLA/csm



Laboratory Report

Block Program Evaluation

**Young Block Company
Tucson, AZ**

Project No. 0103-09 BP

Prepared For:

**Mark Yaglowski
Young Block Company
2200 W. Gardner Lane
Tucson, AZ 85705**

Prepared By:



***PROSOCO, Inc.
April 2001***