




# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 1

## TABLE OF CONTENTS

SAMPLES SUBMITTED.....	3-5
PURPOSE OF TEST .....	6
PRODUCTS EVALUATED.....	7

### SECTION A – CLEANING INTEGRALLY COLORED CMU's

DESCRIPTION OF PRODUCTS EVALUATED.....	8
TEST METHOD.....	8
TEST RESULTS .....	9-19
PHOTOGRAPHS OF CMU CLEANING.....	20-24
CONCLUSIONS .....	24
RECOMMENDATIONS .....	25

### SECTION B – COLOR UNIFORMITY

DESCRIPTION OF PRODUCTS EVALUATED.....	26
TEST METHOD.....	26
TEST RESULTS .....	27-48
PHOTOGRAPHS OF CMU COLOR UNIFORMITY TESTING.....	49-50
CONCLUSIONS .....	51
RECOMMENDATIONS .....	51

### SECTION C - PROTECTIVE WATER REPELLENTS


DESCRIPTION OF PRODUCTS EVALUATED.....	52
TEST METHODS.....	52
TEST RESULTS .....	53-61
PHOTOGRAPHS OF CMU WATER REPELLENCY.....	62
CONCLUSIONS .....	63
RECOMMENDATIONS .....	63

### SECTION D – GRAFFITI CONTROL

DESCRIPTION OF PRODUCTS EVALUATED.....	64
TEST METHOD.....	65
TEST RESULTS .....	66-87
PHOTOGRAPHS OF CMU GRAFFITI TESTING.....	88-90
CONCLUSIONS .....	91
RECOMMENDATIONS .....	91



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 2**

## **SECTION E- STAIN RESISTANCE**


DESCRIPTION OF PRODUCTS EVALUATED.....	92
TEST METHOD.....	93-94
TEST RESULTS .....	94-152
PHOTOGRAPHS OF CMU STAIN TESTING .....	152-155
CONCLUSIONS .....	156
RECOMMENDATIONS .....	156

## **ATTACHMENTS**

Technical Services TECH Note RILEM Tube Test Procedures  
Product Data literature for all products evaluated



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 3**

**FOR:** Rodney Moore  
**cc:** Ralph Morgan  
John Bourne  
Stephen Dean

**SUBJECT:** A. Jandris & Sons, Inc.  
Gardner, MA

**DATE:** April 2003

**PROJECT:** 0302-06 PTP

**SAMPLES SUBMITTED:** Eighty-eight types of block in thirty-two colors.

**Without Dry Blok, 15.5" x 3.75" x 7.5"**


<u>Block</u>	<u>Color</u>
(4) Rough-face CMU's	"LT-N"
(4) Rough-face CMU's	"LT-1"
(4) Rough-face CMU's	"LT-3"
(4) Rough-face CMU's	"LT-13"
(4) Rough-face CMU's	"LT-14"
(4) Rough-face CMU's	"LT-17"
(4) Rough-face CMU's	"LT-18"
(4) Rough-face CMU's	"DK-6"
(4) Rough-face CMU's	"DK-9"
(4) Rough-face CMU's	"DK-12"
(4) Rough-face CMU's	"DK-16"
(4) Rough-face CMU's	"DK-19"
(4) Rough-face CMU's	"DK-21"
(4) Rough-face CMU's	"DK-22"
(4) Rough-face CMU's	"9312"
(4) Rough-face CMU's	"5110"

**With Dry Block, 15.5" x 3.5" x 7.5", Coated**

<u>Block</u>	<u>Color</u>
(4) Ground-face CMU's	"2501"
(4) Ground-face CMU's	"2502"
(4) Ground-face CMU's	"2503"
(4) Ground-face CMU's	"2504"
(4) Ground-face CMU's	"2505"
(4) Ground-face CMU's	"2506"



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 4


(4) Ground-face CMU's	"2507"
(4) Ground-face CMU's	"2508"
(4) Ground-face CMU's	"2509"
(4) Ground-face CMU's	"2510"
(4) Ground-face CMU's	"2511"
(4) Ground-face CMU's	"2512"
(4) Ground-face CMU's	"9301"
(4) Ground-face CMU's	"9302"
(4) Ground-face CMU's	"9303"
(4) Ground-face CMU's	"9304"
(4) Ground-face CMU's	"9305"
(4) Ground-face CMU's	"9306"
(4) Ground-face CMU's	"9307"
(4) Ground-face CMU's	"9308"
(4) Ground-face CMU's	"9309"
(4) Ground-face CMU's	"9310"
(4) Ground-face CMU's	"9311"
(4) Ground-face CMU's	"9312"
(4) Ground-face CMU's	"510"
(4) Ground-face CMU's	"520"
(4) Ground-face CMU's	"530"
(4) Ground-face CMU's	"540"
(4) Ground-face CMU's	"560"
(4) Ground-face CMU's	"570"
(4) Ground-face CMU's	"580"
(4) Ground-face CMU's	"590"
(4) Ground-face CMU's	"5100"
(4) Ground-face CMU's	"5110"
(4) Ground-face CMU's	"5120"
(4) Ground-face CMU's	"5200"

**With Dry Block, 15.5" x 3.5" x 7.5", Uncoated**

(4) Ground-face CMU's	"2501"
(4) Ground-face CMU's	"2502"
(4) Ground-face CMU's	"2503"
(4) Ground-face CMU's	"2504"



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 5**

(4) Ground-face CMU's	"2505"
(4) Ground-face CMU's	"2506"
(4) Ground-face CMU's	"2507"
(4) Ground-face CMU's	"2508"
(4) Ground-face CMU's	"2509"
(4) Ground-face CMU's	"2510"
(4) Ground-face CMU's	"2511"
(4) Ground-face CMU's	"2512"
(4) Ground-face CMU's	"9301"
(4) Ground-face CMU's	"9302"
(4) Ground-face CMU's	"9303"
(4) Ground-face CMU's	"9304"
(4) Ground-face CMU's	"9305"
(4) Ground-face CMU's	"9306"
(4) Ground-face CMU's	"9307"
(4) Ground-face CMU's	"9308"
(4) Ground-face CMU's	"9309"
(4) Ground-face CMU's	"9310"
(4) Ground-face CMU's	"9311"
(4) Ground-face CMU's	"9312"
(4) Ground-face CMU's	"510"
(4) Ground-face CMU's	"520"
(4) Ground-face CMU's	"530"
(4) Ground-face CMU's	"540"
(4) Ground-face CMU's	"560"
(4) Ground-face CMU's	"570"
(4) Ground-face CMU's	"580"
(4) Ground-face CMU's	"590"
(4) Ground-face CMU's	"5100"
(4) Ground-face CMU's	"5110"
(4) Ground-face CMU's	"5120"
(4) Ground-face CMU's	"5200"

**Submitted by: Rodney Moore**



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 6

---

## PURPOSE OF TESTING:

Seventy-two integrally colored ground-face concrete blocks and sixteen integrally colored rough-face concrete blocks with large, small and fine aggregate were submitted for testing using PROSOCO's new construction cleaning and water repellent products.

**A. Cleaning Concrete Masonry Units:** Sure Klean® Custom Masonry Cleaner was evaluated for removal of laboratory applied mortar.

To simulate new construction soiling, all CMU's are placed on a bench with finished surface facing upward. Hollow cylinders measuring 50 mm in diameter and 75 mm tall are positioned on top of each CMU and filled with a wet mixture of Ash Grove® Type S mortar. The wet, mortar-filled cylinder is allowed to remain in contact with the CMU for 10 minutes before removal.

Heavy deposits of mortar are removed with dry scraping after 24 hours. Prepared cleaning solutions are then evaluated for their effectiveness in removing residual Ash Grove® Type S mortar staining after 3 days, 7 days, and 14 days of curing.

**B. Color Uniformity Testing\*** - Sure Klean® Custom Masonry Cleaner was evaluated at various dilutions to determine the optimal concentration of cleaner that leaves the external surface looking most like the natural through-body color of the CMU. Color uniformity was evaluated by comparing aggregate exposure and surface pigment alternation/removal of each cleaned surface compared to the natural through-body color of the CMU.

Aggregate Exposure is the visual examination comparing aggregate exposure of the interior, through-body section of CMU to surfaces cleaned with selected product(s) at given dilutions.

Surface Pigment Alternation/Removal\* is the visual examination comparing the pigmentation of the interior, through-body section of the CMU to surfaces cleaned with selected product(s) at given dilutions.

The following is the scale used for reporting results of both categories:

0 – <b>Worst</b> match to through-body	3 – <b>Good</b> match to through-body
1 – <b>Poor</b> match to through-body	4 – <b>Best</b> match to through-body
2 – <b>Fair</b> match to through-body	

**\* NOTE: When cleaning integrally colored CMU.**

Integrally colored concrete masonry units (CMU's) frequently have high amounts of pigments concentrated on the surface of the cured concrete unit. Variation of surface pigment concentrations from one CMU to the next creates a blotchy appearance in the completed wall. Allowed to remain on the surface of the CMU, the weakly bound pigment will weather and streak, further detracting from the appearance of the completed CMU wall.

In addition to removing excess mortar and construction related soiling, the goal of any cleaning operation undertaken on integrally colored CMU should include removal of unnaturally high concentrations of surface pigment. By revealing the natural through-body color on the integrally colored unit, the overall color uniformity and weathering resistance of the completed CMU wall is improved.


**C. Protective Water Repellents** - Sure Klean® Custom Masonry Sealer was evaluated for its ability to provide water repellency to the submitted samples.

**D. Graffiti Control** – Sure Klean® Weather Seal Blok-Guard® & Graffiti Control was evaluated for its ability to control graffiti on the submitted samples. Sure Klean® Fast Acting Stripper, Defacer Eraser® Graffiti Wipe and Defacer Eraser® Graffiti Release were evaluated for their ability to remove graffiti from the submitted samples.

**E. Stain Resistance** – Stand Off® Stone, Tile & Masonry Protector was evaluated for its ability to resist staining agents applied to the submitted samples. Enviro Klean® 2010 All Surface Cleaner diluted with 10 parts fresh water was evaluated for its ability to remove the staining agents from the treated samples.



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 7**

---

## PRODUCTS EVALUATED FOR CLEANING AND COLOR UNIFORMITY

Block Type	Product	Dilution
All Submitted CMU's	Sure Klean® Custom Masonry Cleaner	1:2, 1:4, 1:6

## WATER REPELLENT PRODUCTS EVALUATED

Block Type	Product	Dilution
All submitted CMU's	Sure Klean® Custom Masonry Sealer	Concentrate

## GRAFFITI CONTROL PRODUCTS EVALUATED

Block Type	Product
All submitted CMU's	Sure Klean® Weather Seal Blok-Guard® & Graffiti Control

## GRAFFITI REMOVAL PRODUCTS EVALUATED


Block Type	Product
All submitted CMU's	Sure Klean® Fast Acting Stripper
	Defacer Eraser® Graffiti Wipe
	Defacer Eraser® Graffiti Release

## STAIN REMOVAL PRODUCTS EVALUATED

Block Type	Product
All submitted CMU's	Stand Off® Stone, Tile & Masonry Protector



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 8**

---

## **SECTION A – CLEANING INTEGRALLY COLORED CMU's**

### **DESCRIPTION OF PRODUCTS EVALUATED**

These cleaning trials were conducted to determine the optimal cleaning/cure time combination.

**Sure Klean® Custom Masonry Cleaner** – A general purpose, concentrated acidic cleaner for most custom masonry and colored concrete. Removes concrete splashes, excess mortar, mud, heavy efflorescence and surface soiling, leaving the masonry clean and uniform with no acid burning or streaking. Liquid concentrate for dilution with 2-6 parts water. Apply by brush or low-pressure spray.

---

### **TEST METHOD – Cleaning**

Dilution ratios refer to mixtures of parts concentrated cleaner : parts fresh water. Chemical cleaners were evaluated using the following procedure:


1. Prewet the surface with water.
2. Apply each cleaner at the appropriate dilutions.
3. Allow appropriate dwell time for each cleaner:  
    Custom Masonry Cleaner ..... 3 minutes
4. Reapply the products and moderately agitate with a brush.
5. Pressure rinse thoroughly.\*
6. Allow the surface to dry for at least 18 hours and visually examine.

\* Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.





# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 9


## TEST RESULTS - Cleaning

### % removal

"LT-N" rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"LT-1" rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"LT-3" rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"LT-13" rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"LT-17" rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"LT-18" rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"DK-6" rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"DK-9" rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 10


## TEST RESULTS – Cleaning continued

### % removal

“DK-12” rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“DK-16” rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“DK-21” rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“DK-22” rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9312” rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“5110” rough-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2501” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2502” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 11


## TEST RESULTS – Cleaning continued

### % removal

“2503” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2504” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2505” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2506” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2507” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2508” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2509” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2510” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 12


## TEST RESULTS – Cleaning continued

### % removal

“2511” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2512” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9301” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9302” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9303” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9304” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9305” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9306” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 13


## TEST RESULTS – Cleaning continued

### % removal

“9307” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9308” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9309” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9310” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9311” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9312” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“510” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“520” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 14


## TEST RESULTS – Cleaning continued

### % removal

“530” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“540” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“560” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“570” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“580” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“590” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“5100” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“5110” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 15


## TEST RESULTS – Cleaning continued

### % removal

“5120” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“5200” ground-face, coated				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2501” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2502” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2503” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2504” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2505” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“2506” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 16

**TEST RESULTS – Cleaning continued**


**% removal**

"2507" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"2508" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"2509" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"2510" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"2511" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"2512" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9301" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9302" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 17


**TEST RESULTS – Cleaning continued**

**% removal**

"9303" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9304" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9305" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9306" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9307" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9308" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9309" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
"9310" ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 18


## TEST RESULTS – Cleaning continued

### % removal

“9311” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“9312” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“510” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“520” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“530” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“540” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“560” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“570” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 19**


**TEST RESULTS – Cleaning continued**

**% removal**

“580” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
590” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“5100” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“5110” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“5120” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
“5200” ground-face				
Product	Dilution	3 day	7 day	14 day
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.


Page 20

## PHOTOGRAPHS- Cleaning

“LT-3” rough-face, 3 Day Cleaning

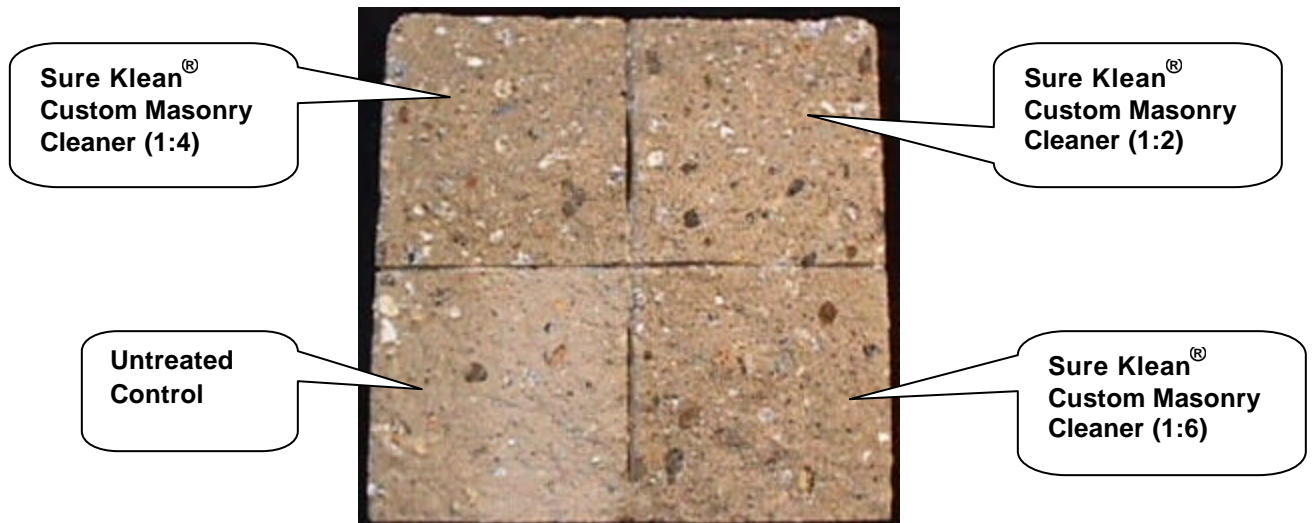


“LT-3” rough-face, 7 Day Cleaning

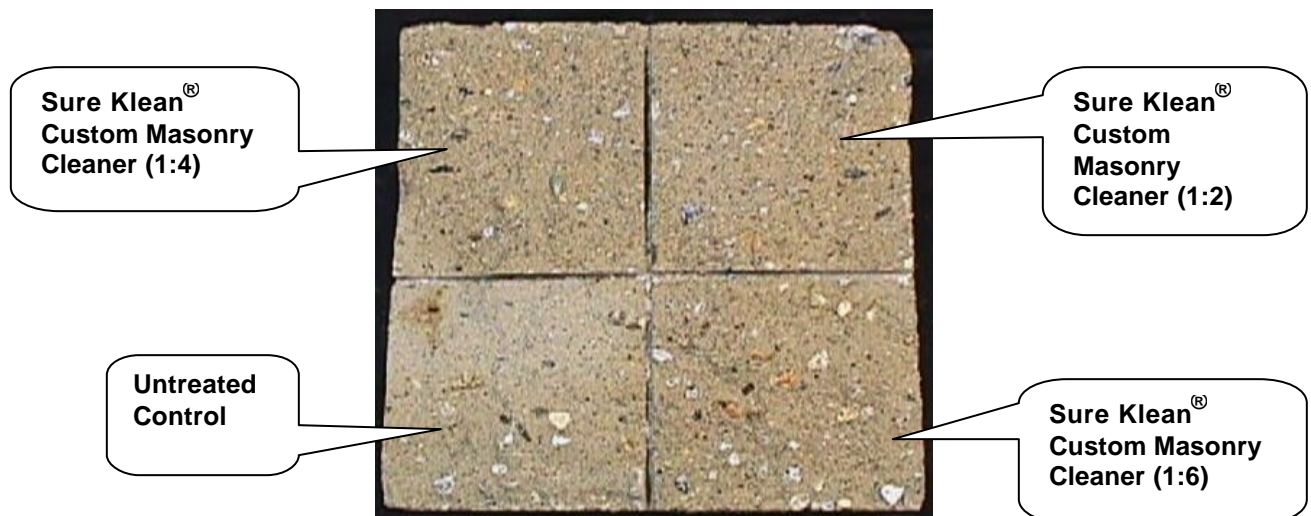



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 21

“LT-N” rough-face, 14 Day Cleaning




“2501” ground-face coated, 3 Day Cleaning

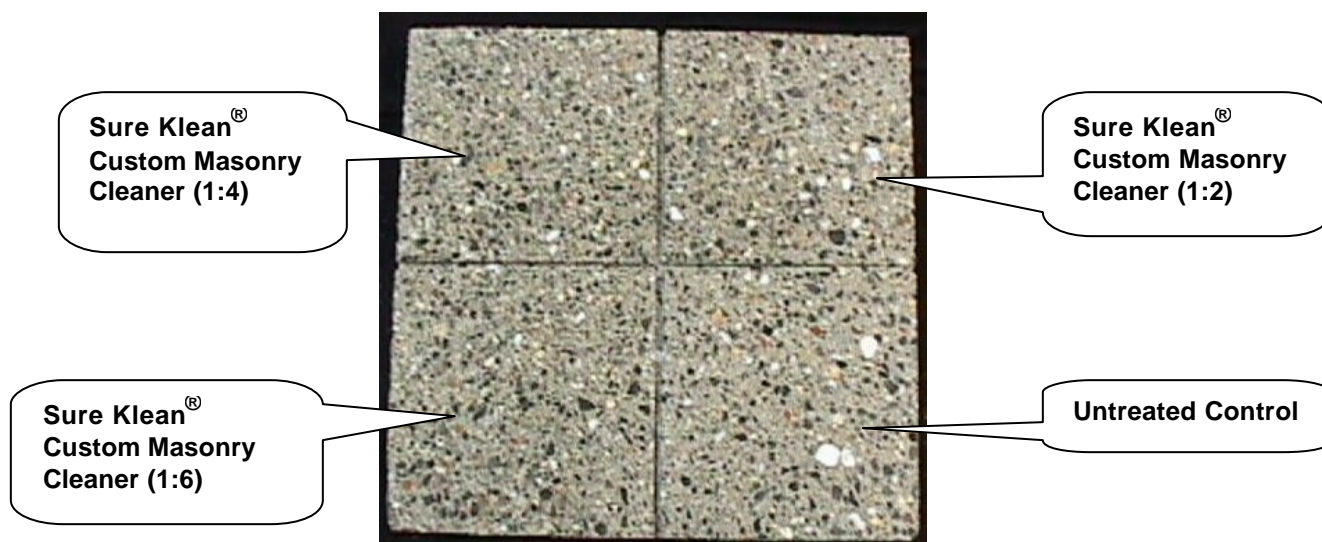






# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 22

## "2501" ground-face coated, 7 Day Cleaning

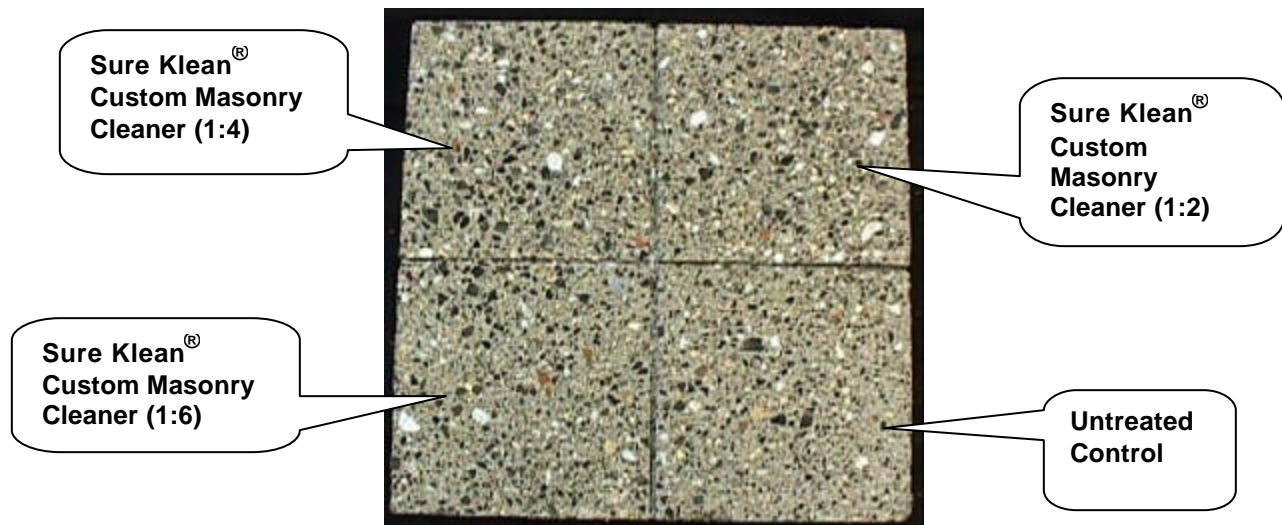


## "2501" ground-face coated, 14 Day Cleaning

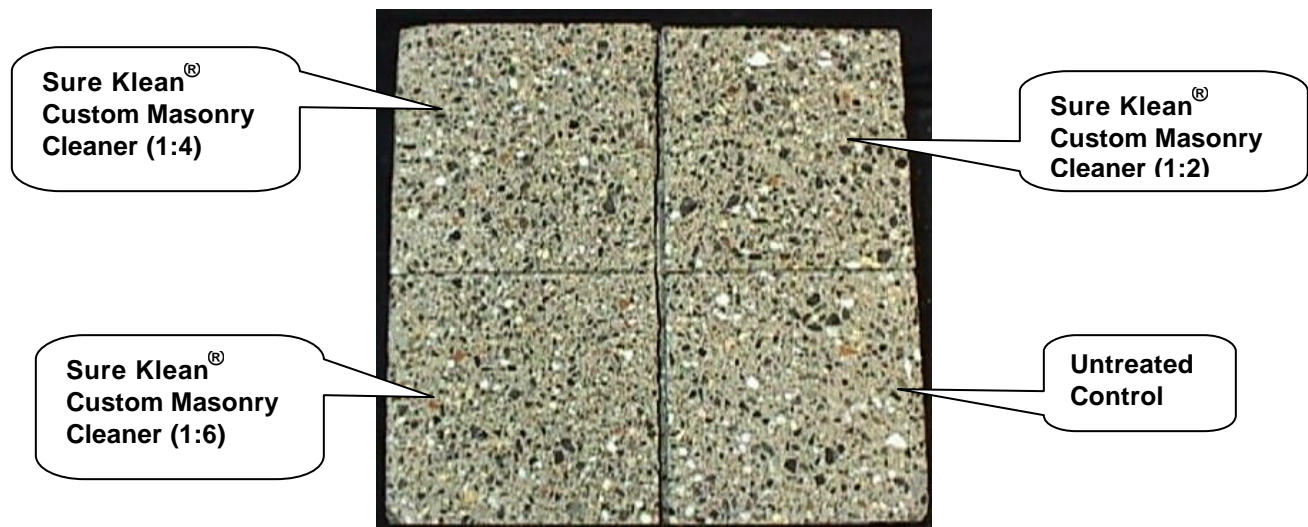




# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 23

“2512” ground-face, 3 Day Cleaning

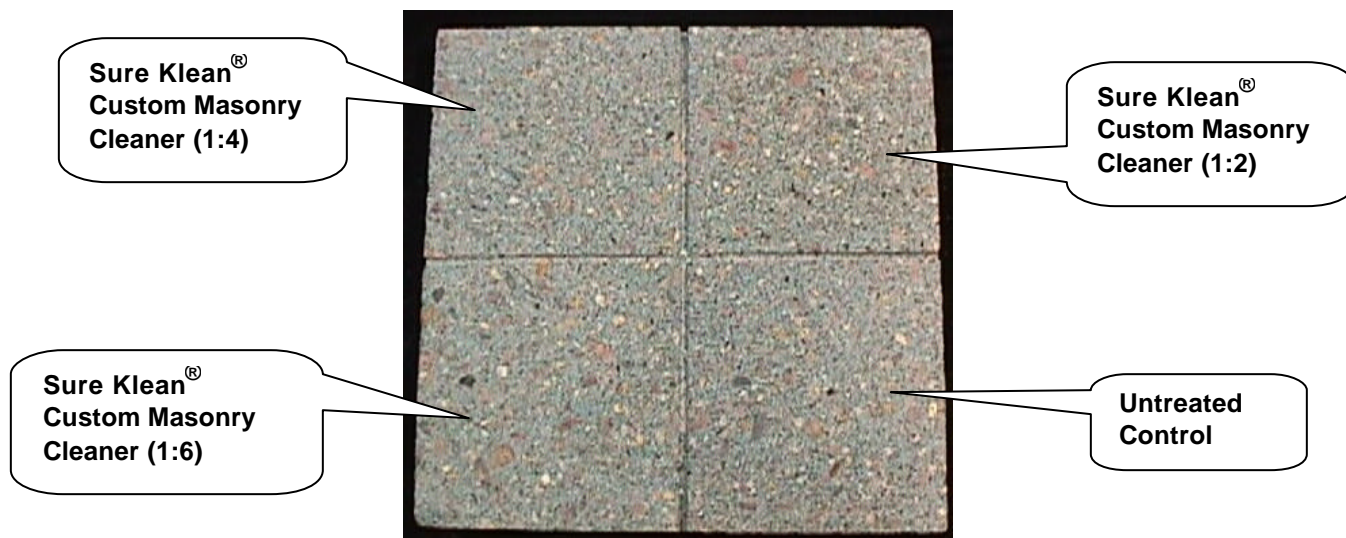


“2512” ground-face, 7 Day Cleaning

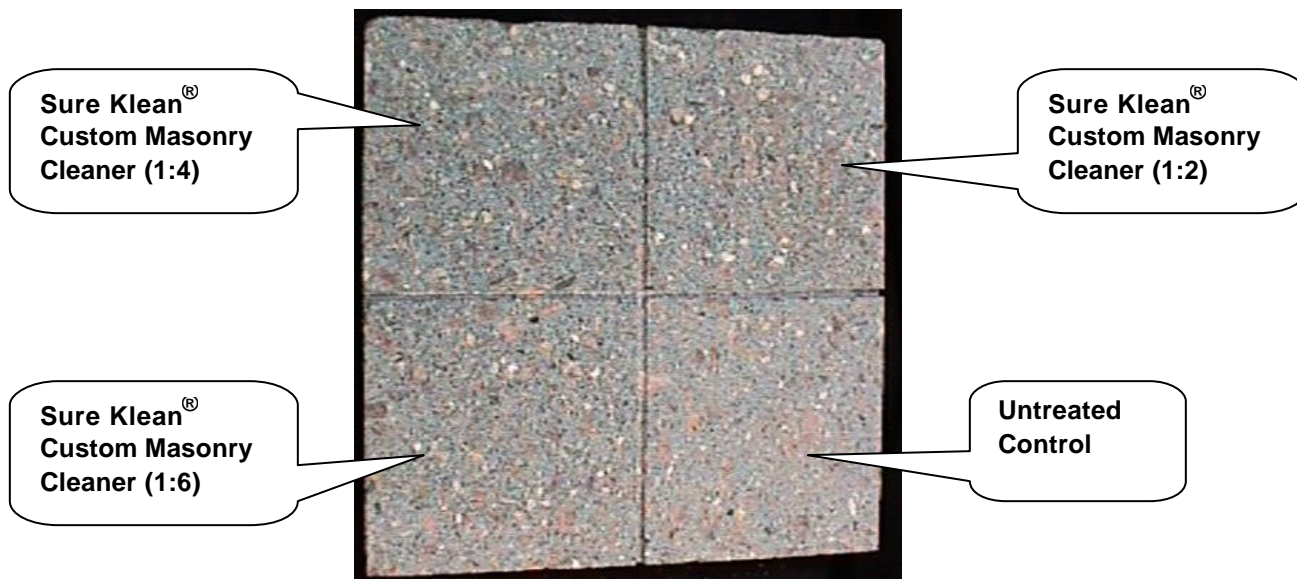




# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 24

"2512" ground-face, 14 Day Cleaning

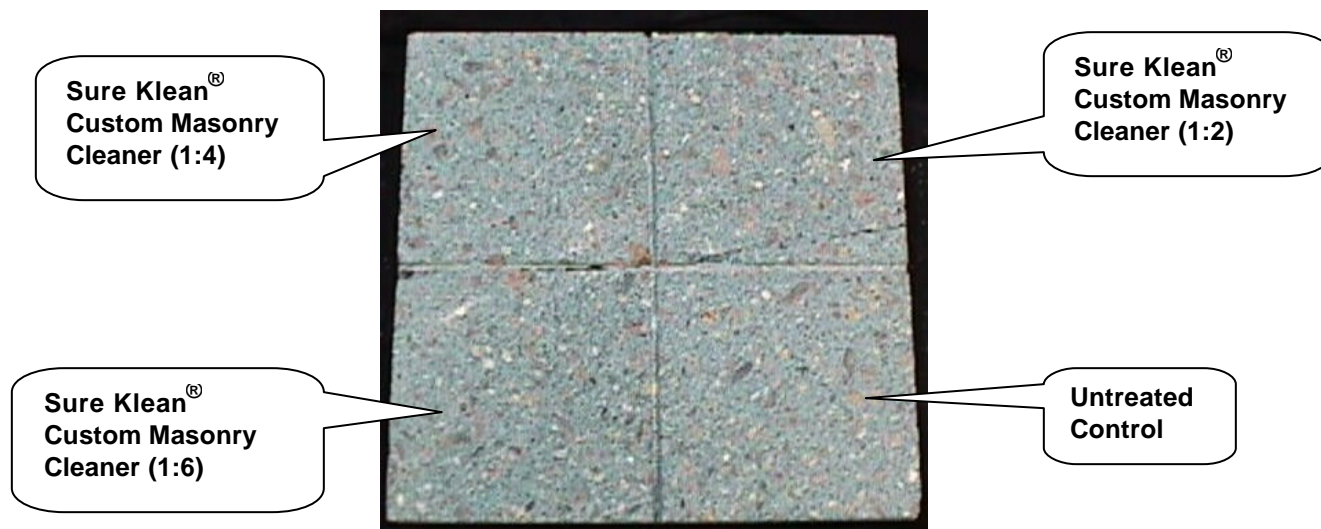

## CONCLUSIONS - Cleaning


Based upon the test data, all of the submitted block samples were efficiently cleaned with each dilution of the selected PROSOCO Inc.'s cleaning products. Use higher concentrations and surface agitation to maximize aggregate exposure. Use low concentration and surface agitation to minimize aggregate exposure.

All dilutions of Sure Klean® Custom Masonry Cleaner tested affected the substrate in a similar manner, removing slight to heavy concentrations of pigmented matrix from the rough and smooth block faces, exposing small and large aggregate, and enhancing the natural appearance of the integrally colored concrete masonry unit.





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 25**

---

## RECOMMENDED PRODUCTS AND DILUTIONS - CLEANING

Recommendations for cleaning for each type of CMU submitted by A. Jandris & Sons, Inc., Gardner, MA are provided in the chart below. Recommendations are based on the optimum dilution for complete removal of mortar.


Block	New Construction Cleaning (Type S mortar, 14 day)
All Submitted CMU's	Sure Klean <sup>®</sup> Custom Masonry Cleaner (1:6)

The most appropriate cleaner and dilution should be determined on the specific job-site, and will be dependent primarily on the nature and severity of soiling present at that location. Pressure rinsing equipment providing at least 400 psi at 4-6 gpm delivered through a 15-40 degree fan spray often produces best cleaning results.

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate cleaning product and procedures for a particular project. See product literature for additional application and product information.



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 26**

---

## **SECTION B – COLOR UNIFORMITY:**

### **DESCRIPTION OF PRODUCTS EVALUATED – Color Uniformity:**

**Sure Klean® Custom Masonry Cleaner** – A general purpose, concentrated acidic cleaner for most custom masonry and colored concrete. Removes concrete splashes, excess mortar, mud, heavy efflorescence and surface soiling, leaving the masonry clean and uniform with no acid burning or streaking. Liquid concentrate for dilution with 2-6 parts water. Apply by brush or low-pressure spray.

---

### **TEST METHOD – Color Uniformity Testing:**


Dilution ratios refer to mixtures of concentrated cleaner : fresh water.

1. Prewet the surface with water.
2. Apply each cleaner at the appropriate dilutions.
3. Allow appropriate dwell time, as specified.  
Custom Masonry Cleaner ..... 3 minutes
4. Reapply the products and moderately agitate with a brush.
5. Pressure rinse thoroughly.\*
6. Allow the sample to dry for at least 18 hours and visually examine.
7. Break the sample in half and compare the through-body surfaces to the cleaned surfaces for the best match.

\* Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 27

## TEST RESULTS – Color Uniformity

Substrate: Rough-face		Pigment Color: “LT-N” rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: “LT-1” rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: “LT-3” rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: “LT-13” rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 28

## TEST RESULTS – Color Uniformity Continued

Substrate: Rough-face		Pigment Color: "LT-14" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: "LT-17" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: "LT-18" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: "DK-6" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 29

## TEST RESULTS – Color Uniformity Continued

Substrate: Rough-face		Pigment Color: "DK-9" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: "DK-12" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: "DK-16" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: "DK-19" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 30

## Test results- Color Uniformity Continued

Substrate: Rough-face		Pigment Color: "DK-21" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: "DK-22" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	3	1
Custom Masonry Cleaner	1:4	3	2
Custom Masonry Cleaner	1:6	2	4
Substrate: Rough-face		Pigment Color: "9312" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Rough-face		Pigment Color: "5110" rough-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	3	4
Custom Masonry Cleaner	1:6	3	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 31

## TEST RESULTS- Color Uniformity Continued

<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2501" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2502" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2503" rough-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2504" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 32

## TEST RESULTS- Color Uniformity Continued

<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2505" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2506" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2507" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2508" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body

2 – **Fair** match to through-body


3 – **Good** match to through-body

4 – **Best** match to through-body





# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 33

## TEST RESULTS- Color Uniformity Continued

<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2509" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	3	4
Custom Masonry Cleaner	1:6	3	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2510" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2511" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "2512" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 34

## TEST RESULTS- Color Uniformity Continued

<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9301" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9302" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9303" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9304" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 35

## TEST RESULTS- Color Uniformity Continued

<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9305" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9306" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9307" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9308" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 36**

**TEST RESULTS- Color Uniformity Continued**

<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9309" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9310" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9311" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "9312" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 37

## TEST RESULTS- Color Uniformity Continued

<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "510" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "520" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "530" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "540" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 38

## TEST RESULTS- Color Uniformity Continued

Substrate: Ground-face, coated		Pigment Color: "560" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	3	4
Custom Masonry Cleaner	1:6	3	4
Substrate: Ground-face, coated		Pigment Color: "570" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face, coated		Pigment Color: "580" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face, coated		Pigment Color: "590" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	3
Custom Masonry Cleaner	1:4	4	3
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 39**

**TEST RESULTS- Color Uniformity Continued**

<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "5100" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "5110" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "5120" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face, coated		<b>Pigment Color:</b> "5200" ground-face coated	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 40

## TEST RESULTS- Color Uniformity Continued

Substrate: Ground-face		Pigment Color: "2501" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2502" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2503" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2504" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body

2 – **Fair** match to through-body


3 – **Good** match to through-body

4 – **Best** match to through-body





# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 41

## TEST RESULTS- Color Uniformity Continued

Substrate: Ground-face		Pigment Color: "2505" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2506" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2507" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2508" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 42

## TEST RESULTS- Color Uniformity Continued

Substrate: Ground-face		Pigment Color: "2509" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2510" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2511" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "2512" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 43

## TEST RESULTS- Color Uniformity Continued

Substrate: Ground-face		Pigment Color: "9301" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "9302" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "9303" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "9304" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 44

## TEST RESULTS- Color Uniformity Continued

Substrate: Ground-face		Pigment Color: "9305" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "9306" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "9307" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "9308" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 45**

**TEST RESULTS- Color Uniformity Continued**

<b>Substrate:</b> Ground-face		<b>Pigment Color:</b> "9309" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face		<b>Pigment Color:</b> "9310" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face		<b>Pigment Color:</b> "9311" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face		<b>Pigment Color:</b> "9312" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 46

## TEST RESULTS- Color Uniformity Continued

Substrate: Ground-face		Pigment Color: "510" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "520" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "530" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "540" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 47**

**TEST RESULTS- Color Uniformity Continued**

<b>Substrate:</b> Ground-face		<b>Pigment Color:</b> "560" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face		<b>Pigment Color:</b> "570" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face		<b>Pigment Color:</b> "580" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
<b>Substrate:</b> Ground-face		<b>Pigment Color:</b> "590" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body


2 – **Fair** match to through-body

3 – **Good** match to through-body

4 – **Best** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 48

## TEST RESULTS- Color Uniformity Continued

Substrate: Ground-face		Pigment Color: "5100" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "5110" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	3	4
Custom Masonry Cleaner	1:6	3	4
Substrate: Ground-face		Pigment Color: "5120" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Substrate: Ground-face		Pigment Color: "5200" ground-face	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4

Scale used for reporting results of both categories

0 – **Worst** match to through-body

1 – **Poor** match to through-body

2 – **Fair** match to through-body


3 – **Good** match to through-body

4 – **Best** match to through-body





# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.


Page 49

## PHOTOGRAPHS – Color Uniformity

“LT-N” rough-face after cleaning

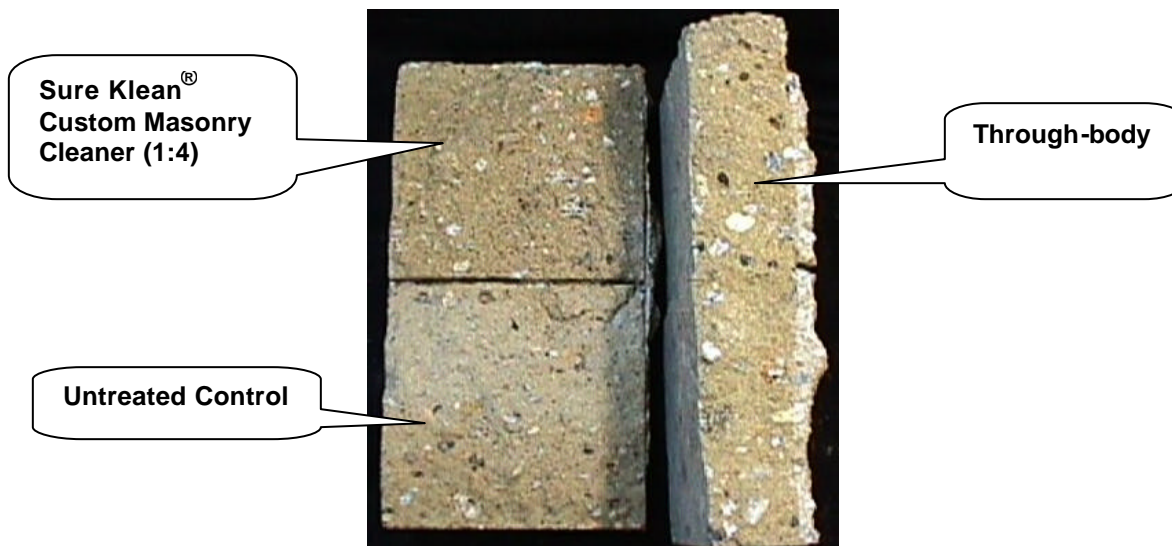


“2501” ground-face after cleaning

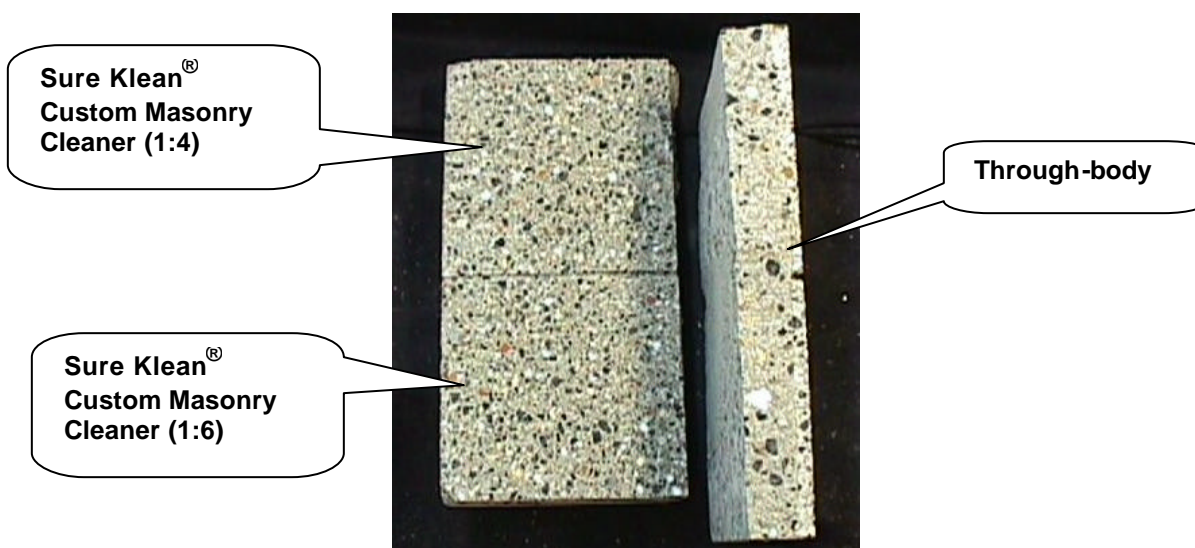



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 50**

---


**PHOTOGRAPHS- Color Uniformity Continued**

**“2512” rough-face after cleaning**





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 51**

---

## CONCLUSIONS - COLOR UNIFORMITY:

All dilutions of Sure Klean<sup>®</sup> Custom Masonry Cleaner tested affected the substrate in a similar manner. Higher concentrations of cleaner removed moderate to heavy concentrations of pigmented matrix, exposing small and large aggregate. Lower concentrations of cleaner removed slight to moderate concentrations of pigmented matrix, exposing small and large aggregate. All dilutions enhanced the natural appearance of the integrally colored CMU.

---

## RECOMMENDATIONS - COLOR UNIFORMITY

Recommendations for color uniformity for each type of CMU submitted by A. Jandris & Sons, Inc., Gardner, MA are provided in the chart below. Recommendations are based on the optimum dilution that provides the best color uniformity and the complete removal of mortar.


Block	Color Uniformity
"5110" rough-face, "5110" ground-face	Sure Klean <sup>®</sup> Custom Masonry Cleaner (1:2)
All Other Submitted Samples	Sure Klean <sup>®</sup> Custom Masonry Cleaner (1:6)

The most appropriate cleaner and dilution should be determined on the specific job-site, and will be dependent primarily on the nature and severity of soiling present at that location. Pressure rinsing equipment providing at least 400 psi at 4-6 gpm delivered through a 15-40 degree fan spray often produces best cleaning results.

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate cleaning product and procedures for a particular project. See product literature for additional application and product information.



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 52**

---

## **SECTION C - PROTECTIVE WATER REPELLENTS:**

The testing described below evaluates the suitability of water repellent treatments.

The surface treatments evaluated were selected for their suitability for application based on the following selection criteria:

1. Weatherproofing properties
2. Color change
3. Ease of application

---

## **DESCRIPTIONS OF PRODUCTS EVALUATED - Protective Water Repellents:**

**Sure Klean® Custom Masonry Sealer** -- A clear, solvent-based silicone elastomer formulated to weatherproof custom masonry units, cast stone, architectural concrete block, precast concrete, wood, and porous masonry. Custom Masonry Sealer penetrates and fills pores to prevent water penetration through exterior walls expose to normal weathering.

---

## **SAMPLE PREPARATION - Protective Water Repellents:**

The submitted blocks were scored, allowed to dry, and to reabsorb atmospheric humidity for 24 hours prior to treatment. The treatment method consisted of a wet-on-wet brush application. All treatments were allowed to cure at least 3 days prior to testing.

---


## **TEST METHODS - Protective Water Repellents:**

### **Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes**

The water absorption tube test simulating wind driven rain conditions was performed. This test simulates 60 mile per hour wind driven rain conditions for a period of 20 minutes. See Technical Services TECH Note RILEM Tube Test Procedures.



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 53**


## TEST RESULTS - Protective Water Repellents

### Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes

RESULTS	
"LT-N" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"LT-1" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"LT-3" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"LT-13" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"LT-14" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"LT-17" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"LT-18" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"DK-6" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"DK-9" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	57 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 54**

**TEST RESULTS - Protective Water Repellents continued**

"DK-12" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	56 mph
"DK-16" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	58 mph
"DK-19" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"DK-21" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"DK-22" rough-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"9312" rough-face	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
"5110" rough-face	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
"2501" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"2502" ground-face, coated	
Untreated Control	50 mph
Custom Masonry Sealer	59 mph
"2503" ground-face, coated	
Untreated Control	43 mph
Custom Masonry Sealer	59 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 55**

**TEST RESULTS - Protective Water Repellents continued**

"2504" ground-face, coated	
Untreated Control	45 mph
Custom Masonry Sealer	56 mph
"2505" ground-face, coated	
Untreated Control	46 mph
Custom Masonry Sealer	60 mph
"2506" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"2507" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	48 mph
"2508" ground-face, coated	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
"2509" ground-face, coated	
Untreated Control	57 mph
Custom Masonry Sealer	59 mph
"2510" ground-face, coated	
Untreated Control	55 mph
Custom Masonry Sealer	58 mph
"2511" ground-face, coated	
Untreated Control	52 mph
Custom Masonry Sealer	59 mph
"2512" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	56 mph
"9301" ground-face, coated	
Untreated Control	48 mph
Custom Masonry Sealer	59 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 56**


**TEST RESULTS - Protective Water Repellents continued**

"9302" ground-face, coated	
Untreated Control	53 mph
Custom Masonry Sealer	60 mph
"9303" ground-face, coated	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
"9304" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	58 mph
"9305" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"9306" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"9307" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"9308" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	58 mph
"9309" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"9310" ground-face, coated	
Untreated Control	54 mph
Custom Masonry Sealer	57 mph
"9311" ground-face, coated	
Untreated Control	57 mph
Custom Masonry Sealer	60 mph





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 57**

**TEST RESULTS - Protective Water Repellents continued**

"9312" ground-face, coated	
Untreated Control	56 mph
Custom Masonry Sealer	60 mph
"510" ground-face, coated	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
"520" ground-face, coated	
Untreated Control	55 mph
Custom Masonry Sealer	60 mph
"530" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"540" ground-face, coated	
Untreated Control	45 mph
Custom Masonry Sealer	60 mph
"560" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"570" ground-face, coated	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
"580" ground-face, coated	
Untreated Control	54 mph
Custom Masonry Sealer	60 mph
"590" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"5100" ground-face, coated	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 58**

**TEST RESULTS - Protective Water Repellents continued**

"5110" ground-face, coated	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"5120" ground-face, coated	
Untreated Control	47 mph
Custom Masonry Sealer	58 mph
"5200" ground-face, coated	
Untreated Control	47 mph
Custom Masonry Sealer	60 mph
"2501" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	52 mph
"2502" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	55 mph
"2503" ground-face	
Untreated Control	52 mph
Custom Masonry Sealer	57 mph
"2504" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	58 mph
"2505" ground-face	
Untreated Control	56 mph
Custom Masonry Sealer	57 mph
"2506" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	58 mph
"2507" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	58 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 59**

**TEST RESULTS - Protective Water Repellents continued**

"2508" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"2509" ground-face	
Untreated Control	42 mph
Custom Masonry Sealer	59 mph
"2510" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"2511" ground-face	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
"2512" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"9301" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	58 mph
"9302" ground-face	
Untreated Control	46 mph
Custom Masonry Sealer	59 mph
"9303" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	56 mph
"9304" ground-face	
Untreated Control	54 mph
Custom Masonry Sealer	60 mph
"9305" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 60**

**TEST RESULTS - Protective Water Repellents continued**

"9306" ground-face	
Untreated Control	43 mph
Custom Masonry Sealer	59 mph
"9307" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"9308" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"9309" ground-face	
Untreated Control	56 mph
Custom Masonry Sealer	58 mph
"9310" ground-face	
Untreated Control	46 mph
Custom Masonry Sealer	60 mph
"9311" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	56 mph
"9312" ground-face	
Untreated Control	45 mph
Custom Masonry Sealer	52 mph
"510" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	60 mph
"520" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	51 mph
"530" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 61**

**TEST RESULTS - Protective Water Repellents continued**

"540" ground-face	
Untreated Control	46 mph
Custom Masonry Sealer	57 mph
"560" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	57 mph
"570" ground-face	
Untreated Control	50 mph
Custom Masonry Sealer	60 mph
"580" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"590" ground-face	
Untreated Control	45 mph
Custom Masonry Sealer	60 mph
"5100" ground-face	
Untreated Control	56 mph
Custom Masonry Sealer	60 mph
"5110" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	59 mph
"5120" ground-face	
Untreated Control	46 mph
Custom Masonry Sealer	60 mph
"5200" ground-face	
Untreated Control	< 40 mph
Custom Masonry Sealer	58 mph



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.


Page 62

## PHOTOGRAPHS – Protective Water Repellents

“DK-21” rough-face surface beading

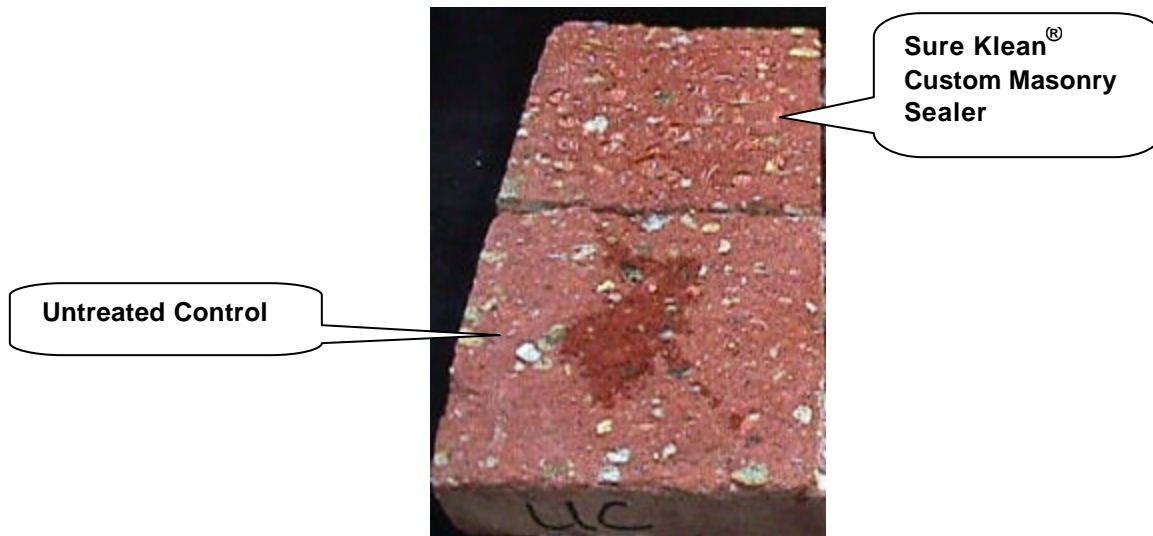

“2511” ground-face coated surface beading

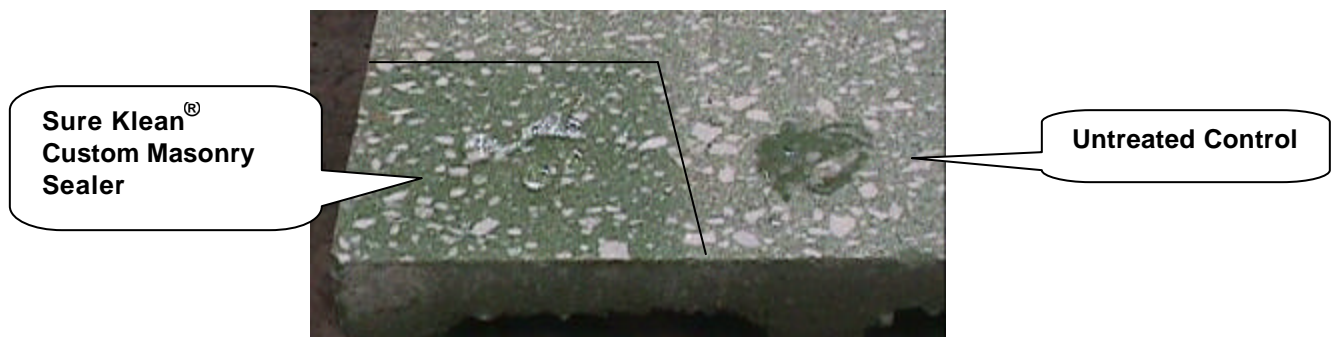


“570” ground-face surface beading





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 63**

---

## **CONCLUSIONS - Protective Water Repellents**

Based upon laboratory evaluations, Sure Klean<sup>®</sup> Custom Masonry Sealer provided sufficient water repellency to all of the submitted samples.

---

## **RECOMMENDATIONS - PROTECTIVE WATER REPELLENTS**


Recommendations for water repellency treatment for each type of CMU submitted by A. Jandris & Sons Inc., Gardner, MA are provided in the chart below. Recommendations are based on the treatment that proved most effective and can provide water repellency on all types submitted.

<b>Block</b>	<b>Water Repellents</b>	<b>Dilution</b>
All Submitted CMU's	Sure Klean <sup>®</sup> Custom Masonry Sealer	Concentrate

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate water repellent product and procedures for a particular project. See product literature for additional application and product information.



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 64**

---

## **SECTION D – GRAFFITI CONTROL**

### **DESCRIPTION OF PRODUCTS EVALUATED**

These trials were conducted to determine the optimal graffiti control treatment.

#### **Graffiti Control Treatments**

**Sure Klean® Weather Seal Blok-Guard® & Graffiti Control** – A clear, solvent-based silicone elastomer formulated to weatherproof custom masonry units, cast stone, architectural concrete block, precast concrete, wood, and porous masonry. Weather Seal Blok-Guard® & Graffiti Control penetrates and fills pores to prevent water penetration through exterior walls expose to normal weathering.

#### **Products Evaluated for Graffiti Removal**

**Defacer Eraser® Graffiti Wipe** – An easy-to-use graffiti remover that does not contain methanol, methylene chloride or other “halogenated” solvents prohibited on many projects. Graffiti Wipe removes a variety of graffiti stains from most smooth masonry, wood and metal surfaces.

**Defacer Eraser® Graffiti Release** – An easy-to-use graffiti remover that does not contain methanol, methylene chloride or other “halogenated” solvents prohibited on many projects. Graffiti Release removes a variety of graffiti stains from most smooth masonry, wood and metal surfaces.

**Sure Klean® Fast Acting Stripper** – A thixotropic stripping compound formulated specifically for removal of high strength paints and coatings such as epoxies, polyurethanes, and floor enamels. Additionally, Fast Acting Stripper dissolves most spray paints, marking pens, lacquers and other graffiti.


#### **Graffiti Agents**

Interior/Exterior Spray Paint (Black)  
Permanent Marker (Green)  
Permanent Marker (Red)  
Permanent Marker (Black)





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 65**

---

## **SAMPLE PREPARATION – Graffiti Control**

This evaluation compares the effectiveness in preventing staining of enamel spray paint and permanent markers.

Sections of the concrete samples were treated with Sure Klean® Weather Seal Blok-Guard® & Graffiti Control in accordance with PROSOCO, Inc.'s Product Guide application.

Removal of the graffiti agents was attempted 24 hours after application of the graffiti agents, using either Defacer Eraser® Graffiti Wipe, Sure Klean® Fast Acting Stripper or Defacer Eraser® Graffiti Release.

---

## **TEST METHOD – Graffiti Control**


Chemical cleaners were evaluated using the following procedure:

1. Apply the product to a dry surface, soiled with graffiti.
2. Allow appropriate dwell time:  
    Graffiti Wipe ..... 5 minutes  
    Fast Acting Stripper ..... 20 minutes  
    Graffiti Release..... 15 minutes
3. Pressure rinse thoroughly until water runs clear. \*
4. Allow the surface to dry thoroughly and visually examine to determine effectiveness.

\* Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 66

## TEST RESULTS – Graffiti Control

“LT-N” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	65%	65%	52%
Graffiti Wipe	70%	75%	70%	75%	73%
Graffiti Release	70%	60%	65%	60%	64%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	85%	85%	85%
Graffiti Wipe	90%	85%	85%	90%	88%
Graffiti Release	75%	75%	80%	80%	78%
“LT-1” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	60%	50%	50%	55%
Graffiti Wipe	60%	50%	50%	55%	54%
Graffiti Release	50%	50%	55%	50%	51%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	80%	80%	85%	80%
Graffiti Wipe	90%	80%	80%	80%	83%
Graffiti Release	70%	70%	80%	80%	75%
“LT-3” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	60%	60%	60%	60%
Graffiti Wipe	60%	55%	60%	60%	56%
Graffiti Release	50%	55%	60%	60%	43%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	80%	85%	83%
Graffiti Wipe	95%	80%	85%	80%	85%
Graffiti Release	90%	80%	85%	85%	85%
“LT-13” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	65%	50%	55%	60%
Graffiti Wipe	60%	50%	55%	55%	55%
Graffiti Release	60%	50%	50%	50%	52%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	95%	90%	90%	89%
Graffiti Wipe	80%	95%	85%	95%	89%
Graffiti Release	80%	90%	90%	90%	83%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 67

## TEST RESULTS – Graffiti Control (Continued)

“LT-14” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	60%	65%	64%
Graffiti Wipe	60%	50%	55%	60%	56%
Graffiti Release	50%	50%	60%	65%	56%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	90%	85%	84%
Graffiti Wipe	80%	85%	90%	80%	84%
Graffiti Release	75%	80%	85%	85%	81%
“LT-17” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	60%	70%	65%
Graffiti Wipe	70%	50%	50%	55%	56%
Graffiti Release	60%	60%	50%	50%	55%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	80%	80%	83%
Graffiti Wipe	90%	85%	80%	85%	85%
Graffiti Release	70%	80%	80%	80%	73%
“LT-18” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	65%	70%	70%	66%
Graffiti Wipe	65%	70%	55%	60%	63%
Graffiti Release	65%	50%	60%	60%	59%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	95%	90%	90%	88%
Graffiti Wipe	90%	85%	90%	90%	86%
Graffiti Release	80%	75%	85%	85%	83%
“DK-6” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	60%	50%	60%	58%
Graffiti Wipe	60%	55%	55%	50%	55%
Graffiti Release	50%	40%	50%	50%	43%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	85%	85%	80%	85%
Graffiti Wipe	90%	85%	90%	90%	86%
Graffiti Release	80%	80%	85%	80%	81%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 68

## TEST RESULTS – Graffiti Control (Continued)

“DK-9” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	60%	60%	60%	60%
Graffiti Wipe	65%	60%	60%	65%	63%
Graffiti Release	60%	60%	60%	65%	62%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	85%	85%	90%	88%
Graffiti Wipe	95%	90%	95%	95%	94%
Graffiti Release	90%	75%	90%	90%	86%
“DK-12” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	60%	70%	65%
Graffiti Wipe	65%	60%	60%	65%	63%
Graffiti Release	50%	60%	70%	65%	61%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	85%	90%	90%
Graffiti Wipe	95%	90%	95%	95%	94%
Graffiti Release	90%	85%	90%	85%	88%
“DK-16” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	55%	65%	50%	60%	58%
Graffiti Wipe	60%	50%	50%	60%	55%
Graffiti Release	60%	50%	50%	55%	54%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	80%	85%	83%
Graffiti Wipe	85%	90%	85%	85%	86%
Graffiti Release	75%	80%	80%	85%	80%
“DK-19” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	55%	50%	60%	44%
Graffiti Wipe	65%	60%	55%	60%	60%
Graffiti Release	55%	50%	50%	55%	53%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	90%	85%	85%	80%	85%
Graffiti Release	65%	85%	85%	80%	79%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 69

## TEST RESULTS – Graffiti Control (Continued)

“DK-21” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	60%	60%	55%	63%
Graffiti Wipe	75%	55%	60%	60%	63%
Graffiti Release	70%	55%	55%	55%	59%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	90%	90%	90%
Graffiti Wipe	90%	90%	85%	90%	89%
Graffiti Release	90%	85%	90%	90%	89%
“DK-22” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	60%	65%	60%	61%
Graffiti Wipe	70%	65%	60%	60%	64%
Graffiti Release	60%	60%	60%	55%	59%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	85%	95%	93%
Graffiti Wipe	90%	90%	80%	90%	83%
Graffiti Release	85%	90%	85%	90%	88%
“9132” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	60%	70%	65%
Graffiti Wipe	70%	70%	60%	65%	66%
Graffiti Release	60%	60%	60%	65%	64%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	90%	85%	84%
Graffiti Wipe	90%	80%	90%	80%	85%
Graffiti Release	75%	70%	90%	85%	80%
“5110” rough-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	55%	60%	50%	50%	54%
Graffiti Wipe	60%	50%	60%	55%	56%
Graffiti Release	60%	40%	45%	40%	46%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	90%	85%	80%	83%
Graffiti Wipe	85%	90%	90%	80%	86%
Graffiti Release	85%	85%	85%	80%	84%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 70

## TEST RESULTS – Graffiti Control (Continued)

“2501” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	65%	65%	65%	61%
Graffiti Wipe	95%	90%	90%	90%	91%
Graffiti Release	10%	40%	40%	40%	33%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	60%	60%	60%	58%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	70%	70%	70%	70%	70%
“2502” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	55%	55%	55%	56%
Graffiti Wipe	95%	85%	85%	85%	88%
Graffiti Release	10%	30%	30%	30%	25%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	60%	60%	60%	60%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	75%	75%	75%	75%	75%
“2503” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	30%	80%	80%	80%	68%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	90%	90%	90%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	80%	80%	80%	80%	80%
“2504” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	85%	85%	85%	88%
Graffiti Wipe	100%	90%	90%	90%	93%
Graffiti Release	70%	60%	60%	60%	63%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	90%	90%	91%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	85%	80%	80%	80%	81%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 71

## TEST RESULTS – Graffiti Control (Continued)

“2505” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	20%	85%	85%	85%	69%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	95%	95%	100%	98%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	100%	85%	85%	85%	89%
“2506” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	80%	80%	80%	83%
Graffiti Wipe	95%	90%	95%	90%	93%
Graffiti Release	10%	50%	50%	50%	40%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	85%	85%	85%	86%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	20%	75%	75%	75%	61%
“2507” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	100%	90%	90%	90%	96%
Graffiti Release	30%	50%	50%	50%	45%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	60%	50%	50%	50%	53%
“2508” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	70%	70%	63%
Graffiti Wipe	90%	80%	80%	80%	83%
Graffiti Release	10%	40%	40%	40%	33%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	75%	75%	75%	75%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	30%	60%	60%	60%	53%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 72


## TEST RESULTS – Graffiti Control (Continued)

“2509” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	70%	70%	63%
Graffiti Wipe	95%	90%	90%	90%	91%
Graffiti Release	85%	90%	85%	85%	86%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	70%	70%	70%	70%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	70%	70%	70%	70%	70%
“2510” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	60%	60%	60%	63%
Graffiti Wipe	80%	60%	60%	60%	65%
Graffiti Release	20%	40%	40%	40%	35%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	85%	85%	81%
Graffiti Wipe	90%	95%	100%	100%	96%
Graffiti Release	40%	50%	50%	50%	43%
“2511” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	60%	90%	90%	90%	83%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	75%	90%	90%	90%	86%
“2512” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	80%	80%	75%	76%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	40%	80%	80%	80%	70%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	75%	76%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	80%	70%	70%	70%	73%





# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 73

## TEST RESULTS – Graffiti Control (Continued)

“9301” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	90%	90%	90%	86%
Graffiti Wipe	95%	85%	85%	85%	88%
Graffiti Release	30%	50%	50%	50%	45%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	95%	100%	95%	95%	96%
Graffiti Release	80%	70%	70%	70%	73%
“9302” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	80%	80%	80%	61%
Graffiti Wipe	95%	85%	85%	85%	88%
Graffiti Release	30%	50%	50%	50%	45%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	80%	80%	80%	76%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	30%	60%	60%	60%	43%
“9303” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	70%	70%	63%
Graffiti Wipe	90%	90%	90%	90%	90%
Graffiti Release	30%	40%	40%	40%	38%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	90%	90%	90%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	90%	70%	70%	70%	75%
“9304” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	85%	85%	81%
Graffiti Wipe	95%	95%	95%	90%	91%
Graffiti Release	20%	40%	40%	40%	35%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	40%	70%	70%	70%	63%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 74

## TEST RESULTS – Graffiti Control (Continued)

“9305” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	80%	80%	80%	73%
Graffiti Wipe	100%	90%	90%	90%	93%
Graffiti Release	20%	75%	75%	75%	61%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	65%	80%	80%	80%	76%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	75%	70%	70%	70%	71%
“9306” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	90%	90%	90%	86%
Graffiti Wipe	100%	80%	85%	90%	89%
Graffiti Release	20%	20%	40%	40%	30%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	90%	90%	90%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	80%	70%	80%	80%	73%
“9307” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	40%	70%	70%	70%	63%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	70%	70%	70%	70%	70%
“9308” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	70%	70%	70%	70%
Graffiti Wipe	95%	70%	70%	70%	76%
Graffiti Release	30%	60%	60%	60%	53%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	65%	75%	75%	75%	73%
Graffiti Wipe	95%	90%	95%	95%	91%
Graffiti Release	60%	70%	70%	70%	63%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 75

## TEST RESULTS – Graffiti Control (Continued)

“9309” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	80%	65%	65%	65%
Graffiti Wipe	95%	75%	75%	75%	80%
Graffiti Release	40%	75%	75%	75%	66%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	80%	80%	80%	75%
Graffiti Wipe	95%	90%	90%	90%	91%
Graffiti Release	80%	70%	70%	70%	73%
“9310” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	65%	80%	80%	80%	76%
Graffiti Wipe	95%	85%	85%	85%	83%
Graffiti Release	40%	80%	80%	80%	70%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	70%	70%	70%	70%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	90%	80%	80%	80%	83%
“9311” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	60%	60%	60%	53%
Graffiti Wipe	90%	80%	80%	80%	83%
Graffiti Release	20%	70%	70%	70%	58%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	80%	80%	80%	75%
Graffiti Wipe	90%	95%	90%	90%	91%
Graffiti Release	80%	80%	80%	80%	80%
“9312” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	70%	70%	70%	65%
Graffiti Wipe	95%	85%	85%	85%	88%
Graffiti Release	40%	85%	85%	85%	54%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	80%	80%	80%	75%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	70%	75%	75%	75%	74%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 76

## TEST RESULTS – Graffiti Control (Continued)

“510” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	60%	60%	60%	53%
Graffiti Wipe	90%	85%	85%	85%	86%
Graffiti Release	10%	30%	30%	30%	25%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	80%	80%	80%	76%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	30%	80%	80%	80%	65%
“520” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	60%	60%	60%	60%
Graffiti Wipe	90%	85%	85%	85%	86%
Graffiti Release	10%	40%	40%	40%	33%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	85%	85%	84%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	65%	70%	70%	70%	69%
“530” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	80%	80%	80%	73%
Graffiti Wipe	100%	90%	90%	90%	93%
Graffiti Release	20%	60%	60%	60%	50%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	65%	70%	70%	70%	66%
“540” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	75%	75%	75%	71%
Graffiti Wipe	90%	90%	90%	90%	90%
Graffiti Release	75%	75%	75%	75%	75%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	80%	80%	80%	80%	80%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 77

## TEST RESULTS – Graffiti Control (Continued)

“560” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	95%	80%	80%	80%	84%
Graffiti Release	65%	80%	80%	80%	76%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	90%	90%	90%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	75%	80%	80%	80%	79%
“570” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	65%	75%	75%	75%	72%
Graffiti Wipe	95%	85%	85%	85%	88%
Graffiti Release	20%	40%	40%	40%	35%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	90%	90%	90%	86%
Graffiti Wipe	100%	95%	95%	95%	96%
Graffiti Release	50%	60%	60%	60%	53%
“580” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	60%	60%	60%	60%
Graffiti Wipe	95%	80%	80%	80%	84%
Graffiti Release	10%	50%	50%	50%	40%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	50%	60%	60%	60%	53%
“590” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	70%	70%	70%	70%
Graffiti Wipe	95%	90%	90%	90%	91%
Graffiti Release	20%	30%	30%	30%	28%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	80%	80%	80%	73%
Graffiti Wipe	100%	100%	100%	100%	100%
Graffiti Release	50%	40%	40%	40%	43%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 78

## TEST RESULTS – Graffiti Control (Continued)

“5100” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	70%	70%	70%	65%
Graffiti Wipe	90%	90%	90%	90%	90%
Graffiti Release	30%	70%	70%	70%	60%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	70%	70%	70%	63%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	80%	70%	70%	70%	73%
“5110” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	70%	70%	70%	63%
Graffiti Wipe	80%	70%	70%	70%	73%
Graffiti Release	50%	70%	70%	70%	65%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	80%	80%	80%	73%
Graffiti Wipe	90%	90%	90%	90%	90%
Graffiti Release	80%	80%	80%	80%	80%
“5120” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	50%	50%	50%	50%
Graffiti Wipe	90%	80%	80%	80%	83%
Graffiti Release	20%	40%	40%	40%	35%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	70%	70%	70%	70%
Graffiti Wipe	95%	90%	90%	90%	91%
Graffiti Release	85%	80%	80%	80%	81%
“5200” ground-face coated					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	30%	70%	70%	70%	60%
Graffiti Wipe	90%	85%	85%	85%	86%
Graffiti Release	10%	30%	30%	30%	25%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	80%	80%	80%	70%
Graffiti Wipe	90%	90%	90%	90%	90%
Graffiti Release	65%	70%	70%	70%	66%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 79

## TEST RESULTS – Graffiti Control (Continued)

“2501” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	40%	40%	40%	45%
Graffiti Wipe	80%	70%	70%	70%	73%
Graffiti Release	60%	30%	30%	30%	38%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	88%	88%	88%	86%
Graffiti Wipe	85%	95%	95%	95%	88%
Graffiti Release	60%	60%	60%	60%	60%
“2502” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	50%	50%	50%	50%
Graffiti Wipe	65%	60%	60%	60%	61%
Graffiti Release	30%	30%	30%	30%	30%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	70%	70%	70%	71%
Graffiti Wipe	90%	75%	75%	80%	80%
Graffiti Release	50%	30%	30%	30%	35%
“2503” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	70%	70%	70%	70%
Graffiti Wipe	95%	90%	90%	90%	91%
Graffiti Release	40%	70%	70%	70%	63%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	95%	95%	95%	91%
Graffiti Wipe	95%	95%	100%	100%	98%
Graffiti Release	30%	85%	85%	85%	71%
“2504” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	80%	80%	80%	84%
Graffiti Wipe	95%	80%	80%	80%	84%
Graffiti Release	90%	75%	75%	75%	79%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	90%	90%	91%
Graffiti Wipe	100%	98%	98%	98%	99%
Graffiti Release	90%	90%	90%	90%	90%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 80


## TEST RESULTS – Graffiti Control (Continued)

“2505” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	80%	80%	80%	83%
Graffiti Wipe	90%	80%	80%	80%	83%
Graffiti Release	40%	75%	75%	75%	44%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	100%	100%	98%
Graffiti Wipe	95%	95%	100%	100%	98%
Graffiti Release	75%	90%	95%	100%	90%
“2506” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	75%	70%	70%	69%
Graffiti Wipe	80%	90%	85%	85%	85%
Graffiti Release	40%	50%	50%	50%	43%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	95%	95%	95%	86%
Graffiti Wipe	80%	95%	95%	95%	91%
Graffiti Release	70%	70%	70%	70%	70%
“2507” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	25%	25%	25%	29%
Graffiti Wipe	70%	50%	50%	50%	55%
Graffiti Release	25%	20%	20%	20%	21%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	50%	50%	50%	58%
Graffiti Wipe	75%	65%	65%	65%	68%
Graffiti Release	60%	45%	45%	45%	49%
“2508” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	30%	40%	40%	40%	38%
Graffiti Wipe	20%	40%	40%	40%	35%
Graffiti Release	10%	30%	30%	30%	25%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	85%	95%	95%	95%	88%
Graffiti Release	50%	50%	50%	50%	50%





# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 81

## TEST RESULTS – Graffiti Control (Continued)

“2509” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	50%	50%	50%	43%
Graffiti Wipe	90%	50%	50%	50%	60%
Graffiti Release	40%	50%	50%	50%	48%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	90%	90%	90%	89%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	95%	85%	85%	85%	88%
“2510” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	30%	30%	30%	35%
Graffiti Wipe	75%	40%	40%	40%	49%
Graffiti Release	50%	50%	50%	50%	50%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	70%	70%	70%	71%
Graffiti Wipe	85%	90%	90%	90%	89%
Graffiti Release	60%	80%	80%	80%	75%
“2511” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	75%	75%	75%	69%
Graffiti Wipe	80%	70%	70%	70%	73%
Graffiti Release	85%	65%	65%	65%	70%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	95%	95%	95%	90%
Graffiti Wipe	95%	95%	95%	90%	94%
Graffiti Release	90%	80%	80%	90%	85%
“2512” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	50%	50%	50%	43%
Graffiti Wipe	85%	80%	80%	80%	81%
Graffiti Release	75%	65%	65%	65%	68%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	90%	90%	91%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	80%	70%	70%	70%	73%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 82

## TEST RESULTS – Graffiti Control (Continued)

“9301” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	60%	60%	60%	55%
Graffiti Wipe	70%	75%	75%	75%	74%
Graffiti Release	70%	55%	55%	55%	59%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	83%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	50%	70%	70%	70%	65%
“9302” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	30%	60%	60%	60%	53%
Graffiti Wipe	90%	60%	60%	60%	68%
Graffiti Release	50%	60%	60%	60%	58%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	80%	80%	80%	78%
Graffiti Wipe	90%	80%	80%	80%	88%
Graffiti Release	30%	70%	70%	70%	60%
“9303” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	80%	80%	80%	73%
Graffiti Wipe	75%	80%	80%	80%	79%
Graffiti Release	60%	75%	75%	75%	71%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	95%	95%	95%	90%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	90%	80%	80%	80%	88%
“9304” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	70%	70%	70%	70%
Graffiti Wipe	80%	70%	70%	70%	78%
Graffiti Release	75%	70%	70%	70%	71%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	88%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	50%	65%	65%	65%	61%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 83

## TEST RESULTS – Graffiti Control (Continued)

“9305” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	65%	70%	70%	70%	69%
Graffiti Wipe	95%	70%	70%	70%	76%
Graffiti Release	55%	70%	70%	70%	66%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	80%	80%	80%	78%
Graffiti Wipe	95%	90%	90%	90%	91%
Graffiti Release	65%	70%	70%	70%	69%
“9306” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	80%	80%	80%	81%
Graffiti Wipe	95%	90%	90%	90%	91%
Graffiti Release	90%	65%	65%	65%	71%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	95%	95%	93%
Graffiti Wipe	100%	95%	100%	95%	98%
Graffiti Release	50%	75%	85%	90%	75%
“9307” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	35%	70%	70%	70%	61%
Graffiti Wipe	40%	75%	75%	75%	66%
Graffiti Release	40%	75%	75%	75%	66%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	85%	85%	84%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	90%	90%	90%	90%	90%
“9308” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	30%	30%	30%	33%
Graffiti Wipe	75%	50%	50%	50%	56%
Graffiti Release	40%	30%	30%	30%	33%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	95%	95%	95%	59%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	75%	70%	70%	70%	71%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 84

## TEST RESULTS – Graffiti Control (Continued)

“9309” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	35%	50%	50%	50%	46%
Graffiti Wipe	75%	60%	60%	60%	64%
Graffiti Release	30%	60%	60%	60%	53%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	80%	80%	80%	84%
Graffiti Wipe	90%	95%	90%	95%	93%
Graffiti Release	70%	75%	75%	75%	74%
“9310” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	40%	40%	40%	48%
Graffiti Wipe	80%	50%	50%	50%	58%
Graffiti Release	25%	50%	50%	50%	44%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	80%	80%	80%	84%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	70%	90%	90%	90%	85%
“9311” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	50%	50%	50%	48%
Graffiti Wipe	80%	50%	50%	50%	58%
Graffiti Release	30%	50%	50%	50%	45%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	90%	90%	88%
Graffiti Wipe	80%	95%	95%	95%	91%
Graffiti Release	85%	75%	75%	75%	78%
“9312” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	30%	30%	30%	30%	30%
Graffiti Wipe	75%	50%	50%	50%	56%
Graffiti Release	70%	30%	30%	30%	40%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	75%	75%	75%	75%
Graffiti Wipe	85%	85%	85%	85%	85%
Graffiti Release	70%	70%	70%	70%	70%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 85

## TEST RESULTS – Graffiti Control (Continued)

“510” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	60%	60%	60%	55%
Graffiti Wipe	80%	60%	60%	60%	65%
Graffiti Release	50%	50%	50%	50%	50%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	90%	90%	90%
Graffiti Wipe	90%	90%	90%	90%	90%
Graffiti Release	85%	80%	80%	80%	81%
“520” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	65%	65%	65%	66%
Graffiti Wipe	80%	70%	70%	70%	73%
Graffiti Release	40%	50%	50%	50%	48%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	90%	90%	90%	86%
Graffiti Wipe	80%	95%	95%	95%	91%
Graffiti Release	40%	70%	70%	70%	63%
“530” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	80%	80%	80%	78%
Graffiti Wipe	90%	90%	90%	90%	90%
Graffiti Release	50%	65%	65%	65%	61%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	90%	90%	90%	85%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	50%	85%	85%	85%	76%
“540” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	50%	50%	50%	55%
Graffiti Wipe	80%	60%	60%	60%	65%
Graffiti Release	30%	50%	50%	50%	45%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	90%	90%	90%	89%
Graffiti Wipe	95%	95%	95%	95%	95%
Graffiti Release	70%	90%	90%	90%	80%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 86

## TEST RESULTS – Graffiti Control (Continued)

“560” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	80%	80%	80%	80%	80%
Graffiti Release	60%	70%	70%	70%	68%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	90%	90%	90%	89%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	40%	75%	75%	75%	66%
“570” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	50%	50%	50%	56%
Graffiti Wipe	85%	55%	55%	55%	63%
Graffiti Release	60%	50%	50%	50%	53%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	80%
Graffiti Wipe	90%	95%	95%	95%	94%
Graffiti Release	70%	80%	85%	80%	79%
“580” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	85%	85%	84%
Graffiti Wipe	95%	85%	85%	85%	88%
Graffiti Release	30%	65%	65%	65%	56%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	100%	100%	95%	95%
Graffiti Wipe	95%	100%	100%	100%	99%
Graffiti Release	80%	90%	90%	90%	88%
“590” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	90%	90%	90%	83%
Graffiti Wipe	90%	90%	90%	90%	90%
Graffiti Release	40%	75%	75%	75%	64%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	95%	95%	95%	84%
Graffiti Wipe	95%	95%	95%	90%	94%
Graffiti Release	40%	90%	90%	90%	78%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 87

## TEST RESULTS – Graffiti Control (Continued)

“5100” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	60%	60%	60%	55%
Graffiti Wipe	80%	60%	60%	60%	70%
Graffiti Release	25%	50%	50%	50%	44%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	75%	75%	75%	75%
Graffiti Wipe	85%	90%	90%	90%	89%
Graffiti Release	30%	60%	60%	60%	53%
“5110” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	60%	50%	50%	50%	53%
Graffiti Wipe	70%	60%	60%	60%	63%
Graffiti Release	65%	50%	50%	50%	54%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	65%	90%	90%	85%	83%
Graffiti Wipe	75%	90%	90%	90%	86%
Graffiti Release	85%	80%	80%	80%	81%
“5120” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	40%	50%	50%	50%	43%
Graffiti Wipe	70%	50%	50%	50%	55%
Graffiti Release	50%	50%	50%	50%	50%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	50%	80%	80%	80%	73%
Graffiti Wipe	80%	85%	90%	85%	85%
Graffiti Release	60%	60%	60%	60%	60%
“5200” ground-face					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	65%	50%	50%	50%	54%
Graffiti Wipe	80%	50%	50%	50%	58%
Graffiti Release	55%	40%	40%	40%	44%
Blok-Guard® & Graffiti Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	75%	90%	90%	90%	86%
Graffiti Wipe	80%	95%	95%	95%	91%
Graffiti Release	65%	75%	75%	75%	73%



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 88

## PHOTOGRAPHS – Graffiti Control


“LT-18” rough-face, Graffiti Applied



“LT-18” rough-face, Graffiti Removed

Sure Klean<sup>®</sup> Weather  
Seal Blok-Guard<sup>®</sup> &  
Graffiti Control

Untreated Control

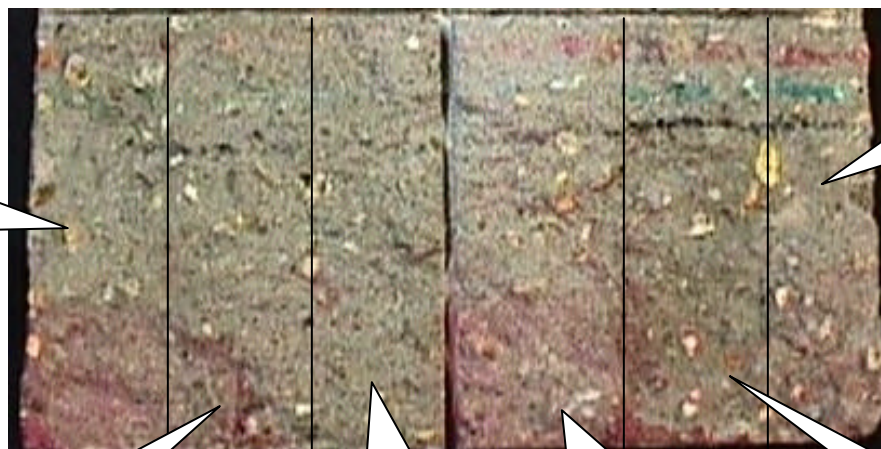

Sure Klean<sup>®</sup>  
Fast Acting  
Stripper

Defacer  
Eraser<sup>®</sup>  
Graffiti Wipe

Defacer Eraser<sup>®</sup>  
Graffiti Release

Defacer  
Eraser<sup>®</sup>  
Graffiti Wipe


Sure Klean<sup>®</sup>  
Fast Acting  
Stripper

Defacer Eraser<sup>®</sup>  
Graffiti Release





# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 89

---

## PHOTOGRAPHS – Graffiti Control Continued

---

“2507” ground-face coated, Graffiti Applied

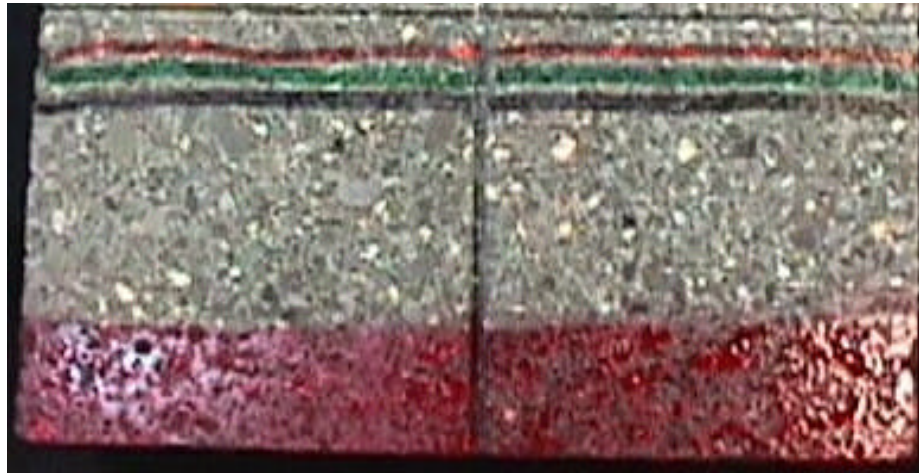

“2507” ground-face coated, Graffiti Removed

Sure Klean<sup>®</sup> Weather  
Seal Blok-Guard<sup>®</sup> &  
Graffiti Control

Untreated Control

Sure Klean<sup>®</sup>  
Fast Acting  
Stripper

Defacer Eraser<sup>®</sup>  
Graffiti Release

Defacer  
Eraser<sup>®</sup>  
Graffiti Wipe


Defacer Eraser<sup>®</sup>  
Graffiti Release

Sure Klean<sup>®</sup>  
Fast Acting  
Stripper

Defacer  
Eraser<sup>®</sup>  
Graffiti Wipe



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 90

## PHOTOGRAPHS- Graffiti Control Continued

“540” ground-face, Graffiti Applied

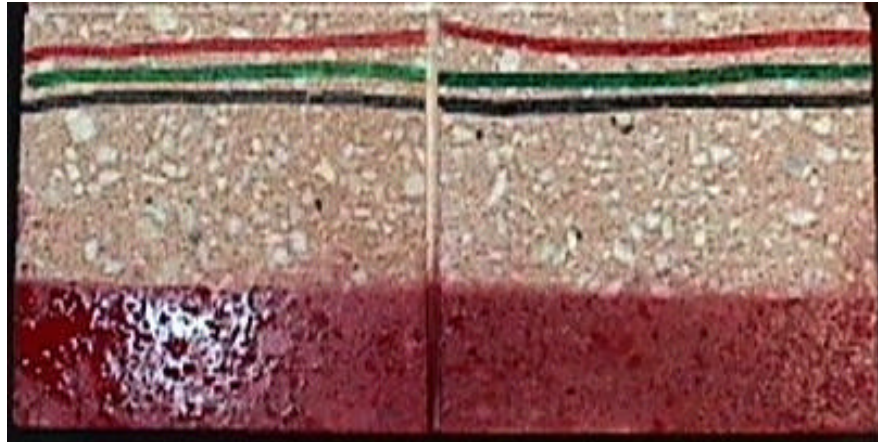

“540” ground-face, Graffiti Removed

Sure Klean<sup>®</sup> Weather  
Seal Blok-Guard<sup>®</sup> &  
Graffiti Control

Untreated Control

Defacer Eraser<sup>®</sup>  
Graffiti Release

Sure Klean<sup>®</sup>  
Fast Acting  
Stripper

Defacer Eraser<sup>®</sup>  
Graffiti Wipe


Sure Klean<sup>®</sup> Fast  
Acting Stripper

Defacer Eraser<sup>®</sup>  
Graffiti Release

Defacer Eraser<sup>®</sup>  
Graffiti Wipe



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 91**

---

## **CONCLUSIONS – Graffiti Control**

Based upon laboratory evaluations, graffiti removal was improved when the submitted samples were treated with Sure Klean<sup>®</sup> Blok-Guard<sup>®</sup> & Graffiti Control prior to graffiti application.

## **RECOMMENDATIONS – GRAFFITI CONTROL**


Recommendations for graffiti control treatment for each type of CMU submitted by A. Jandris & Sons, Inc., Gardner, MA are provided in the chart below. Recommendations are based on the treatment that proved most effective for providing graffiti repellency and the product that was most effective at removing the graffiti on all types submitted.

<b>Block Type</b>	<b>Graffiti Repellents</b>	<b>Graffiti Removers</b>
All Submitted CMU's	Sure Klean <sup>®</sup> Blok-Guard <sup>®</sup> & Graffiti Control	Defacer Eraser <sup>®</sup> Graffiti Wipe

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate graffiti control product and procedure for a particular project. See product literature for additional application and product information.



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 92**

---

## **SECTION D – STAIN RESISTANCE**

### **DESCRIPTION OF PRODUCTS EVALUATED**

These trials were conducted to determine the effectiveness of treatments in preventing food, oil, and miscellaneous staining on the submitted samples.

#### **Products Evaluated for Stain Protection:**

**Stand Off® Stone, Tile & Masonry Protector** – A penetrating oil and stain repellent. Easy-to-use. Low-VOC, low-odor protective treatment improves the stain resistance and simplifies maintenance cleaning of interior and exterior stone, quarry tile, concrete and masonry surfaces.

#### **Kitchen Products Evaluated:**

Coca Cola  
Ketchup  
Mustard  
Red wine  
Balsamic Vinegar  
Soy Sauce  
Olive oil  
Wesson Oil  
Coffee

#### **Temperature:**

ambient (~70°F)  
ambient (~70°F)  
ambient (~70°F)  
ambient (~70°F)  
ambient (~70°F)  
ambient (~70°F)  
ambient (~70°F)  
250°F  
120°F


---

### **SAMPLE PREPARATION – Stain Resistance**

Samples were cleaned with Enviro Klean® 2010 All Surface Cleaner diluted with 10 parts water, allowed to dry and absorb atmospheric moisture for 24 hours prior to treatment. The method of application for protective treatments consisted of a wet-on-wet saturating brush application. Samples were allowed to cure for at least 2 weeks prior to testing.



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 93

---

## TEST METHOD – Stain Resistance

### Surface Beading Evaluation

The food and oil products were applied to the test areas by using a dropper creating a bead 0.5 – 1.0 cm in diameter. The beading properties of the oils and liquids were visually evaluated within two minutes after application. The results are reported as a rating based on the angle of contact between the base of the droplet and the substrate. A rating of “1 or 2” indicated the smallest angle of contact ( $<90^\circ$ ) which correlates to “above average” repellency. A rating of “3 or 4” indicates “average” repellency. A rating of “5 or greater” indicated that the oil quickly absorbed into the substrate and correlates to “below average” repellency.

**Note: Non-free flowing staining agents such as ketchup and mustard are applied in a blob and not evaluated for their beading properties.**

#### Rating System (1-5)

1. No wetting of contact area (no darkening); angle less than  $90^\circ$



2. Wetting contained to the contact area (slight darkening); angle is less than  $90^\circ$



3. Wetting contained to the contact area (slight darkening); angle is greater than  $90^\circ$ , but less than  $135^\circ$ .



4. Wetting beyond the contact area (darkening); angle is greater than  $135^\circ$




5. Wetting beyond the contact area (darkening); angle is flat.





# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 94

## TEST METHODS: Continued

### Stain Resistance


The soiling agents were allowed to dwell on the treated and untreated substrate for times of 24 hours, 4 hours, 1 hour, and 10 minutes. The test areas were then cleaned with Enviro Klean® 2010 All Surface Cleaner diluted 1 part concentrate to 10 parts fresh water and scrubbed under a stream of running water from a faucet. Samples were allowed to dry for 24 hours. Evaluation consisted of a visual examination of the tested areas to determine the percentage of staining removal.

## TEST RESULTS – Surface Beading

“LT-N” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	3	4	3	4
STMP	4	-	-	3	3	3	2	2	4
“LT-1” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	2
STMP	4	-	-	3	3	2	2	3	3
“LT-3” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	2	3	4	4	3
STMP	4	-	-	3	3	3	2	2	3
“LT-13” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	2
STMP	4	-	-	3	2	2	2	2	3



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 95**

**TEST RESULTS – Surface Beading continued**

“LT-14” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	3
STMP	2	-	-	2	2	2	2	2	3
“LT-17” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	3	3	2	4	4	3
STMP	2	-	-	2	2	2	2	3	3
“LT-18” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	3	2	3	4	4	3
STMP	3	-	-	2	2	2	3	2	3
“DK-6” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	4	4	3	3
STMP	3	-	-	2	2	2	2	2	3
“DK-9” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	2	4	3	4
STMP	3	-	-	3	2	3	4	4	2
“DK-12” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	4
STMP	4	-	-	3	3	2	4	4	3



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 96


## TEST RESULTS – Surface Beading continued

“DK-16” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	3	4	3	3
STMP	4	-	-	3	3	2	2	2	3
“DK-19” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	3	4	3	3
STMP	4	-	-	2	2	2	2	2	3
“DK-21” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	3
STMP	2	-	-	3	3	2	2	2	2
“DK-22” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	4	4	4	3
STMP	4	-	-	3	2	2	2	2	3
“9312” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	3
STMP	4	-	-	3	3	2	2	2	3
“5110” rough-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	4
STMP	4	-	-	2	2	2	2	2	3





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**


**Page 97**

**TEST RESULTS – Surface Beading continued**

“2501” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	4
STMP	4	-	-	3	3	3	2	2	4
“2502” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	3
STMP	4	-	-	2	2	2	2	2	3
“2503” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	3	4	4	3
STMP	4	-	-	3	3	2	2	2	3
“2504” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	2	2	4	4	3
STMP	4	-	-	3	2	2	2	2	3
“2505” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	4
STMP	4	-	-	3	3	2	4	4	3
“2506” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	4
STMP	4	-	-	3	3	3	2	2	4



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 98

## TEST RESULTS – Surface Beading continued

“2507” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	2
STMP	4	-	-	3	3	2	2	2	3
“2508” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	3	3	4	4	4
STMP	4	-	-	3	3	3	2	2	4
“2509” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	2	2	4	4	4
STMP	4	-	-	3	3	2	2	2	3
“2510” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	3	4	4	4
STMP	4	-	-	3	3	3	2	2	4
“2511” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	3
STMP	4	-	-	3	3	3	2	2	3
“2512” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	3	2	4	4	3
STMP	4	-	-	3	3	3	2	2	3



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 99

## TEST RESULTS – Surface Beading continued

“9301” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	3	4	4	3
STMP	3	-	-	2	2	2	2	2	3
“9302” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	2	2	4	4	2
STMP	4	-	-	3	3	2	2	2	4
“9303” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	4
STMP	4	-	-	2	2	2	2	2	3
“9304” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	3
STMP	4	-	-	3	3	2	2	2	3
“9305” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	3
STMP	4	-	-	4	2	2	2	2	3
“9306” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	4
STMP	4	-	-	3	2	2	2	2	3



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 100

## TEST RESULTS – Surface Beading continued

“9307” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	4
STMP	4	-	-	2	2	2	2	2	3
“9308” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	4	2	4	4	4	4
STMP	4	-	-	2	3	2	2	2	3
“9309” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	2	4	4	3
STMP	4	-	-	3	3	2	2	2	4
“9310” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	2	4	4	3
STMP	4	-	-	4	3	2	2	2	4
“9311” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	4
STMP	4	-	-	3	3	3	4	4	4
“9312” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	2	4	4	4
STMP	3	-	-	3	3	4	2	2	4



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 101

## TEST RESULTS – Surface Beading continued

“510” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	3
STMP	2	-	-	3	3	2	2	2	2
“520” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	2
STMP	2	-	-	2	2	2	2	2	3
“530” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	2	2	4	4	3
STMP	4	-	-	3	3	2	2	2	2
“540” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	2	2	2	4	4	2
STMP	4	-	-	4	3	2	2	2	4
“560” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	3
STMP	2	-	-	3	3	3	2	2	3
“570” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	3	2	2	3
STMP	2	-	-	3	3	3	4	4	3



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 102

## TEST RESULTS – Surface Beading continued

“580” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	2	2	4	4	3
STMP	4	-	-	3	3	3	2	2	4
“590” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	2
STMP	4	-	-	3	3	3	2	2	4
“5100” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	3
STMP	4	-	-	3	3	3	2	2	4
“5110” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	2
STMP	4	-	-	2	2	2	2	2	3
“5120” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	2
STMP	4	-	-	4	4	4	2	2	3
“5200” ground-face, coated									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	4	4	3
STMP	3	-	-	2	2	2	2	2	3



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 103

## TEST RESULTS – Surface Beading continued

“2501” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	4	4	5	5	5
STMP	2	-	-	2	2	2	2	2	2
“2502” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	5	-	-	5	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“2503” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	2	4	4	4	3	4
STMP	2	-	-	2	2	2	2	2	2
“2504” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	5	-	-	5	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“2505” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	4	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“2506” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	5	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 104

## TEST RESULTS – Surface Beading continued


“2507” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	5	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“2508” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	4	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“2509” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	4	4	4	4	4	4
STMP	2	-	-	3	2	2	2	2	2
“2510” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	4	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“2511” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	4	4	4	4	4	4
STMP	2	-	-	2	3	2	2	2	2
“2512” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	4	4	4	4	4
STMP	2	-	-	3	2	2	2	2	2

## TEST RESULTS – Surface Beading continued





# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 105

“9301” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	2	2	3	2	4	2
STMP	2	-	-	2	2	2	2	2	2
“9302” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	4	3	3	4	4	3
STMP	2	-	-	2	2	2	2	2	2
“9303” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	3	4	3	4	4	2
STMP	2	-	-	2	2	2	2	2	2
“9304” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	4	3	4	4	3
STMP	2	-	-	2	2	2	2	2	2
“9305” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	5	-	-	4	4	4	4	4	3
STMP	2	-	-	2	2	2	2	2	2
“9306” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	2	2	4	4	4
STMP	2	-	-	2	2	2	2	2	2



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 106

## TEST RESULTS – Surface Beading continued

“9307” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	4	-	-	4	2	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“9308” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“9309” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	3
STMP	2	-	-	2	2	2	2	2	2
“9310” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	4	3	3	4	4	3
STMP	2	-	-	2	2	2	2	2	2
“9311” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	4	3	3	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“9312” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	4	3	4	4	3
STMP	2	-	-	2	2	2	2	2	2



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 107

## TEST RESULTS – Surface Beading continued

“510” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“520” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“530” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	3	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“540” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	2	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“560” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“570” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	4	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 108

## TEST RESULTS – Surface Beading continued

“580” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	3	3	3	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“590” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	3	-	-	3	3	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“5100” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	3	3	4	4	4
STMP	2	-	-	2	2	2	2	2	2
“5110” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	2	2	2	2	2	2
STMP	2	-	-	4	3	4	5	5	4
“5120” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	3	4	4	4	3
STMP	2	-	-	2	2	2	2	2	2
“5200” ground-face									
	Coco-Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
Untreated Control	2	-	-	3	4	4	4	4	4
STMP	2	-	-	2	2	2	2	2	2



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 109**

## TEST RESULTS – Stain Resistance: Kitchen Stains

Cleaned with: Enviro Klean® 2010 All Surface Cleaner (1:10)

% Removal

### “LT-N” rough-face


Untreated Control									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	100%	80%	75%	90%	80%	70%	<1%	<1%	70%
4 hour	100%	100%	95%	85%	85%	85%	<1%	<1%	80%
1 hour	100%	100%	100%	90%	90%	90%	<1%	<1%	90%
10 min.	100%	100%	100%	90%	95%	90%	<1%	<1%	100%
Stand Off™ Stone, Tile, & Masonry Protector									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	100%	95%	95%	100%	100%	100%	100%	100%	100%
4 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
1 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
10 min.	100%	100%	100%	100%	100%	100%	100%	100%	100%

### “LT-1” rough-face

Untreated Control									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	90%	90%	80%	85%	80%	85%	<1%	<1%	60%
4 hour	95%	90%	85%	95%	80%	85%	<1%	<1%	60%
1 hour	100%	95%	90%	95%	85%	90%	<1%	<1%	70%
10 min.	100%	100%	95%	100%	95%	90%	<1%	<1%	80%
Stand Off™ Stone, Tile, & Masonry Protector									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	100%	95%	90%	100%	100%	100%	100%	100%	100%
4 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
1 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
10 min.	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 110**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“LT-3” rough-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	100%	90%	90%	80%	80%	<1%	<1%	45%
<b>4 hour</b>	95%	100%	90%	90%	95%	85%	<1%	<1%	60%
<b>1 hour</b>	100%	95%	95%	90%	95%	85%	<1%	<1%	70%
<b>10 min.</b>	100%	95%	100%	95%	100%	90%	<1%	<1%	70%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“LT-13” rough-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	70%	65%	80%	80%	70%	<1%	<1%	55%
<b>4 hour</b>	100%	75%	80%	85%	95%	70%	<1%	<1%	70%
<b>1 hour</b>	100%	90%	90%	90%	90%	80%	<1%	<1%	70%
<b>10 min.</b>	100%	100%	100%	100%	95%	90%	<1%	<1%	70%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	90%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 111

## TEST RESULTS – Stain Resistance: Kitchen Stains

% Removal

### “LT-14” rough-face


Untreated Control									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	90%	85%	80%	80%	80%	80%	<1%	<1%	65%
4 hour	100%	95%	80%	85%	80%	85%	<1%	<1%	65%
1 hour	100%	100%	90%	85%	80%	85%	<1%	<1%	70%
10 min.	100%	100%	95%	90%	85%	90%	<1%	<1%	70%
Stand Off™ Stone, Tile, & Masonry Protector									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	100%	95%	95%	100%	100%	100%	100%	100%	100%
4 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
1 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
10 min.	100%	100%	100%	100%	100%	100%	100%	100%	100%

### “LT-17” rough-face

Untreated Control									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	90%	90%	100%	60%	100%	100%	<1%	<1%	70%
4 hour	100%	100%	100%	70%	100%	100%	<1%	<1%	70%
1 hour	100%	100%	100%	70%	100%	100%	<1%	<1%	70%
10 min.	100%	100%	100%	95%	100%	100%	<1%	<1%	90%
Stand Off™ Stone, Tile, & Masonry Protector									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	100%	90%	100%	100%	100%	100%	100%	100%	100%
4 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
1 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
10 min.	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 112**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“LT-18” rough-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	80%	75%	100%	75%	100%	100%	<1%	<1%	95%
<b>4 hour</b>	80%	100%	100%	75%	100%	100%	<1%	<1%	95%
<b>1 hour</b>	95%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>10 min.</b>	95%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%


**“DK-6” rough-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	80%	75%	70%	70%	60%	20%	20%	40%
<b>4 hour</b>	100%	80%	80%	70%	80%	80%	20%	20%	50%
<b>1 hour</b>	100%	90%	80%	80%	85%	80%	30%	30%	60%
<b>10 min.</b>	100%	90%	90%	80%	90%	80%	30%	30%	60%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 113**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“DK-9” rough-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	80%	85%	85%	85%	80%	<1%	<1%	60%
<b>4 hour</b>	100%	100%	95%	85%	90%	80%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	90%	90%	90%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	95%	90%	90%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	90%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“DK-12” rough-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	85%	95%	75%	80%	<1%	<1%	85%
<b>4 hour</b>	100%	100%	95%	100%	80%	80%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	80%	80%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	100%	90%	90%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 114**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“DK-16” rough-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	80%	80%	80%	70%	75%	<1%	<1%	70%
<b>4 hour</b>	100%	95%	95%	95%	80%	85%	<1%	<1%	70%
<b>1 hour</b>	100%	100%	100%	100%	80%	90%	<1%	<1%	85%
<b>10 min.</b>	100%	100%	100%	100%	85%	90%	<1%	<1%	85%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“DK-19” rough-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	85%	75%	70%	80%	70%	<1%	<1%	60%
<b>4 hour</b>	100%	95%	80%	75%	85%	70%	<1%	<1%	70%
<b>1 hour</b>	100%	100%	90%	75%	85%	70%	<1%	<1%	70%
<b>10 min.</b>	100%	100%	95%	80%	85%	80%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	95%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 115**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“DK-21” rough-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	85%	70%	70%	80%	80%	70%	<1%	<1%	60%
<b>4 hour</b>	90%	70%	75%	85%	80%	70%	<1%	<1%	60%
<b>1 hour</b>	100%	85%	85%	90%	90%	75%	<1%	<1%	70%
<b>10 min.</b>	100%	90%	90%	95%	90%	80%	<1%	<1%	85%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“DK-22” rough-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	85%	70%	70%	80%	80%	70%	<1%	<1%	50%
<b>4 hour</b>	90%	70%	75%	85%	85%	75%	<1%	<1%	60%
<b>1 hour</b>	100%	85%	85%	90%	85%	75%	<1%	<1%	60%
<b>10 min.</b>	100%	90%	90%	95%	90%	90%	<1%	<1%	65%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 116

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9312”, rough-face**


Untreated Control									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	90%	80%	80%	70%	70%	70%	<1%	<1%	70%
4 hour	100%	90%	80%	75%	70%	75%	<1%	<1%	80%
1 hour	100%	100%	90%	80%	70%	75%	<1%	<1%	80%
10 min.	100%	100%	95%	95%	70%	75%	<1%	<1%	95%
Stand Off <sup>®</sup> Stone, Tile, & Masonry Protector									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	100%	100%	95%	95%	95%	100%	100%	100%	100%
4 hour	100%	100%	100%	95%	95%	100%	100%	100%	100%
1 hour	100%	100%	100%	100%	100%	100%	100%	100%	100%
10 min.	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“5110”, rough-face**

Untreated Control									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	100%	85%	75%	80%	65%	70%	<1%	<1%	75%
4 hour	100%	100%	80%	85%	70%	75%	<1%	<1%	80%
1 hour	100%	100%	95%	90%	70%	80%	<1%	<1%	80%
10 min.	100%	100%	95%	85%	70%	80%	<1%	<1%	85%
Stand Off <sup>®</sup> Stone, Tile, & Masonry Protector									
	Coca Cola	Ketchup	Mustard	Red Wine	Balsamic Vinegar	Soy Sauce	Olive Oil	Wesson Oil	Hot Coffee
24 hr	100%	95%	95%	90%	90%	100%	100%	100%	100%
4 hour	100%	100%	95%	100%	95%	100%	100%	100%	100%
1 hour	100%	100%	100%	100%	95%	100%	100%	100%	100%
10 min.	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 117**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2501” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	90%	90%	100%	<1%	<1%	60%
<b>4 hour</b>	100%	100%	100%	90%	100%	100%	<1%	<1%	60%
<b>1 hour</b>	100%	100%	100%	95%	100%	100%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	95%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2502” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	80%	85%	90%	90%	70%	70%	40%
<b>4 hour</b>	100%	100%	100%	90%	90%	90%	70%	70%	40%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	70%	70%	40%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	100%	100%	100%	90%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 118**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2503” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	95%	95%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	50%	50%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	50%	50%	100%
<b>Stand Off<sup>™</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	50%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2504” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	85%	100%	100%	50%	50%	90%
<b>4 hour</b>	100%	100%	95%	90%	100%	100%	50%	50%	90%
<b>1 hour</b>	100%	100%	95%	100%	100%	100%	50%	50%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	50%	50%	100%
<b>Stand Off<sup>™</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	95%	100%	95%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 119**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2505” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	95%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2506” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	85%	100%	100%	95%	<1%	<1%	100%
<b>4 hour</b>	100%	95%	95%	100%	100%	100%	<1%	<1%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	100%	100%	100%	100%	50%	100%
<b>4 hour</b>	100%	100%	95%	100%	100%	100%	100%	60%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 120**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2507” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	85%	100%	90%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>™</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	90%	100%	90%	100%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%


**“2508” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	60%	70%	70%	<1%	<1%	70%
<b>4 hour</b>	100%	100%	100%	70%	80%	80%	<1%	<1%	80%
<b>1 hour</b>	100%	100%	100%	80%	100%	100%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>™</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	90%	95%	100%	90%	90%	95%
<b>4 hour</b>	100%	100%	100%	95%	95%	100%	90%	90%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	90%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 121

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2509” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	90%	100%	100%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	90%	100%	100%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	90%	100%	100%	70%	70%	95%
<b>4 hour</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2510” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	90%	70%	40%	80%	<1%	<1%	70%
<b>4 hour</b>	100%	100%	95%	70%	60%	90%	<1%	<1%	80%
<b>1 hour</b>	100%	100%	100%	80%	90%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	100%	100%	60%	100%	80%
<b>4 hour</b>	100%	95%	100%	100%	100%	100%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 122**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2511” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	90%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2512” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	90%	90%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	95%	90%	90%	90%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	95%	95%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	95%	95%	90%	90%	100%	90%	95%
<b>4 hour</b>	100%	100%	95%	100%	100%	100%	100%	90%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	95%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	95%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 123

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9301” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	90%	70%	90%	30%	30%	90%
<b>4 hour</b>	100%	100%	100%	90%	80%	90%	40%	40%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	50%	50%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	95%	100%	100%	100%	100%	70%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	90%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9302” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	100%	100%	100%	<1%	<1%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	100%	100%	100%	70%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 124**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9303” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	90%	90%	95%	95%	<1%	<1%	100%
<b>4 hour</b>	100%	100%	95%	90%	95%	95%	<1%	<1%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9304” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	95%	95%	95%	50%	50%	90%
<b>4 hour</b>	100%	100%	90%	95%	100%	100%	50%	50%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	50%	50%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	50%	50%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	90%	95%	80%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	90%	95%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	90%	95%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 125**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9305” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9306” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	90%	100%	100%	100%	40%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	40%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	40%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	40%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	80%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 126

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9307” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	95%	95%	100%	<1%	<1%	75%
<b>4 hour</b>	100%	100%	100%	95%	100%	100%	<1%	<1%	75%
<b>1 hour</b>	100%	100%	100%	95%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	70%	70%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9308” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	95%	95%	60%	95%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	95%	95%	80%	100%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	95%	100%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	95%	90%	95%	80%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	90%	100%	80%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 127**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9309” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	40%	60%	60%	<1%	<1%	70%
<b>4 hour</b>	100%	100%	95%	50%	80%	70%	<1%	<1%	70%
<b>1 hour</b>	100%	100%	100%	80%	100%	80%	<1%	<1%	70%
<b>10 min.</b>	100%	100%	100%	100%	100%	90%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	70%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9310” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	95%	85%	70%	90%	85%	<1%	<1%	60%
<b>4 hour</b>	100%	100%	95%	75%	90%	90%	<1%	<1%	70%
<b>1 hour</b>	100%	100%	100%	100%	95%	95%	<1%	<1%	80%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	90%	90%	95%	100%	100%	95%
<b>4 hour</b>	100%	100%	100%	90%	90%	100%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	90%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 128**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9311” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	90%	40%	90%	<1%	<1%	40%
<b>4 hour</b>	100%	100%	90%	90%	40%	90%	<1%	<1%	40%
<b>1 hour</b>	100%	100%	95%	100%	40%	100%	<1%	<1%	60%
<b>10 min.</b>	100%	100%	100%	100%	70%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	95%	95%	95%	100%	100%	90%
<b>4 hour</b>	100%	95%	95%	95%	95%	95%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	95%	95%	95%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	95%	95%	100%	100%	100%


**“9312” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	100%	90%	40%	80%	60%	<1%	<1%	85%
<b>4 hour</b>	95%	100%	90%	50%	80%	70%	<1%	<1%	85%
<b>1 hour</b>	100%	100%	90%	70%	90%	100%	<1%	<1%	85%
<b>10 min.</b>	100%	100%	100%	95%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	85%	95%	95%	50%	90%	90%
<b>4 hour</b>	100%	100%	100%	85%	95%	100%	90%	100%	90%
<b>1 hour</b>	100%	100%	100%	90%	95%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	90%	100%	100%	100%	100%	100%





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 129**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“510” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	70%	70%	80%	<1%	<1%	70%
<b>4 hour</b>	100%	100%	100%	70%	70%	90%	<1%	<1%	70%
<b>1 hour</b>	100%	100%	100%	70%	70%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	95%	100%	100%	100%	100%	90%
<b>4 hour</b>	100%	100%	100%	95%	100%	100%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“520” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	95%	85%	85%	95%	50%	50%	85%
<b>4 hour</b>	100%	100%	100%	85%	85%	100%	50%	50%	85%
<b>1 hour</b>	100%	100%	100%	95%	100%	100%	50%	50%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	50%	50%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	95%	95%	95%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	95%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 130**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“530” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	95%	90%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	95%	95%	100%	100%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	95%	100%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	90%	90%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	90%	90%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	95%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	95%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“540” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	90%	70%	95%	100%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	90%	70%	95%	100%	<1%	<1%	100%
<b>1 hour</b>	100%	100%	100%	90%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	100%	100%	100%	100%	95%	90%
<b>4 hour</b>	100%	100%	90%	100%	100%	100%	100%	95%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 131**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“560” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	85%	90%	80%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	90%	90%	90%	100%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	100%	100%	100%	90%	90%	95%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	90%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	90%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	90%	100%

**“570” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	80%	85%	90%	<1%	<1%	70%
<b>4 hour</b>	100%	100%	100%	90%	90%	90%	<1%	<1%	80%
<b>1 hour</b>	100%	100%	100%	90%	95%	100%	90%	90%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 132**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“580” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	70%	100%	100%	<1%	<1%	100%
<b>4 hour</b>	100%	100%	95%	80%	100%	100%	<1%	<1%	100%
<b>1 hour</b>	100%	100%	100%	90%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	90%	100%	100%	100%	100%	60%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“590” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	95%	95%	90%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	95%	100%	100%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	100%	95%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 133**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“5100” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	90%	80%	85%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	90%	85%	90%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	95%	90%	100%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	90%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“5110” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	90%	90%	50%	50%	90%	<1%	<1%	40%
<b>4 hour</b>	90%	90%	90%	50%	50%	90%	<1%	<1%	40%
<b>1 hour</b>	95%	90%	90%	70%	70%	90%	<1%	<1%	40%
<b>10 min.</b>	100%	100%	90%	70%	70%	90%	<1%	<1%	40%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	70%	60%	100%	<1%	<1%	70%
<b>4 hour</b>	100%	100%	90%	70%	80%	100%	100%	100%	70%
<b>1 hour</b>	100%	100%	100%	70%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	70%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 134

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“5120” ground-face, coated**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	85%	70%	90%	100%	<1%	<1%	70%
<b>4 hour</b>	100%	100%	95%	75%	90%	100%	<1%	<1%	70%
<b>1 hour</b>	100%	100%	100%	100%	90%	100%	<1%	<1%	70%
<b>10 min.</b>	100%	100%	100%	100%	90%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	80%	80%	100%	100%	95%
<b>4 hour</b>	100%	95%	100%	100%	80%	80%	100%	100%	95%
<b>1 hour</b>	100%	95%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	95%	100%	100%	100%	100%	100%	100%	100%

**“5200” ground-face, coated**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	100%	70%	85%	70%	80%	<1%	<1%	50%
<b>4 hour</b>	95%	100%	90%	85%	70%	80%	<1%	<1%	50%
<b>1 hour</b>	100%	100%	95%	85%	70%	80%	<1%	<1%	50%
<b>10 min.</b>	100%	100%	100%	95%	70%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	100%	90%	90%	100%	100%	100%	100%	90%
<b>4 hour</b>	95%	100%	95%	90%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	95%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 135

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2501” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	95%	95%	95%	<1%	<1%	95%
<b>4 hour</b>	100%	100%	100%	95%	95%	95%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	95%	95%	95%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	95%	95%	95%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	100%	95%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2502” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	100%	80%	85%	100%	100%	<1%	<1%	95%
<b>4 hour</b>	95%	100%	95%	85%	100%	100%	<1%	<1%	95%
<b>1 hour</b>	95%	100%	95%	85%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	95%	85%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 136

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2503” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	100%	90%	100%	100%	<1%	<1%	95%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%


**“2504” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	95%	100%	95%	95%	<1%	<1%	95%
<b>4 hour</b>	100%	100%	100%	100%	100%	95%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	95%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	95%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	85%	90%	90%	100%	100%	95%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 137**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2505” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	100%	100%	90%	95%	90%	<1%	<1%	100%
<b>4 hour</b>	95%	100%	100%	100%	100%	90%	<1%	<1%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	90%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	90%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	90%	95%	100%	100%	95%
<b>4 hour</b>	100%	100%	100%	100%	90%	95%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2506” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	100%	90%	90%	100%	100%	<1%	<1%	95%
<b>4 hour</b>	95%	100%	100%	90%	100%	100%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 138**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2507” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	100%	100%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	100%	100%	100%	100%	100%	100%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2508” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	80%	80%	80%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	80%	80%	80%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	80%	80%	80%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	80%	100%	100%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	70%	100%	80%	100%	100%	80%
<b>4 hour</b>	100%	100%	100%	100%	100%	80%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 139**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2509” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	65%	100%	100%	50%	100%	70%	<1%	<1%	80%
<b>4 hour</b>	100%	100%	100%	100%	100%	75%	<1%	<1%	80%
<b>1 hour</b>	100%	100%	100%	100%	100%	85%	<1%	<1%	80%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	80%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	60%	70%	100%	100%	100%	80%
<b>4 hour</b>	100%	100%	100%	100%	70%	100%	100%	100%	80%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2510” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	70%	90%	70%	70%	70%	<1%	<1%	90%
<b>4 hour</b>	100%	90%	90%	70%	70%	70%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	70%	70%	70%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	70%	70%	70%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	70%	100%	75%	80%	95%	100%	100%	95%
<b>4 hour</b>	100%	95%	100%	75%	95%	100%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	75%	100%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 140**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“2511” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	100%	85%	60%	95%	85%	<1%	<1%	85%
<b>4 hour</b>	95%	100%	85%	70%	95%	85%	<1%	<1%	85%
<b>1 hour</b>	100%	100%	95%	70%	95%	95%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	95%	95%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	60%	95%	80%	100%	100%	90%
<b>4 hour</b>	100%	100%	100%	100%	100%	80%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	95%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“2512” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	90%	90%	70%	90%	90%	<1%	<1%	90%
<b>4 hour</b>	95%	90%	90%	100%	90%	90%	<1%	<1%	90%
<b>1 hour</b>	95%	90%	90%	100%	90%	90%	<1%	<1%	90%
<b>10 min.</b>	95%	90%	90%	100%	90%	90%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	90%	100%	90%	100%	100%	95%
<b>4 hour</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 141**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9301” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	90%	90%	70%	40%	60%	<1%	<1%	75%
<b>4 hour</b>	95%	100%	100%	75%	40%	60%	<1%	<1%	75%
<b>1 hour</b>	100%	100%	100%	80%	50%	60%	<1%	<1%	75%
<b>10 min.</b>	100%	100%	100%	90%	75%	60%	<1%	<1%	75%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	90%	90%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9302” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	90%	90%	85%	80%	80%	<1%	<1%	95%
<b>4 hour</b>	95%	100%	95%	85%	80%	80%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	85%	80%	80%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	85%	80%	80%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	95%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 142**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9303” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	100%	70%	100%	100%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	70%	100%	100%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	70%	100%	100%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	100%	95%	100%	100%	100%	100%	90%
<b>4 hour</b>	100%	100%	100%	95%	100%	100%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9304” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	95%	90%	85%	80%	60%	<1%	<1%	95%
<b>4 hour</b>	95%	95%	95%	85%	80%	60%	<1%	<1%	95%
<b>1 hour</b>	95%	100%	100%	85%	80%	60%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	95%	90%	90%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 143**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9305” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	95%	90%	85%	70%	75%	<1%	<1%	80%
<b>4 hour</b>	95%	95%	95%	95%	70%	75%	<1%	<1%	80%
<b>1 hour</b>	95%	100%	100%	95%	70%	75%	<1%	<1%	80%
<b>10 min.</b>	100%	100%	100%	100%	70%	75%	<1%	<1%	80%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	95%	100%	100%	95%	95%	95%	95%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	95%

**“9306” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	80%	80%	90%	95%	95%	95%	<1%	<1%	90%
<b>4 hour</b>	80%	90%	100%	95%	95%	95%	<1%	<1%	90%
<b>1 hour</b>	90%	100%	100%	95%	95%	95%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	95%	95%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	90%	100%	85%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	85%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	95%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 144

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9307” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	80%	60%	95%	85%	90%	100%	<1%	<1%	100%
<b>4 hour</b>	90%	90%	100%	95%	95%	100%	<1%	<1%	100%
<b>1 hour</b>	95%	100%	100%	95%	95%	100%	<1%	<1%	100%
<b>10 min.</b>	95%	100%	100%	95%	95%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%


**“9308” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	90%	90%	80%	70%	95%	<1%	<1%	80%
<b>4 hour</b>	95%	100%	100%	95%	75%	100%	<1%	<1%	80%
<b>1 hour</b>	100%	100%	100%	100%	80%	100%	<1%	<1%	80%
<b>10 min.</b>	100%	100%	100%	100%	85%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	90%	95%	100%	100%	100%	90%
<b>4 hour</b>	100%	100%	100%	90%	95%	100%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	95%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	95%	100%	100%	100%	100%	100%





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 145**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9309” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	95%	85%	80%	80%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	90%	80%	80%	90%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	90%	80%	100%	100%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	80%	90%	100%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9310” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	80%	100%	95%	80%	80%	80%	<1%	<1%	80%
<b>4 hour</b>	85%	100%	95%	80%	80%	80%	<1%	<1%	80%
<b>1 hour</b>	90%	100%	95%	80%	100%	80%	<1%	<1%	80%
<b>10 min.</b>	90%	100%	100%	80%	100%	80%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	75%	95%	95%	100%	100%	90%
<b>4 hour</b>	100%	100%	100%	75%	95%	95%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	80%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 146**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“9311” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	80%	95%	40%	65%	75%	90%	<1%	<1%	70%
<b>4 hour</b>	80%	100%	90%	65%	75%	90%	<1%	<1%	70%
<b>1 hour</b>	80%	100%	90%	65%	75%	90%	<1%	<1%	70%
<b>10 min.</b>	80%	100%	90%	65%	75%	90%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	95%	95%	90%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	90%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	90%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“9312” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	95%	90%	70%	90%	90%	<1%	<1%	80%
<b>4 hour</b>	90%	95%	90%	70%	90%	90%	<1%	<1%	80%
<b>1 hour</b>	100%	100%	90%	70%	90%	90%	<1%	<1%	80%
<b>10 min.</b>	100%	100%	100%	70%	95%	90%	<1%	<1%	80%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	100%	90%	80%	90%	100%	100%	100%	90%
<b>4 hour</b>	95%	100%	95%	80%	100%	100%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	90%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	90%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 147**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“510” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	70%	70%	70%	50%	50%	50%	<1%	<1%	50%
<b>4 hour</b>	80%	95%	85%	50%	50%	50%	<1%	<1%	50%
<b>1 hour</b>	90%	100%	90%	55%	50%	50%	<1%	<1%	50%
<b>10 min.</b>	100%	100%	95%	55%	50%	50%	<1%	<1%	50%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	85%	90%	100%	100%	100%	95%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	95%

**“520” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	85%	90%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	95%	85%	90%	90%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	85%	90%	90%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	90%	90%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	90%	100%	100%	100%	100%	90%
<b>4 hour</b>	100%	100%	95%	95%	100%	100%	100%	100%	90%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 148**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“530” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	90%	70%	70%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	100%	70%	70%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	100%	70%	70%	<1%	<1%	90%
<b>10 min.</b>	100%	100%	100%	100%	70%	70%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“540” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	95%	85%	60%	75%	90%	<1%	<1%	85%
<b>4 hour</b>	100%	100%	90%	60%	85%	90%	<1%	<1%	85%
<b>1 hour</b>	100%	100%	100%	60%	85%	90%	<1%	<1%	85%
<b>10 min.</b>	100%	100%	100%	100%	100%	90%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%
<b>4 hour</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	90%	100%	100%	100%	100%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 149**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“560” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	95%	90%	100%	100%	<1%	<1%	95%
<b>4 hour</b>	100%	100%	95%	90%	100%	100%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	95%	90%	100%	100%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	90%	100%	100%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	85%	100%	100%	<1%	100%	95%
<b>4 hour</b>	100%	100%	100%	85%	100%	100%	100%	100%	95%
<b>1 hour</b>	100%	100%	100%	85%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	95%	100%	100%	100%	100%	100%

**“570” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	85%	90%	90%	95%	60%	60%	<1%	<1%	80%
<b>4 hour</b>	95%	100%	95%	100%	60%	60%	<1%	<1%	80%
<b>1 hour</b>	100%	100%	95%	100%	60%	60%	<1%	<1%	80%
<b>10 min.</b>	100%	100%	100%	100%	60%	60%	<1%	<1%	80%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	95%	100%	100%	100%	100%	95%	95%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	95%	95%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	95%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	95%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 150**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“580” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	100%	100%	85%	85%	80%	<1%	<1%	95%
<b>4 hour</b>	100%	100%	100%	85%	90%	100%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	85%	100%	100%	<1%	<1%	100%
<b>10 min.</b>	100%	100%	100%	95%	100%	100%	<1%	<1%	100%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%

**“590” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	80%	90%	90%	70%	90%	<1%	<1%	95%
<b>4 hour</b>	100%	100%	100%	100%	70%	100%	<1%	<1%	95%
<b>1 hour</b>	100%	100%	100%	100%	70%	100%	<1%	<1%	95%
<b>10 min.</b>	100%	100%	100%	100%	70%	100%	<1%	<1%	95%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	100%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 151**

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“5100” ground-face**


<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	90%	90%	75%	50%	30%	20%	<1%	<1%	40%
<b>4 hour</b>	90%	100%	80%	50%	30%	20%	<1%	<1%	40%
<b>1 hour</b>	90%	100%	90%	50%	30%	20%	<1%	<1%	40%
<b>10 min.</b>	90%	100%	90%	50%	30%	20%	<1%	<1%	40%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	90%	85%	75%	95%	90%	90%	90%
<b>4 hour</b>	100%	100%	100%	85%	95%	100%	90%	90%	90%
<b>1 hour</b>	100%	100%	100%	85%	95%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	85%	95%	100%	100%	100%	100%

**“5110” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	100%	85%	75%	60%	60%	<1%	<1%	90%
<b>4 hour</b>	95%	100%	85%	75%	60%	60%	<1%	<1%	90%
<b>1 hour</b>	95%	100%	90%	75%	60%	60%	<1%	<1%	90%
<b>10 min.</b>	95%	100%	95%	75%	60%	60%	<1%	<1%	90%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	85%	80%	90%	<1%	<1%	90%
<b>4 hour</b>	100%	100%	100%	90%	80%	90%	<1%	<1%	90%
<b>1 hour</b>	100%	100%	100%	90%	80%	90%	100%	100%	90%
<b>10 min.</b>	100%	100%	100%	90%	80%	90%	100%	100%	90%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 152

**TEST RESULTS – Stain Resistance: Kitchen Stains**

% Removal

**“5120” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	95%	85%	85%	70%	85%	90%	<1%	<1%	70%
<b>4 hour</b>	95%	95%	90%	70%	90%	90%	<1%	<1%	70%
<b>1 hour</b>	100%	100%	95%	70%	90%	90%	<1%	<1%	70%
<b>10 min.</b>	100%	100%	100%	85%	90%	90%	<1%	<1%	85%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	90%	90%	70%	100%	100%	100%	100%	100%
<b>4 hour</b>	100%	100%	100%	70%	100%	100%	100%	100%	100%
<b>1 hour</b>	100%	100%	100%	75%	100%	100%	100%	100%	100%
<b>10 min.</b>	100%	100%	100%	90%	100%	100%	100%	100%	100%


**“5200” ground-face**

<b>Untreated Control</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	50%	95%	50%	20%	50%	75%	<1%	<1%	60%
<b>4 hour</b>	50%	100%	60%	20%	50%	75%	<1%	<1%	60%
<b>1 hour</b>	50%	100%	70%	20%	70%	100%	<1%	<1%	60%
<b>10 min.</b>	75%	100%	90%	50%	75%	100%	<1%	<1%	60%
<b>Stand Off<sup>®</sup> Stone, Tile, &amp; Masonry Protector</b>									
	<b>Coca Cola</b>	<b>Ketchup</b>	<b>Mustard</b>	<b>Red Wine</b>	<b>Balsamic Vinegar</b>	<b>Soy Sauce</b>	<b>Olive Oil</b>	<b>Wesson Oil</b>	<b>Hot Coffee</b>
<b>24 hr</b>	100%	95%	95%	95%	90%	90%	100%	100%	85%
<b>4 hour</b>	100%	100%	95%	100%	90%	90%	100%	100%	95%
<b>1 hour</b>	100%	100%	95%	100%	90%	100%	100%	100%	95%
<b>10 min.</b>	100%	100%	100%	100%	100%	100%	100%	100%	100%





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 153**

---

## PHOTOGRAPHS- Stain Removal

**“DK-9” rough-face, Stains Applied**




**“DK-9” rough-face, Stains Removed**





# PALLET TAG PROGRAM LABORATORY REPORT




**PROSOCO, Inc.**

**Page 154**

---

## PHOTOGRAPHS- Stain Removal Continued

**“510” ground-faced coated, Stains Applied**

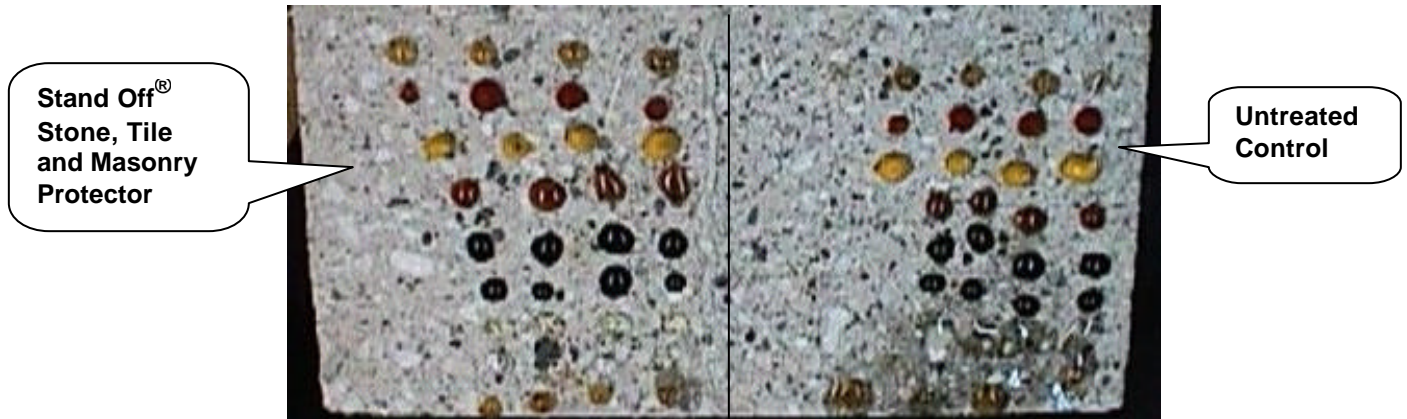


**“510” ground-faced coated, Stains Removed**





# PALLET TAG PROGRAM LABORATORY REPORT




**PROSOCO, Inc.**

**Page 155**

## PHOTOGRAPHS- Stain Removal

**“9308” ground-faced, Stains Applied**

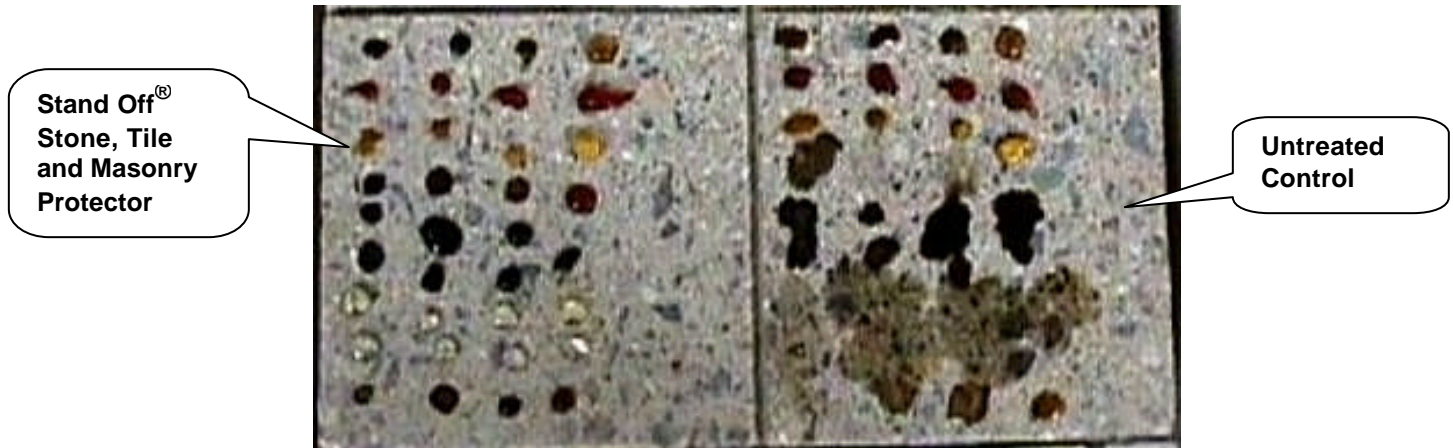


**“9308” ground-faced, Stains Removed**







# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 156**

---

## CONCLUSIONS – Stain Resistance

Based upon laboratory evaluations, Stand Off<sup>®</sup> Stone, Tile, and Masonry Protector was an effective treatment in repelling the staining agents from the submitted CMU's.

---

## RECOMMENDATIONS – STAIN RESISTANCE


Recommendations for stain resistance treatment for each type of CMU submitted by A. Jandris & Sons, Inc., Gardner, MA are provided in the charts below. Recommendations are based on the treatments that proved most effective for providing stain repellency on all types submitted.

Sample	Stain Repellent	Maintenance Cleaner
All Submitted CMUs	Stand Off <sup>®</sup> Stone, Tile and Masonry Protector	Enviro Klean <sup>®</sup> 2010 All Surface Cleaner (1:10)

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate product and procedure for a particular project. See product literature for application and product information.

Nathan R. Colaner  
Technical Analyst

NRC/



---

***Laboratory Report***

**Pallet Tag Program Evaluation**

**A. Jandris & Sons, Inc.  
Gardner, MA**

***Project No. 0302-06 PTP***

***Prepared For:***

**Rodney Moore  
A. Jandris & Sons, Inc.  
Gardner, MA**

***Prepared By:***



***PROSOCO, Inc.  
April 2003***