



PALLET TAG PROGRAM LABORATORY REPORT




TABLE OF CONTENTS

SAMPLES SUBMITTED2

PURPOSE OF TEST3

PRODUCTS EVALUATED.....4-5

SECTION A – NEW CONSTRUCTION CLEANING

DESCRIPTION OF PRODUCTS EVALUATED6

TEST METHOD6

TEST RESULTS7-12

PHOTOGRAPHS13-15

CONCLUSIONS.....16

RECOMMENDATIONS.....16

SECTION B – LIMITING SURFACE ALTERATIONS

DESCRIPTION OF PRODUCTS EVALUATED17

TEST METHOD17

TEST RESULTS18-20

CONCLUSIONS.....21

RECOMMENDATIONS.....21

SECTION C - PROTECTIVE WATER REPELLENTS

DESCRIPTION OF PRODUCTS EVALUATED22

TEST METHODS23

TEST RESULTS24-26

PHOTOGRAPHS27

CONCLUSIONS.....28

RECOMMENDATIONS.....28

SECTION E – STAIN REPELLENCY

DESCRIPTION OF PRODUCTS EVALUATED29

TEST METHOD30

TEST RESULTS31-47

PHOTOGRAPHS48

CONCLUSIONS.....49

RECOMMENDATIONS.....49

SECTION F- COLOR ENHANCEMENT

DESCRIPTION OF PRODUCTS EVALUATED50

TEST METHODS50

TEST RESULTS51

PHOTOGRAPHS52


RECOMMENDATIONS.....53

ATTACHMENTS

- Technical Services TECH Note RILEM Test Method No. II.4
- Product Data literature for all products evaluated



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 2

FOR: Boral Bricks, Inc. (Pavers)
cc: Rob Poitevent
Mike Burdette
Paul Tessier
Steve Dean

SUBJECT: Boral Bricks, Inc.
Augusta, GA

DATE:

PROJECT: 0407-08 PTP


SAMPLES SUBMITTED: Fourteen types of clay pavers.

| <u>Sample</u> | <u>Number</u> | <u>Color</u> | <u>Size</u> |
|--------------------------|---------------|--------------|--------------|
| "Bourbon Street" | 12 | Red Orange | 8" x 4" x 3" |
| "Burgundy Straight-Edge" | 12 | Dark Red | 8" x 4" x 3" |
| "Dark Gray" | 12 | Dark Gray | 8" x 4" x 3" |
| "Dark Pink" | 12 | Dark Pink | 8" x 4" x 3" |
| "Heartland Flash" | 12 | Red | 8" x 4" x 3" |
| "Key West" | 12 | Tan | 8" x 4" x 3" |
| "Medium Brown" | 12 | Brown | 8" x 4" x 3" |
| "Parquet Tan" | 12 | Yellow Tan | 8" x 4" x 3" |
| "Peachtree Avenue" | 12 | Pink | 8" x 4" x 3" |
| "Pink" | 12 | Pink | 8" x 4" x 3" |
| "Red Straight-Edge" | 12 | Red | 8" x 4" x 3" |
| "Santee Gray" | 12 | Dark Gray | 8" x 4" x 3" |
| "Savannah Brown" | 12 | Dark Brown | 8" x 4" x 3" |
| "Tan" | 12 | Tan | 8" x 4" x 3" |

Submitted by: Rob Poitevent



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 3

PURPOSE OF TESTING:

Fourteen types of clay pavers were submitted to PROSOCO, Inc.'s Testing Laboratory with a request to determine if application of the products evaluated will produce any surface alteration during new construction cleaning operations. Additionally, the effectiveness of water repellents, stain repellents, and color enhancing treatments suitable for clay pavers were evaluated.

A. New Construction Cleaning – Enviro Klean[®] Safety Klean and either Sure Klean[®] 600 Detergent or Sure Klean[®] Vana Trol[®] were evaluated for removal of laboratory applied mortar or grout.

To simulate new construction soiling, all samples were placed on a bench with finished surface facing upward. Hollow cylinders measuring 50 mm in diameter and 75 mm tall were positioned on top of each paver and filled with a wet mixture of Ash Grove[®] Type S cementitious mortar or sanded grout. The wet mortar- or grout-filled cylinder was allowed to remain in contact with the pavers for 10 minutes before removal.

Soiled pavers were allowed to dry before test cleaning.

Heavy deposits of mortar or grout were removed with dry scraping after 24 hours. Prepared cleaning solutions were then evaluated for their effectiveness in removing residual Ash Grove[®] Type S mortar after 3, 7, and 14 days of curing. Prepared cleaning solutions were evaluated for their effectiveness in removing residual grout after 3 and 7 days of curing.

B. Limiting Surface Alterations – Enviro Klean[®] Safety Klean and either Sure Klean[®] 600 Detergent or Sure Klean[®] Vana Trol[®] were tested at various dilutions to determine if a cleaning program implemented to remove excess mortar or grout, and related new construction soiling would otherwise alter the appearance of cleaned surfaces. Surface Alteration was evaluated visually based upon perceived discoloration or erosion/etching of the masonry unit.

Surface Finish Removal is the visual examination of the pavers comparing the surface finish of the untreated control surface to the surface finish cleaned with selected product(s) at given dilutions.

Substrate Deterioration is the visual examination of the pavers comparing the surface of the untreated control to surfaces cleaned with selected product(s) at given dilutions looking for any potential erosion/digestion of the paver.

Color Change is the visual examination comparing the color of the untreated control surface to color of surfaces cleaned with selected products at given dilutions.

Staining is the visual examination for changes that are the result of a chemical reaction that leaves a staining precipitate.


C. Water Repellent Evaluation - Consolideck[®] Saltguard[®] WB, Stand Off[®] SLX100 Water & Oil Repellent, Stand Off[®] Impregnator, and Sure Klean[®] Paver Enhancer were evaluated on the submitted samples for their ability to provide water repellency.

D. Stain Repellency – Stand Off[®] SLX100 Water & Oil Repellent, Stand Off[®] Stone, Tile, & Masonry Protector, and Stand Off[®] Impregnator were evaluated for their ability to repel stains.

E. Color Enhancement – Sure Klean[®] Paver Enhancer and Stand Off[®] Gloss 'N Guard were evaluated for their ability to provide color enhancement to the submitted pavers.



PALLET TAG PROGRAM LABORATORY REPORT



PRODUCTS EVALUATED FOR CLEANING AND LIMITING SURFACE ALTERATIONS

| Sample | Product | Dilution |
|---|----------------------------|----------|
| "Bourbon Street" "Burgundy Straight-Edge" "Heartland Flash" "Red Straight-Edge" | Sure Klean® 600 Detergent | 1:6, 1:8 |
| | Enviro Klean® Safety Klean | 1:2, 1:3 |
| "Dark Gray" "Dark Pink" "Key West" "Medium Brown" "Parquet Tan" "Peachtree Avenue" "Pink" "Santee Gray" "Savannah Brown" "Tan" | Sure Klean® Vana Trol® | 1:6, 1:8 |
| | Enviro Klean® Safety Klean | 1:2, 1:3 |


WATER REPELLENT PRODUCTS EVALUATED

| SAMPLE | TREATMENT | DILUTION |
|---------------------------|---|-------------|
| All Submitted Clay Pavers | Sure Klean® Paver Enhancer | Concentrate |
| | Consolideck® Saltguard® WB | Concentrate |
| | Stand Off® SLX100 Water & Oil Repellent | Concentrate |
| | Stand Off® Impregnator | Concentrate |

Dilution ratios refer to mixtures of concentrated product : fresh water.



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 5

STAIN REPELLENT PRODUCTS EVALUATED

| SAMPLE | TREATMENT | DILUTION |
|---------------------------|--|-------------|
| All Submitted Clay Pavers | Stand Off [®] SLX100 Water & Oil Repellent | Concentrate |
| | Stand Off [®] Stone, Tile & Masonry Protector | Concentrate |
| | Stand Off [®] Impregnator | Concentrate |


COLOR ENHANCEMENT PRODUCTS EVALUATED

| SAMPLE | TREATMENT | DILUTION |
|---------------------------|--|-------------|
| All Submitted Clay Pavers | Sure Klean [®] Paver Enhancer | Concentrate |
| | Stand Off [®] Gloss 'N Guard | Concentrate |

Dilution ratios refer to mixtures of concentrated product : fresh water.



PALLET TAG PROGRAM LABORATORY REPORT



SECTION A – NEW CONSTRUCTION CLEANING

DESCRIPTION OF PRODUCTS EVALUATED – New Construction Cleaning

These cleaning trials were conducted to determine the optimal cleaning/cure time combination to most efficiently remove Ash Grove® Type S mortar or grout from the submitted clay pavers.

Ash Grove® Type S cementitious mortar was prepared in compliance with the manufacturers instructions, applied to the paver surface and allowed to cure for 3, 7 and 14 days. Sanded grout was applied to the paver surface and allowed to cure for 3 and 7 days. Mortar and grout removal was accomplished using chemical assistance and a high-pressure water rinse with pressure rinsing equipment. The removal of Ash Grove® Type S cementitious masonry mortar was visually evaluated after 3, 7 and 14 days of curing. Removal of sanded grout was evaluated after 3 and 7 days.

Enviro Klean® Safety Klean – An effective, safe alternative to acidic compounds for cleaning brick, tile, and concrete surfaces. Safety Klean rids new masonry construction of excess mortar, dirt and other common job site soiling. It's ideal for projects where traditional acidic cleaners are not allowed. Non-fuming Safety Klean contains no hydrochloric or other traditional inorganic acids and is safe for use on and around most metal surfaces. Always test. Additionally, it is up to 70 percent more effective than citric and glycolic acids, and 50 percent more effective than phosphoric acid.

Sure Klean® 600 Detergent – A general purpose, concentrated acidic cleaner for brick, tile and concrete surfaces. 600 Detergent dissolves mortar smears and construction dirt quickly, leaving the masonry clean and uniform with no acid burning or streaking.

Sure Klean® Vana Trol® - A concentrated acidic cleaner for new masonry surfaces that are subject to vanadium, manganese and other metallic stains. Use on: gray, brown, white, and most light-colored brick; natural stone; cast stone. Dissolves mortar smears and construction dirt quickly, leaving the masonry clean and uniform with no acid burning or streaking. Liquid concentrate for dilution with 4-10 parts water. Apply by brush or low-pressure spray.

TEST METHOD – New Construction Cleaning

Dilution ratios refer to mixtures of concentrated cleaner : fresh water. Chemical cleaners were evaluated using the following procedure:


1. Prewet the surface with water.
2. Apply the cleaner.
3. Allow the appropriate dwell time, as specified.

| | |
|---------------------|-------------|
| Safety Klean | 3-5 minutes |
| 600 Detergent | 3-5 minutes |
| Vana Trol® | 3-5 minutes |
4. Pressure rinse thoroughly.*

*Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.



PALLET TAG PROGRAM LABORATORY REPORT



Test Results – New Construction Cleaning

% Removal (Type S Mortar)

“Bourbon Street”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® 600 Detergent | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 100% |

“Burgundy Straight-Edge”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® 600 Detergent | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 99% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 99% |
| | 1:3 | 100% | 100% | 99% |

“Dark Gray”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 100% |

“Dark Pink”


| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 100% |

“Heartland Flash”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® 600 Detergent | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



Test Results – New Construction Cleaning

% Removal (Type S Mortar)

“Key West”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 99% | 99% |
| | 1:8 | 100% | 95% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 99% | 99% | 95% |
| | 1:3 | 99% | 99% | 95% |

“Medium Brown”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 95% |

“Parquet Tan”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 100% |

“Peachtree Avenue”


| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 100% |

“Pink”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 95% |
| | 1:8 | 100% | 99% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 99% | 95% | 95% |
| | 1:3 | 95% | 95% | 95% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 9

Test Results – New Construction Cleaning

% Removal (Type S Mortar)

“Red Straight-Edge”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® 600 Detergent | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 100% |

“Santee Gray”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 100% |
| | 1:3 | 100% | 100% | 100% |

“Savannah Brown”


| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 99% |
| | 1:8 | 100% | 100% | 90% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 90% |
| | 1:3 | 100% | 100% | 90% |

“Tan”

| Product | Dilution | 3 day | 7 day | 14 day |
|----------------------------|----------|-------|-------|--------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% | 100% |
| | 1:8 | 100% | 100% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% | 95% |
| | 1:3 | 100% | 100% | 95% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 10

Test Results – New Construction Cleaning

% Removal (Sanded Grout)

“Bourbon Street”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® 600 Detergent | 1:6 | 95% | 95% |
| | 1:8 | 95% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 95% | 95% |
| | 1:3 | 95% | 95% |

“Burgundy Straight-Edge”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® 600 Detergent | 1:6 | 99% | 99% |
| | 1:8 | 99% | 99% |
| Enviro Klean® Safety Klean | 1:2 | 95% | 99% |
| | 1:3 | 95% | 95% |

“Dark Gray”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 99% | 99% |
| | 1:8 | 99% | 99% |
| Enviro Klean® Safety Klean | 1:2 | 99% | 99% |
| | 1:3 | 99% | 99% |

“Dark Pink”


| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 95% | 95% |
| | 1:8 | 95% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 95% | 95% |
| | 1:3 | 95% | 95% |

“Heartland Flash”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® 600 Detergent | 1:6 | 100% | 99% |
| | 1:8 | 100% | 99% |
| Enviro Klean® Safety Klean | 1:2 | 99% | 95% |
| | 1:3 | 95% | 95% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 11

Test Results – New Construction Cleaning

% Removal (Sanded Grout)

“Key West”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 99% | 95% |
| | 1:8 | 99% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 95% | 95% |
| | 1:3 | 95% | 95% |

“Medium Brown”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% |
| | 1:8 | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% |
| | 1:3 | 100% | 100% |

“Parquet Tan”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% |
| | 1:8 | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% |
| | 1:3 | 100% | 100% |

“Peachtree Avenue”


| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 99% | 95% |
| | 1:8 | 99% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 95% | 90% |
| | 1:3 | 95% | 90% |

“Pink”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 99% | 99% |
| | 1:8 | 95% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 99% | 99% |
| | 1:3 | 99% | 99% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 12

Test Results – New Construction Cleaning

% Removal (Sanded Grout)

“Red Straight-Edge”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® 600 Detergent | 1:6 | 95% | 95% |
| | 1:8 | 95% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 99% | 99% |
| | 1:3 | 99% | 95% |

“Santee Gray”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 100% | 100% |
| | 1:8 | 100% | 100% |
| Enviro Klean® Safety Klean | 1:2 | 100% | 100% |
| | 1:3 | 100% | 100% |

“Savannah Brown”


| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 99% | 99% |
| | 1:8 | 99% | 99% |
| Enviro Klean® Safety Klean | 1:2 | 99% | 100% |
| | 1:3 | 99% | 100% |

“Tan”

| Product | Dilution | 3 day | 7 day |
|----------------------------|----------|-------|-------|
| Sure Klean® Vana Trol® | 1:6 | 99% | 99% |
| | 1:8 | 95% | 95% |
| Enviro Klean® Safety Klean | 1:2 | 95% | 95% |
| | 1:3 | 95% | 95% |



PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 13

PHOTOGRAPHS – Cleaning (Type S Mortar Removal)

“Bourbon Street” Clay Paver; 3 Day Cleaning

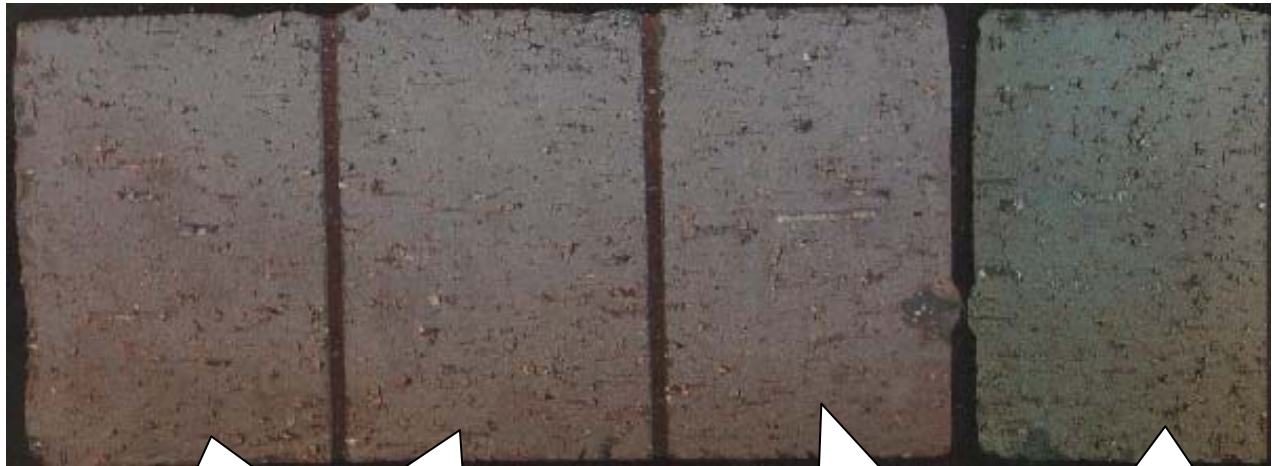


Sure Klean® 600
Detergent 1:6

Sure Klean® 600
Detergent 1:8

Enviro Klean®
Safety Klean 1:2

Enviro Klean®
Safety Klean 1:3

“Bourbon Street” Clay Paver; 7 day cleaning

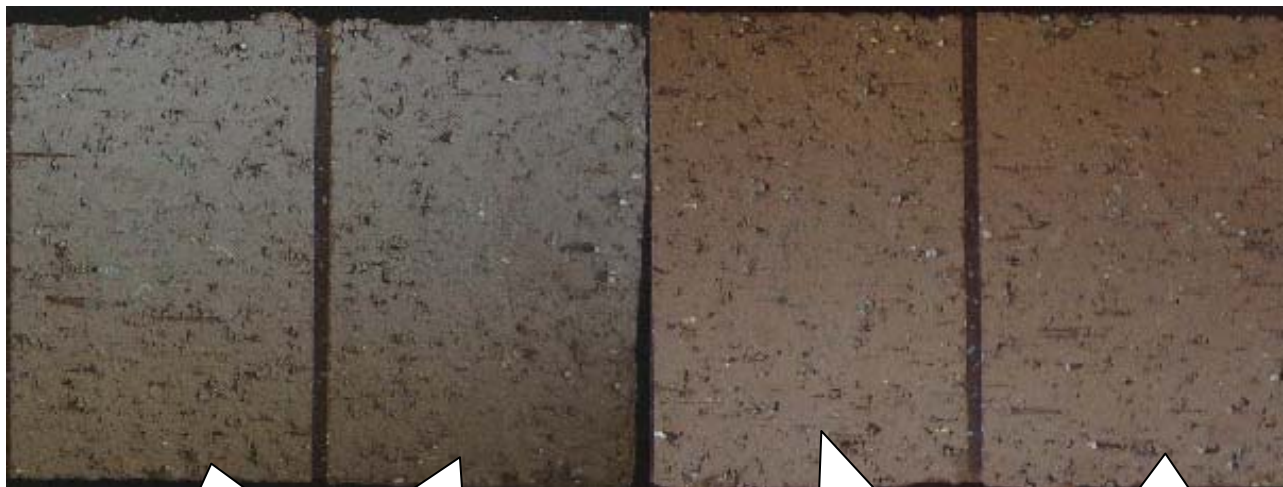

Sure Klean® 600
Detergent 1:6


Sure Klean® 600
Detergent 1:8

Enviro Klean®
Safety Klean 1:2

Enviro Klean®
Safety Klean 1:3



PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 14

PHOTOGRAPHS – Continued (Type S Mortar Removal)

“Bourbon Street” Clay Paver; 14 day cleaning

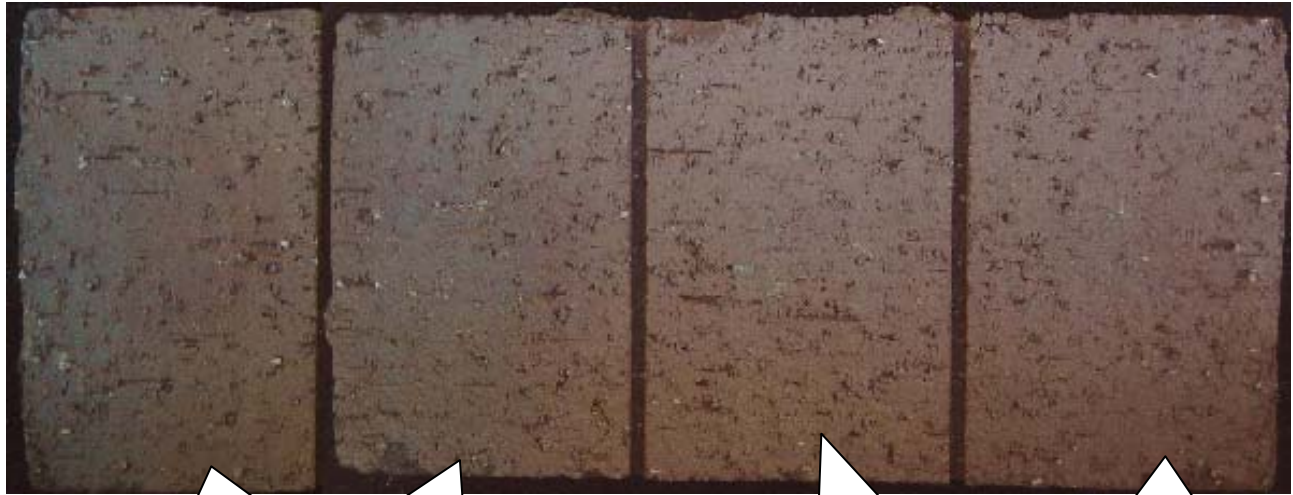

Sure Klean® 600
Detergent 1:6


Sure Klean® 600
Detergent 1:8

Enviro Klean®
Safety Klean 1:2

Enviro Klean®
Safety Klean 1:3



PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 15

PHOTOGRAPHS – Cleaning (Sanded Grout Removal)

“Bourbon Street” Clay Paver; 3 Day Cleaning

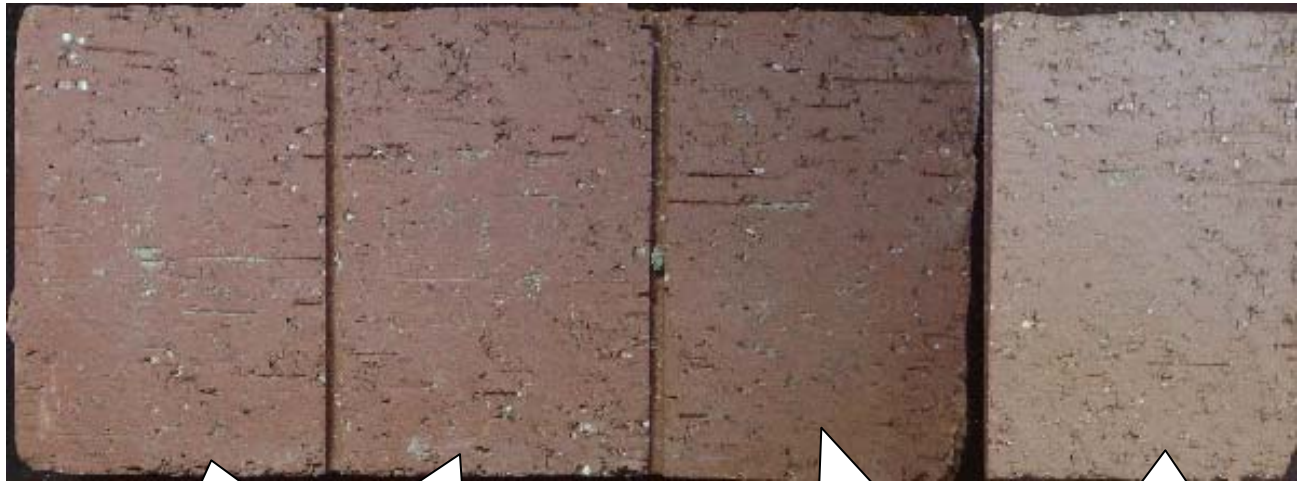


Sure Klean® 600
Detergent 1:6

Sure Klean® 600
Detergent 1:8

Enviro Klean®
Safety Klean 1:2

Enviro Klean®
Safety Klean 1:3

“Bourbon Street” Clay Paver; 7 day cleaning

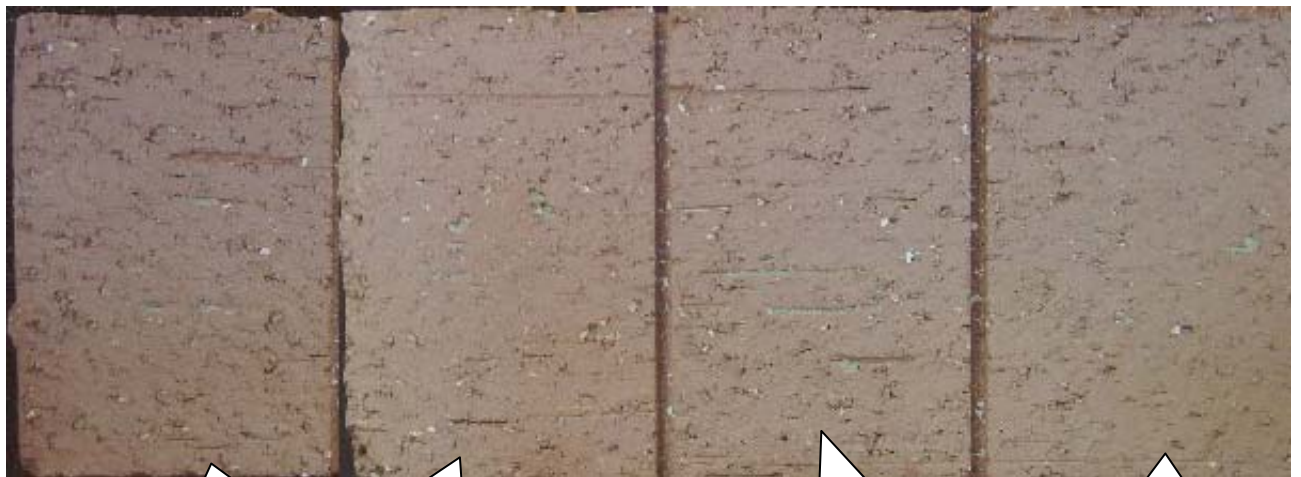

Sure Klean® 600
Detergent 1:6


Sure Klean® 600
Detergent 1:8

Enviro Klean®
Safety Klean 1:2

Enviro Klean®
Safety Klean 1:3



PALLET TAG PROGRAM LABORATORY REPORT



CONCLUSIONS – New Construction Cleaning

Based on the test results, all PROSOCO, Inc. products tested performed well in removing excess mortar or grout smears from the submitted clay pavers. These products performed well in removing the mortar soils even after allowing the mortar to remain on the surface of the pavers for 14 days under ideal curing conditions, and performed well in removing the grout soils after 7 days of curing.

It is recommended that the selected cleaners always be used in the lowest possible concentration. They should be rinsed with the lowest pressure of water as practical, at least 400 psi, to minimize removal of the decorative finish. Excessive pressure and water volume may combine to damage or remove decorative finishes. To facilitate easier removal of excess mortar and construction dirt while minimizing any potential surface alterations to the decorative finish, clean within 7 days of construction.

RECOMMENDATIONS– New Construction Cleaning

Recommendations for cleaning for each type of clay paver submitted by Boral Bricks, Inc., Augusta, GA, are provided in the chart below. Recommendations are based on the optimum dilution for complete removal of mortar while limiting surface alterations.


| Paver Type | New Construction Cleaning (Type S, 14 Days) | New Construction Cleaning (Sanded Grout, 7 Days) |
|---|---|---|
| “Bourbon Street” “Burgundy Straight-Edge” “Heartland Flash” “Red Straight-Edge” | Sure Klean® 600 Detergent (1:8) OR Enviro Klean® Safety Klean (1:3) | Sure Klean® 600 Detergent (1:8) OR Enviro Klean® Safety Klean (1:3) |
| “Dark Gray” “Dark Pink” “Key West” “Medium Brown” “Parquet Tan” “Peachtree Avenue” “Pink” “Santee Gray” “Savannah Brown” “Tan” | Sure Klean® Vana Trol® (1:8) OR Enviro Klean® Safety Klean (1:3) | Sure Klean® Vana Trol® (1:8) OR Enviro Klean® Safety Klean (1:3) |

Excessive pressure and water volume may combine to damage or remove decorative finishes. To facilitate easier removal of excess mortar, grout, and construction dirt while minimizing any potential surface alterations to the decorative finish, clean within 7 days of construction. Rinsing with high-pressure spray (400-800 psi) is recommended.

Apply all products in accordance with the manufacturer’s recommendation provided on container labels and product data sheets. On-site testing should always be conducted to determine the most appropriate cleaning product and procedures for a particular project. See product literature for additional application and product information.



PALLET TAG PROGRAM LABORATORY REPORT



SECTION B – LIMITING SURFACE ALTERATIONS

DESCRIPTION OF PRODUCTS EVALUATED – Limiting Surface Alterations

Enviro Klean® Safety Klean – An effective, safe alternative to acidic compounds for cleaning brick, tile, and concrete surfaces. Safety Klean rids new masonry construction of excess mortar, dirt and other common job site soiling. It's ideal for projects where traditional acidic cleaners are not allowed. Non-fuming Safety Klean contains no hydrochloric or other traditional inorganic acids and is safe for use on and around most metal surfaces. Always test. Additionally, it is up to 70 percent more effective than citric and glycolic acids, and 50 percent more effective than phosphoric acid.

Sure Klean® 600 Detergent – A general purpose, concentrated acidic cleaner for brick, tile and concrete surfaces. 600 Detergent dissolves mortar smears and construction dirt quickly, leaving the masonry clean and uniform with no acid burning or streaking.

Sure Klean® Vana Trol® - A concentrated acidic cleaner for new masonry surfaces that are subject to vanadium, manganese and other metallic stains. Designed for use on gray, brown, white and most light-colored brick, natural stone and cast stone. Dissolves mortar smears and construction dirt quickly, leaving the masonry clean and uniform with no acid burning or streaking. Liquid concentrate for dilution with 4-10 parts water. Apply by brush or low-pressure spray.

TEST METHOD – Limiting Surface Alterations:

Dilution ratios refer to mixtures of concentrated cleaner: fresh water. Chemical cleaners were evaluated using the following procedure:


1. Prewet the surface with water.
2. Apply the cleaner.
3. Allow the appropriate dwell time, as specified.

| | |
|---------------------|-------------|
| Safety Klean..... | 3-5 minutes |
| 600 Detergent | 3-5 minutes |
| Vana Trol® | 3-5 minutes |
4. Pressure rinse thoroughly. *

* Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.



PALLET TAG PROGRAM LABORATORY REPORT




TEST RESULTS – Limiting Surface Alterations

| Substrate: Clay Paver | | Pigment Color: “Key West” | | | |
|------------------------------|----------|--|-------------------------|--------------|----------|
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® Vana Trol® | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® Vana Trol® | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |
| Substrate: Clay Paver | | Pigment Color: “Medium Brown” | | | |
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® Vana Trol® | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® Vana Trol® | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |
| Substrate: Clay Paver | | Pigment Color: “Parquet Tan” | | | |
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® Vana Trol® | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® Vana Trol® | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |
| Substrate: Clay Paver | | Pigment Color: “Peachtree Avenue” | | | |
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® Vana Trol® | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® Vana Trol® | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |
| Substrate: Clay Paver | | Pigment Color: “Pink” | | | |
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® Vana Trol® | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® Vana Trol® | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |

0 – No change 3 – change – heavy
 1 – change – slight 4 – change - excessive
 2 – change – moderate



PALLET TAG PROGRAM LABORATORY REPORT




TEST RESULTS – Limiting Surface Alterations

| Substrate: Clay Paver | | Pigment Color: “Red Straight-Edge” | | | |
|------------------------------|----------|---|-------------------------|--------------|----------|
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® 600 Detergent | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® 600 Detergent | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |
| Substrate: Clay Paver | | Pigment Color: “Santee Gray” | | | |
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® Vana Trol® | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® Vana Trol® | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |
| Substrate: Clay Paver | | Pigment Color: “Savannah Brown” | | | |
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® Vana Trol® | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® Vana Trol® | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |
| Substrate: Clay Paver | | Pigment Color: “Tan” | | | |
| Product | Dilution | Surface Finish Removal | Substrate Deterioration | Color Change | Staining |
| Sure Klean® Vana Trol® | 1:6 | 0 | 0 | 0 | 0 |
| Sure Klean® Vana Trol® | 1:8 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:2 | 0 | 0 | 0 | 0 |
| Enviro Klean® Safety Klean | 1:3 | 0 | 0 | 0 | 0 |

0 – No change 3 – change – heavy
 1 – change – slight 4 – change - excessive
 2 – change – moderate



PALLET TAG PROGRAM LABORATORY REPORT



CONCLUSIONS – Limiting Surface Alterations

Test results indicate that none of the products tested caused any surface alterations on any of the submitted clay pavers. It is recommended that the selected cleaners always be used in the lowest possible concentration. They should be rinsed with the lowest pressure of water as practical to minimize removal of the decorative finish. Excessive pressure and water volume may combine to damage or remove decorative finishes. To facilitate easier removal of excess mortar and construction dirt while minimizing any potential surface alterations to the decorative finish, clean within 7 days of construction.

RECOMMENDED PRODUCTS AND DILUTIONS – Limiting Surface Alterations

Product recommendations for limiting surface alterations for each type of clay paver submitted by Boral Bricks, Inc., Augusta, GA, are provided in the chart below. Recommendations are based on the optimum dilution for complete removal of mortar while limiting surface alterations.


| Paver Type | Limiting Surface Alterations |
|---|---|
| “Bourbon Street” “Burgundy Straight-Edge” “Heartland Flash” “Red Straight-Edge” | Sure Klean® 600 Detergent (1:8) OR Enviro Klean® Safety Klean (1:3) |
| “Dark Gray” “Dark Pink” “Key West” “Medium Brown” “Parquet Tan” “Peachtree Avenue” “Pink” “Santee Gray” “Savannah Brown” “Tan” | Sure Klean® Vana Trol® (1:8) OR Enviro Klean® Safety Klean (1:3) |

Excessive pressure and water volume may combine to damage or remove decorative finishes. To facilitate easier removal of excess mortar, grout, and construction dirt while minimizing any potential surface alterations to the decorative finish, clean within 7 days of construction. Rinsing with high-pressure spray (400-800 psi) is recommended.

Apply all products in accordance with the manufacturer’s recommendation provided on container labels and product data sheets. On-site testing should always be conducted to determine the most appropriate cleaning product and procedures for a particular project. See product literature for additional application and product information.



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 22

SECTION C - PROTECTIVE WATER REPELLENTS:

The testing described below evaluates the suitability of water repellent treatments.

The surface treatments evaluated were selected for their suitability for application based on the following selection criteria:

1. Weatherproofing properties
2. Color change
3. Ease of application

DESCRIPTIONS OF PRODUCTS EVALUATED - Protective Water Repellents:

Consolideck® Saltguard® WB – A ready-to-use water-based, VOC compliant silane/siloxane water repellent and “chloride screen” for the protection of concrete and masonry surfaces. Saltguard® WB penetrates more deeply than conventional water- or solvent-based water repellents. Low odor and alkaline stable, Saltguard® WB is ideal for field or in-plant application to concrete and most masonry surfaces. Saltguard® WB protects horizontal and vertical surfaces from moisture intrusion and chemical attack of chloride salts.

Sure Klean® Paver Enhancer - A solvent-based blend of high-quality siloxanes modified to provide excellent water repellency and color enhancement to interlocking concrete, fired clay, porous tile and many types of natural stone surfaces. Paver Enhancer penetrates and reacts with the surface to form a chemical bond, providing long-term durability, alkali resistance and superior breatheability.

Stand Off® SLX100 Water & Oil Repellent - Combines water and oil repellency on most substrates to prevent staining by waterborne and oily substances. This modified “heat” silane system offers invisible protection and low volatility. The small molecular structure of SLX100 allows for maximum penetration at coverage rates higher than that of conventional silanes. Depth of penetration is controlled by the application rate (loading rate). This makes SLX100 ideal for protecting granite and other dense, color-sensitive surfaces.


Stand Off® Impregnator – Combines water and oil repellency to prevent staining by waterborne or oily substances. This special system offers invisible protection and low volatility.

SAMPLE PREPARATION - Protective Water Repellents:

The submitted pavers were cut, dried and allowed to reabsorb atmospheric humidity for at least 24 hours prior to treatment. The treatment method adhered to the 2004 PROSOCO, Inc. Product Guide. All treatments were allowed to cure for at least 3 days prior to testing.



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 23

TEST METHODS - Protective Water Repellents:

Water Absorption Tube Test: Horizontal RILEM II.4, 5.0 milliliters, 20 minutes

The water absorption tube test simulating wind driven and wind blown rain conditions was performed. Tests were run with horizontal 5.0-milliliter head pressures. Filled to 5 milliliters, a water absorption tube produces a 103 mph dynamic wind pressure. See RILEM II.4 Tech Note for additional information.

The ranking system used to evaluate the effectiveness of the products applied to each submitted sample is as follows:

AA = "Above Average" correlates to less than or equal to 20% of the maximum untreated absorption.

A = "Average" correlates to less than or equal to 50% of the maximum untreated absorption.

BA = "Below Average" correlates to greater than 50% of the maximum untreated absorption.

EXAMPLE: If RILEM tubes applied to an untreated sample result in loss of 5 ml of water or more, then:


A rating of **AA** *Above Average* water repellent performance would require loss of no more than 5 ml X 20% = 1 ml.

A rating of **A** *Average* water repellent performance would require loss of no more than 5 ml X 50% = 2.5ml.

A rating of **BA** *Below Average* water repellent performance would be reported for treatments which result in a loss of more than 50% X 5ml = 2.5ml+.



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 24


TEST RESULTS:

Water Absorption Tube Test: Horizontal RILEM II.4, 5.0 milliliters, 20 minutes
AA = Above Average A = Average BA = Below Average

| “Bourbon Street” | Results in mL loss | Ranking |
|---------------------------------|---------------------------|----------------|
| Untreated Control | 0.5 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.3 | <u>AA</u> |
| “Burgundy Straight-Edge” | Results in mL loss | Ranking |
| Untreated Control | 0.3 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.0 | <u>AA</u> |
| “Dark Gray” | Results in mL loss | Ranking |
| Untreated Control | 4.3 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.3 | <u>AA</u> |
| “Dark Pink” | Results in mL loss | Ranking |
| Untreated Control | 2.2 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.2 | <u>AA</u> |
| “Heartland Flash” | Results in mL loss | Ranking |
| Untreated Control | 0.5 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard WB | 0.0 | <u>AA</u> |
| “Key West” | Results in mL loss | Ranking |
| Untreated Control | 5.0 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.2 | <u>AA</u> |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 25


TEST RESULTS:

Water Absorption Tube Test: Horizontal RILEM II.4, 5.0 milliliters, 20 minutes
AA = Above Average A = Average BA = Below Average

| “Medium Brown” | Results in mL loss | Ranking |
|----------------------------|---------------------------|----------------|
| Untreated Control | 2.4 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.0 | <u>AA</u> |
| “Parquet Tan” | Results in mL loss | Ranking |
| Untreated Control | 0.2 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.0 | <u>AA</u> |
| “Peachtree Avenue” | Results in mL loss | Ranking |
| Untreated Control | 1.4 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.0 | <u>AA</u> |
| “Pink” | Results in mL loss | Ranking |
| Untreated Control | 5.0 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.5 | <u>AA</u> |
| “Red Straight-Edge” | Results in mL loss | Ranking |
| Untreated Control | 1.5 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.0 | <u>AA</u> |
| “Santee Gray” | Results in mL loss | Ranking |
| Untreated Control | 0.8 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.3 | <u>AA</u> |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 26


TEST RESULTS:

Water Absorption Tube Test: Horizontal RILEM II.4, 5.0 milliliters, 20 minutes
AA = Above Average A = Average BA = Below Average

| "Savannah Brown" | Results in mL loss | Ranking |
|-------------------------|---------------------------|----------------|
| Untreated Control | 0.5 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.5 | <u>AA</u> |
| "Tan" | Results in mL loss | Ranking |
| Untreated Control | 1.1 | -- |
| Paver Enhancer | 0.0 | <u>AA</u> |
| SLX100 | 0.0 | <u>AA</u> |
| Impregnator | 0.0 | <u>AA</u> |
| Saltguard® WB | 0.0 | <u>AA</u> |



PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 27

PHOTOGRAPH – Water Repellents

“Bourbon Street” Clay Paver; RILEM Testing

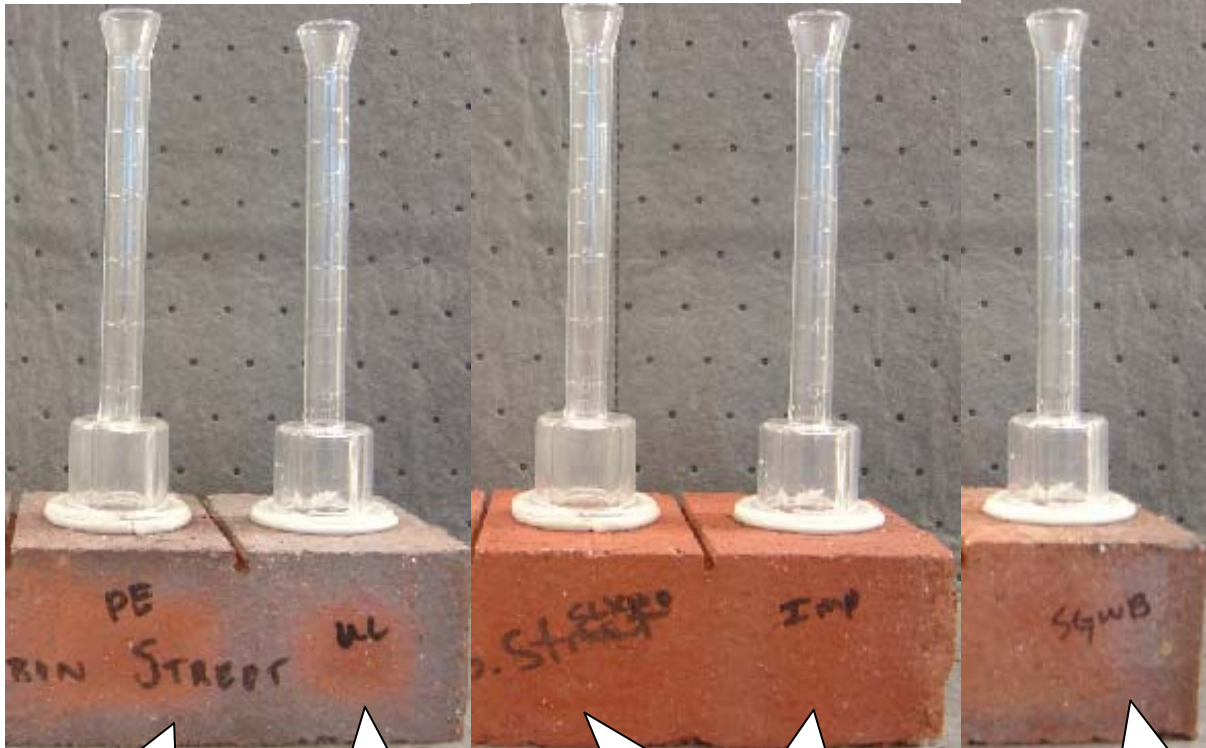

**Sure Klean®
Paver
Enhancer**

**Untreated
Control**


**Stand Off®
SLX100 Water &
Oil Repellent**

**Stand Off®
Impregnator**

**Consolideck®
Saltguard®
WB**



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 28

CONCLUSIONS – Protective Water Repellents:

Test results indicate that all of the water repellents tested exhibited above average water repellency on all submitted clay pavers.

RECOMMENDATIONS – Protective Water Repellents:

Recommendations for water repellent treatments for each type of clay paver submitted by Boral Bricks, Inc., Augusta, GA, are provided in the chart below. Recommendations are based on the treatments that proved most effective and can provide water repellency on all types indicated.


| Paver Type | Water Repellent |
|---------------------------|---|
| All Submitted Clay Pavers | Sure Klean [®] Paver Enhancer OR Consolideck [®] Saltguard [®] WB OR Stand Off [®] SLX100 Water & Oil Repellent OR Stand Off [®] Impregnator |

The ability of a water repellent treatment to prevent the ingress of water is affected by a variety of factors. Therefore, on-site testing should be carried out for all installations with the recommended systems to ensure job site workmanship yields equivalent results.

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate water repellent product and procedures for a particular project. See product literature for additional application and product information.



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 29

SECTION D – STAIN REPELLENCY

These trials were conducted to determine the effectiveness of treatments in preventing food, oil, and miscellaneous staining on the submitted samples.

DESCRIPTION OF PRODUCTS EVALUATED - Stain Protection:

Stand Off® Stone, Tile & Masonry Protector – A penetrating oil and stain repellent. Easy-to-use. Low-VOC, low-odor protective treatment improves the stain resistance and simplifies maintenance cleaning of interior and exterior stone, quarry tile, concrete and masonry surfaces.

Stand Off® SLX100 Water & Oil Repellent - Combines water and oil repellency on most substrates to prevent staining by waterborne and oily substances. This modified “neat” silane system offers invisible protection and low volatility. The small molecular structure of SLX100 allows for maximum penetration at coverage rates higher than that of conventional silanes. Depth of penetration is controlled by the application rate (loading rate). This makes SLX100 ideal for protecting granite and other dense, color-sensitive surfaces.

Stand Off® Impregrator – Combines water and oil repellency to prevent staining by waterborne or oily substances. This special system offers invisible protection and low volatility.

Kitchen Products Evaluated:

Coca Cola
Ketchup
Mustard
Red wine
Balsamic Vinegar
Soy Sauce
Olive Oil
Wesson Oil
Coffee

Temperature:


ambient (~70°F)
ambient (~70°F)
ambient (~70°F)
ambient (~70°F)
ambient (~70°F)
ambient (~70°F)
ambient (~70°F)
(~250°F)
(~120°F)

SAMPLE PREPARATION – Stain Repellency

Samples were cleaned with Enviro Klean® 2010 All Surface Cleaner diluted with 10 parts water, allowed to dry and absorb atmospheric moisture for 24 hours prior to treatment. The method of application for protective treatments followed the PROSOCO, Inc. 2004 Product Guide.



PALLET TAG PROGRAM LABORATORY REPORT



TEST METHOD – Stain Repellency

Surface Beading Evaluation

The food and oil products were applied to the test areas by using a dropper creating a bead 0.5 – 1.0 cm in diameter. The beading properties of the oils and liquids were visually evaluated within two minutes after application. The results are reported as a rating based on the angle of contact between the base of the droplet and the substrate. A rating of “1 or 2” indicated the smallest angle of contact ($<90^\circ$) which correlates to “above average” repellency. A rating of “3 or 4” indicates “average” repellency. A rating of “5 or greater” indicated that the oil quickly absorbed into the substrate and correlates to “below average” repellency.


Note: Non-free flowing staining agents such as ketchup and mustard are applied in a blob and not evaluated for their beading properties.

Rating System (1-5)


1. No wetting of contact area (no darkening); angle less than 90°




2. Wetting contained to the contact area (slight darkening); angle is less than 90°



3. Wetting contained to the contact area (slight darkening); angle is greater than 90° , but less than 135° .



4. Wetting beyond the contact area (darkening); angle is greater than 135°



5. Wetting beyond the contact area (darkening); angle is flat.




Stain Removal Evaluation

The soiling agents were allowed to dwell on the treated and untreated substrates for times of 24 hours, 4 hours, 1 hour, and 10 minutes. The test areas were then cleaned with Enviro Klean[®] 2010 All Surface Cleaner diluted 1 part concentrate to 10 parts fresh water and scrubbed under a stream of running water from a faucet. Samples were allowed to dry for 24 hours. Evaluation consisted of a visual examination of the tested areas to determine the percentage of staining removal.



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 31

TEST RESULTS – Surface Beading

| “Bourbon Street” | | | | | | | | | |
|---------------------------------|-----------|---------|---------|----------|------------------|-----------|-----------|------------|------------|
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Burgundy Straight-Edge” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Dark Gray” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Dark Pink” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Heartland Flash” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Key West” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.


Page 32

TEST RESULTS – Surface Beading

| “Medium Brown” | | | | | | | | | |
|----------------------------|-----------|---------|---------|----------|------------------|-----------|-----------|------------|------------|
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Parquet Tan” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Peachtree Avenue” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Pink” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Red Straight-Edge” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |
| “Santee Gray” | | | | | | | | | |
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 33


TEST RESULTS – Surface Beading

| "Savannah Brown" | | | | | | | | | |
|-------------------|-----------|---------|---------|----------|------------------|-----------|-----------|------------|------------|
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |

| "Tan" | | | | | | | | | |
|-------------------|-----------|---------|---------|----------|------------------|-----------|-----------|------------|------------|
| | Coco-Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| Untreated Control | 4 | - | - | 3 | 3 | 3 | 3 | 4 | 4 |
| STMP | 3 | - | - | 3 | 3 | 3 | 2 | 3 | 3 |
| SLX 100 | 2 | - | - | 2 | 2 | 2 | 2 | 2 | 3 |
| Impregnator | 2 | - | - | 2 | 2 | 2 | 2 | 3 | 3 |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Bourbon Street”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 0% | 100% | 95% | 99% | 95% | 95% | 100% |
| 4 hour | 100% | 100% | 10% | 100% | 95% | 99% | 95% | 95% | 100% |
| 1 hour | 100% | 100% | 90% | 100% | 99% | 100% | 95% | 95% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 95% | 95% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Burgundy Straight-Edge”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 10% | 100% | 100% | 100% | 10% | 10% | 10% |
| 4 hour | 100% | 100% | 10% | 100% | 100% | 100% | 10% | 10% | 10% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 36

TEST RESULTS – Staining Removal


% Removal

“Dark Gray”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| 4 hour | 100% | 100% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 37

TEST RESULTS – Staining Removal


% Removal

“Dark Pink”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| 4 hour | 100% | 100% | 10% | 100% | 100% | 100% | 10% | 10% | 10% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Heartland Flash”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 50% | 100% | 100% | 100% | 30% | 90% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 90% | 90% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 90% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 50% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 30% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Key West”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 10% | 100% | 100% | 100% | 10% | 10% | 10% |
| 4 hour | 100% | 100% | 30% | 100% | 100% | 100% | 10% | 10% | 10% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Medium Brown”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 4 hour | 100% | 100% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 70% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Parquet Tan”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 10% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 42

TEST RESULTS – Staining Removal


% Removal

“Peachtree Avenue”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 4 hour | 100% | 100% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 70% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Pink”

| Untreated Control | | | | | | | | | |
|---|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 10% | 100% | 30% | 30% | 10% | 10% | 100% |
| 4 hour | 100% | 100% | 10% | 100% | 30% | 30% | 10% | 10% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| Stand Off® Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off® SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off® Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Red Straight-Edge”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 10% | 100% | 30% | 30% | 10% | 10% | 100% |
| 4 hour | 100% | 100% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 45

TEST RESULTS – Staining Removal


% Removal

“Santee Gray”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 10% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 4 hour | 100% | 100% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 1 hour | 100% | 100% | 10% | 100% | 100% | 100% | 10% | 10% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 46

TEST RESULTS – Staining Removal


% Removal

“Savannah Brown”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 90% | 10% | 100% | 70% | 70% | 10% | 10% | 100% |
| 4 hour | 100% | 90% | 100% | 100% | 70% | 80% | 10% | 10% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 100% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT



TEST RESULTS – Staining Removal


% Removal

“Tan”

| Untreated Control | | | | | | | | | |
|--|------------------|----------------|----------------|-----------------|-------------------------|------------------|------------------|-------------------|-------------------|
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 30% | 70% | 100% | 100% | 100% | 10% | 10% | 10% |
| 4 hour | 100% | 100% | 70% | 100% | 100% | 100% | 10% | 10% | 10% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 10% | 10% | 10% |
| Stand Off[®] Stone, Tile & Masonry Protector | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] SLX100 Water & Oil Repellent | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| Stand Off[®] Impregnator | | | | | | | | | |
| | Coca Cola | Ketchup | Mustard | Red Wine | Balsamic Vinegar | Soy Sauce | Olive Oil | Wesson Oil | Hot Coffee |
| 24 hr | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 4 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 1 hour | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |
| 10 min. | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% | 100% |



PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 48

PHOTOGRAPHS- Stain Results

“Bourbon Street” Clay Paver; Stains Applied

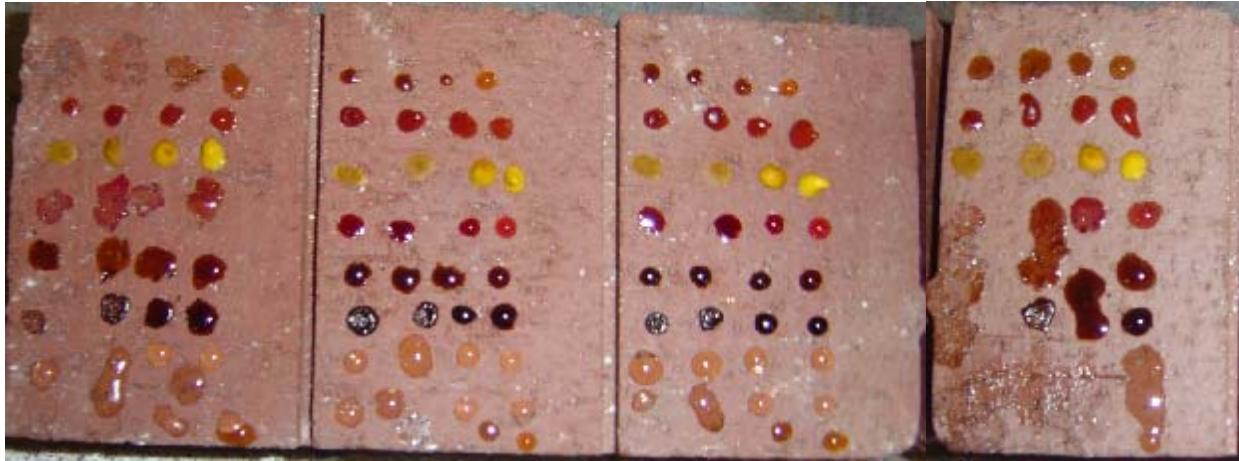

Stand Off® Stone,
Tile, & Masonry
Protector

Stand Off® SLX
100 Water & Oil
Repellent

Stand Off®
Impregnator

Untreated Control

“Bourbon Street” Clay Paver; Stains Removed



Stand Off® Stone,
Tile, & Masonry
Protector


Stand Off® SLX
100 Water & Oil
Repellent

Stand Off®
Impregnator

Untreated Control



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 49

CONCLUSIONS – Stain Repellency

Based upon laboratory evaluations, all of the treatments tested improved the surface beading of the samples. In addition, all of the treatments were effective in repelling the staining agents from the samples.


RECOMMENDATIONS – Stain Repellency

Recommendations for stain resistance treatment for each type of clay paver submitted by Boral Bricks, Inc., Augusta, GA, are provided in the charts below. Recommendations are based on the treatments that proved most effective for providing stain repellency on all types submitted.

| Sample | Stain Repellent | Maintenance Cleaner |
|---------------------------|---|---|
| All Submitted Clay Pavers | Stand Off [®] Impregnator OR Stand Off [®] Stone, Tile & Masonry Protector OR Stand Off [®] SLX100 Water & Oil Repellent | Enviro Klean [®] 2010 All Surface Cleaner (1:10) |



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 50

SECTION E – COLOR ENHANCEMENT:

DESCRIPTION OF PRODUCTS EVALUATED – Color Enhancement:

Sure Klean® Paver Enhancer – A solvent-based blend of high-quality siloxanes modified to provide excellent water repellency and color enhancement to interlocking concrete, fired clay, porous tile and many types of natural stone surfaces. Paver Enhancer penetrates and reacts with the surface to form a chemical bond, providing long-term durability, alkali resistance and superior breatheability.


Stand Off® Gloss 'N Guard – A highly durable protective coating for tile, pavers, terrazzo and other polished and unpolished masonry. Gloss 'N Guard dries to a high-gloss finish that enhances the natural beauty of treated surfaces.

TEST METHOD – COLOR ENHANCEMENT

The color enhancing products were applied in accordance with the application instructions in the 2004 PROSOCO, Inc. Product Guide.



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 51

TEST RESULTS- COLOR ENHANCEMENT

| Paver Name | Sure Klean [®] Paver Enhancer | Stand Off [®] Gloss N' Guard |
|--------------------------|--|---------------------------------------|
| "Bourbon Street" | 3 | 3 |
| "Burgundy Straight-Edge" | 0 | 2 |
| "Dark Gray" | 1 | 1 |
| "Dark Pink" | 1 | 0 |
| "Heartland Flash" | 3 | 3 |
| "Key West" | 0 | 0 |
| "Medium Brown" | 0 | 0 |
| "Parquet Tan" | 0 | 1 |
| "Peachtree Avenue" | 0 | 0 |
| "Pink" | 1 | 0 |
| "Red Straight-Edge" | 0 | 1 |
| "Santee Gray" | 0 | 0 |
| "Savannah Brown" | 1 | 2 |
| "Tan" | 0 | 1 |

Scale: 0- No enhancement; dull


1- Slight Enhancement

2- Moderate Enhancement

3- Significant Enhancement



PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 52

PHOTOGRAPH – Color Enhancement

“Bourbon Street” Clay Paver; Treatments Applied

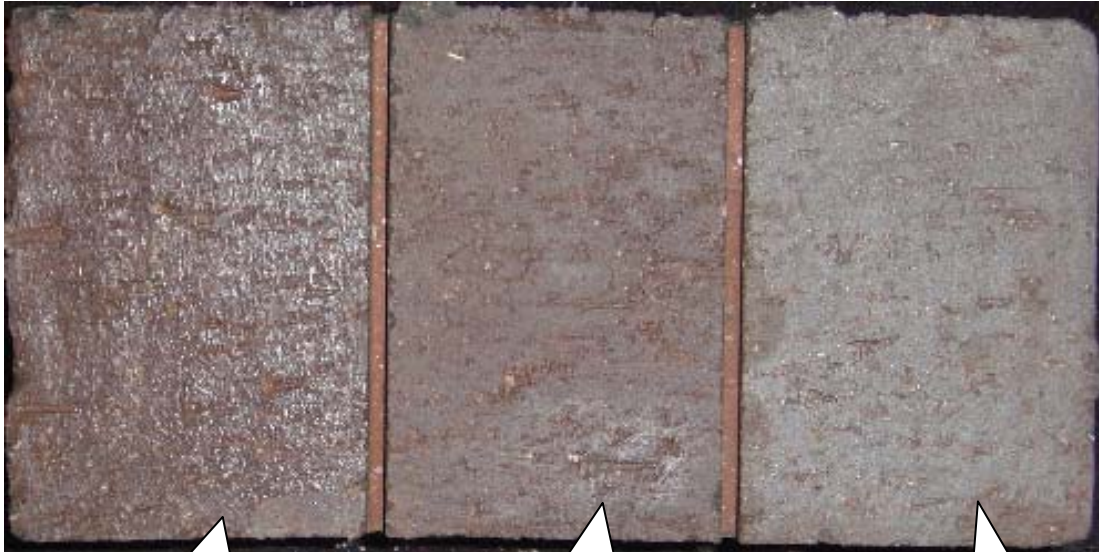


Stand Off[®]
Gloss N' Guard

Sure Klean[®]
Paver Enhancer

Untreated
Control



PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 53


RECOMMENDATIONS – Color Enhancement

Recommendations for color enhancement for each type of clay paver submitted by Boral Bricks, Inc., Augusta, GA, are provided in the chart below. Recommendations are based on the treatment that proved most effective in providing color enhancement to the samples.

| Substrate | Color Enhancer |
|---|---|
| “Bourbon Street” “Dark Gray” “Heartland Flash” | Sure Klean [®] Paver Enhancer OR Stand Off [®] Gloss N’ Guard |
| “Dark Pink” “Pink” | Sure Klean [®] Paver Enhancer |
| “Burgundy Straight-Edge” “Parquet Tan” “Red Straight-Edge” “Savannah Brown” “Tan” | Stand Off [®] Gloss N’ Guard |
| “Key West” “Medium Brown” “Peachtree Avenue” “Santee Gray” | No Recommendation |

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate product and procedures for a particular project. See product literature for additional application and product information.

Christopher A. Moore
Project Testing Laboratory Technician
CAM



Laboratory Report

Pallet Tag Program Evaluation

**Boral Bricks, Inc. (Pavers)
Augusta, GA**

Project No. 0407-08 PTP

Prepared For:

**Boral Bricks, Inc. (Pavers)
1449 Doug Barnard Pkwy
Augusta, GA 30906**

Prepared By:



***PROSOCO, Inc.
December 2004***