




# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 1

## TABLE OF CONTENTS

SAMPLES SUBMITTED .....	2-4
PURPOSE OF TEST .....	5
PRODUCTS EVALUATED .....	6
<b>SECTION A – CLEANING INTEGRALLY COLORED CMU’s</b>	
DESCRIPTION OF PRODUCTS EVALUATED .....	7
TEST METHOD .....	7
TEST RESULTS .....	8-18
PHOTOGRAPHS .....	19-30
CONCLUSIONS .....	31
RECOMMENDATIONS .....	31
<b>SECTION B – COLOR UNIFORMITY</b>	
DESCRIPTION OF PRODUCTS EVALUATED .....	32
TEST METHOD .....	32
TEST RESULTS .....	33-45
PHOTOGRAPHS .....	46-49
CONCLUSIONS .....	50
RECOMMENDATIONS .....	50
<b>SECTION C - PROTECTIVE WATER REPELLENTS</b>	
DESCRIPTION OF PRODUCTS EVALUATED .....	51
TEST METHODS .....	51
TEST RESULTS .....	52-60
PHOTOGRAPHS .....	61
CONCLUSIONS .....	62
RECOMMENDATIONS .....	62
<b>SECTION D – GRAFFITI CONTROL</b>	
DESCRIPTION OF PRODUCTS EVALUATED .....	63
TEST METHOD .....	64
TEST RESULTS .....	65-76
PHOTOGRAPH .....	77
CONCLUSIONS .....	78
RECOMMENDATIONS .....	78

## ATTACHMENTS

Technical Services TECH Note RILEM Tube Test Procedures

Product Data literature for all products evaluated



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 2

**FOR:** Brian Koenings  
**cc:** John Bourne

**SUBJECT:** Northfield Block Company  
 Mundelein, IL

**DATE:** February 20, 2005

**PROJECT:** 0412-04 PTP

**SAMPLES SUBMITTED:** 43 Types of CMU's: 24 split-face/smooth-face, 4 split-face, 10 smooth-face, and 5 ground-face

Block	Name	Color	Integral Water Repellent	Size
Smooth-face CMU	"Beldon Brick #25-Blend"	Orange-Brown/Dark Brown	Dry Blok II	4" x 16" x 8"
Smooth-face CMU	"Heritage Blend #20-Blend"	Red/Dark Brown	Dry Blok II	
Smooth-face CMU	"Lawson Blend #5-Blend"	Orange/Red-Brown	Dry Blok II	
Smooth-face CMU	"Lawson Blend-Spray"	Orange/Red-Brown	Dry Blok II, Okon, G-Pro	
Smooth-face CMU	"Lockport #16-Blend"	Yellow-Tan/Red-Brown	Dry Blok II	
Smooth-face CMU	"Promenade Blend #18-Blend"	Red/Charcoal	Dry Blok II	
Smooth-face CMU	"Promenade Blend-Spray"	Red/Charcoal	Dry Blok II, Okon, G-Pro	
Smooth-face CMU	"Sandlewood Blend #6-Blend"	Brown/Red-Brown	Dry Blok II	
Smooth-face CMU	"Sandlewood Blend-Spray"	Brown/Red-Brown	Dry Blok II, Okon, G-Pro	
Smooth-face CMU	"Springfield Blend-Spray"	Buff/Red-Brown	Dry Blok II, Okon, G-Pro	
Ground-face CMU	"Alabaster"	White	Dry Blok II	8" x 24" x 4"
Ground-face CMU	"Buff"	Yellow/Tan	Dry Blok II	
Ground-face CMU	"Graphite"	Grey	Dry Blok II	
Ground-face CMU	"Limestone"	Tan/White	Dry Blok II	
Ground-face CMU	"Midnight (unsealed)"	Black	Dry Blok II	
Split-face CMU	"Canyon Blend"	Orange/Light Orange	Dry Blok II	8" x 24" x 4"
Split-face CMU	"Desert Blend"	Grey/Buff	Dry Blok II	
Split-face CMU	"Mountain Blend"	Brown/Light Brown	Dry Blok II	
Split-face CMU	"Woodland Blend"	Olive/Grey	Dry Blok II	



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 3**

**SAMPLES SUBMITTED (continued):**

Block	Name	Color	Integral Water Repellent	Size
Split-face CMU	"3776"	Orange-Brown	Dry Blok II	8" x 16" x 8"
Smooth-face CMU				
Split-face CMU	"4660"	Dark Brown	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"4916"	Brown-Tan	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"4970"	Light Purple-Red	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"5558"	Orange-Red	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"8539"	Red-Purple	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"8540"	Purple-Red	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"#191"	Brown	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"#192"	Light Brown	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"#193"	Orange	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"#197"	Tan-Light Orange	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"#21"	Light Yellow-Tan	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"#33"	Tan-Yellow	Dry Blok II	
Smooth-face CMU				



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 4

**SAMPLES SUBMITTED (continued):**

Block	Name	Color	Integral Water Repellent	Size
Split-face CMU	"#43"	Grey	Dry Blok II	8" x 16" x 8"
Smooth-face CMU				
Split-face CMU	"#53"	Orange-Light Brown	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"A-3"	Light Yellow	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"A-7"	Light Tan	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"Ivory"	Yellow-White	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"Mohawk Orange"	Light Brown-Orange	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"Natural"	Light Grey	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"Rose"	Pink-Red	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"Russet"	Red-Brown	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"Std. White"	Grey/White	Dry Blok II	
Smooth-face CMU				
Split-face CMU	"White"	Bright White	Dry Blok II	
Smooth-face CMU				

Submitted by: Brian Koenings



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 5

---

## PURPOSE OF TESTING:

Forty-three types of integrally colored concrete masonry units (CMU's): twenty-four with a split-face and a smooth-face side, four with a split-face side, ten with a smooth-face side, and five with a ground-face side, each with large, small and fine aggregate were submitted for testing using PROSOCO, Inc.'s new construction cleaning products, water repellent products, and graffiti control products.

**A. Cleaning Concrete Masonry Units:** Sure Klean<sup>®</sup> Custom Masonry Cleaner and Sure Klean<sup>®</sup> Burnished Custom Masonry Cleaner were evaluated for removal of laboratory applied mortar.

To simulate new construction soiling, all concrete masonry units (CMU's) are placed on a bench with finished surface facing upward. Hollow cylinders measuring 50 mm in diameter and 75 mm tall are positioned on top of each CMU and filled with a wet mixture of Type S mortar. The wet, mortar-filled cylinder is allowed to remain in contact with the CMU for 10 minutes before removal.

Heavy deposits of mortar are removed with dry scraping after 24 hours. Prepared cleaning solutions are then evaluated for their effectiveness in removing residual Type S mortar staining after 3 days, 7 days, and 14 days of curing.

**B. Color Uniformity Testing\*** - Sure Klean<sup>®</sup> Custom Masonry Cleaner and Sure Klean<sup>®</sup> Burnished Custom Masonry Cleaner were evaluated at various dilutions to determine the optimal concentration of cleaner that leaves the external surface looking most like the natural through-body color of the CMU. Color uniformity was evaluated by comparing aggregate exposure and surface pigment alternation/removal of each cleaned surface compared to the natural through-body color of the CMU.

Aggregate Exposure is the visual examination comparing aggregate exposure of the interior, through-body section of CMU to surfaces cleaned with selected product(s) at given dilutions.

Surface Pigment Alteration/Removal\* is the visual examination comparing the pigmentation of the interior, through-body section of the CMU to surfaces cleaned with selected product(s) at given dilutions.

The following is the scale used for reporting results of both categories:

0 – <b>Worst</b> match to through-body	3 – <b>Good</b> match to through-body
1 – <b>Poor</b> match to through-body	4 – <b>Best</b> match to through-body
2 – <b>Fair</b> match to through-body	

## NOTE: When cleaning integrally colored CMU.

Integrally colored concrete masonry units (CMU's) frequently have high amounts of pigments concentrated on the surface of the cured concrete unit. Variation of surface pigment concentrations from one CMU to the next creates a blotchy appearance in the completed wall. Allowed to remain on the surface of the CMU, the weakly bound pigment will weather and streak, further detracting from the appearance of the completed CMU wall.

In addition to removing excess mortar and construction related soiling, the goal of any cleaning operation undertaken on an integrally colored CMU should include removal of unnaturally high concentrations of surface pigment. By revealing the natural through-body color on the integrally colored unit, the overall color uniformity and weathering resistance of the completed CMU wall is improved.

**C. Protective Water Repellents** – Sure Klean<sup>®</sup> Custom Masonry Sealer and Sure Klean<sup>®</sup> Weather Seal Siloxane WB Concentrate were evaluated for their ability to provide water repellency to the submitted samples.

**D. Graffiti Control** – Sure Klean<sup>®</sup> Custom Masonry Sealer was evaluated for its ability to control graffiti on the submitted samples. Sure Klean<sup>®</sup> Fast Acting Stripper and Defacer Eraser<sup>®</sup> Graffiti Wipe were evaluated for their ability to remove graffiti from the submitted samples.



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 6**

## PRODUCTS EVALUATED FOR CLEANING AND COLOR UNIFORMITY

Block Type	Product	Dilution
All Submitted Split-face and Smooth-face CMU's	Sure Klean® Custom Masonry Cleaner	1:2, 1:4, 1:6
	Sure Klean® Burnished Custom Masonry Cleaner	1:2, 1:3
All Submitted Ground-face CMU's	Sure Klean® Burnished Custom Masonry Cleaner	1:2, 1:3

## WATER REPELLENT PRODUCTS EVALUATED

Block Type	Product	Dilution
All Submitted CMU's	Sure Klean® Custom Masonry Sealer	Concentrate
	Sure Klean® Weather Seal Siloxane WB Concentrate	1:9, 1:14

## GRAFFITI CONTROL PRODUCTS EVALUATED

Block Type	Product	Dilution
All Submitted CMU's	Sure Klean® Custom Masonry Sealer	Concentrate

## GRAFFITI REMOVAL PRODUCTS EVALUATED

Block Type	Product	Dilution
All Submitted CMU's	Sure Klean® Fast Acting Stripper	Concentrate
	Defacer Eraser® Graffiti Wipe	Concentrate



# PALLET TAG PROGRAM LABORATORY REPORT



## SECTION A – CLEANING INTEGRALLY COLORED CMU's

### DESCRIPTION OF PRODUCTS EVALUATED

These cleaning trials were conducted to determine the optimal cleaning/cure time combination.

**Sure Klean® Custom Masonry Cleaner** – A general purpose, concentrated acidic cleaner for most custom masonry and colored concrete. Removes concrete splashes, excess mortar, mud, heavy efflorescence and surface soiling, leaving the masonry clean and uniform with no acid burning or streaking. Liquid concentrate for dilution with 2-6 parts water. Apply by brush or low-pressure spray.

**Sure Klean® Burnished Custom Masonry Cleaner** – Removes common construction and atmospheric staining from custom masonry and other architectural concrete surfaces. This general-purpose, non-etching acidic cleaner removes rust, mud, oil, atmospheric dirt, mortar smears and other stains without altering the surface texture. Burnished Custom Masonry Cleaner adds depth to colors and brightens white matrices and exposed aggregate.

### TEST METHOD – Cleaning

Dilution ratios refer to mixtures of parts concentrated cleaner : parts fresh water. Chemical cleaners were evaluated using the following procedure:

1. Prewet the surface with water.
2. Apply each cleaner at the appropriate dilutions.
3. Allow appropriate dwell time for each cleaner:
  - Custom Masonry Cleaner..... 3 minutes
  - Burnished Custom Masonry Cleaner .....3-5 minutes
4. Reapply the products and moderately agitate with a brush.
5. Pressure rinse thoroughly.\*
6. Allow the surface to dry for at least 18 hours and visually examine.

\* Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 8

## TEST RESULTS – Cleaning


### % Removal of Type S Mortar

<b>“Beldon Brick #25-Blend” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	100%
Burnished Custom Masonry Cleaner	1:3	100%	100%	100%
<b>“Heritage Blend #20-Blend” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	100%
Burnished Custom Masonry Cleaner	1:3	100%	100%	100%
<b>“Lawson Blend #5-Blend” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	100%
Burnished Custom Masonry Cleaner	1:3	100%	100%	100%
<b>“Lawson Blend-Spray” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	95%	95%	95%
Burnished Custom Masonry Cleaner	1:3	90%	90%	90%
<b>“Lockport #16-Blend” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	95%	95%	90%
<b>“Promenade Blend #18-Blend” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	100%
Burnished Custom Masonry Cleaner	1:3	100%	100%	100%





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 9

**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“Promenade Blend-Spray” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	100%
Burnished Custom Masonry Cleaner	1:3	100%	100%	100%
<b>“Sandlewood Blend #6-Blend” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%
<b>“Sandlewood Blend-Spray” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	95%	95%	95%
Burnished Custom Masonry Cleaner	1:3	95%	95%	95%
<b>“Springfield Blend-Spray” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	100%
Burnished Custom Masonry Cleaner	1:3	100%	100%	100%
<b>“Alabaster” Ground-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Burnished Custom Masonry Cleaner	1:2	99%	99%	99%
Burnished Custom Masonry Cleaner	1:3	99%	99%	99%
<b>“Buff” Ground-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Burnished Custom Masonry Cleaner	1:2	100%	99%	99%
Burnished Custom Masonry Cleaner	1:3	100%	99%	99%
<b>“Graphite” Ground-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Burnished Custom Masonry Cleaner	1:2	100%	100%	100%
Burnished Custom Masonry Cleaner	1:3	100%	100%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 10

**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“Limestone” Ground-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Burnished Custom Masonry Cleaner	1:2	100%	99%	99%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%
<b>“Midnight (unsealed)” Ground-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Burnished Custom Masonry Cleaner	1:2	100%	100%	99%
Burnished Custom Masonry Cleaner	1:3	100%	99%	99%
<b>“Canyon Blend” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	95%	95%
Custom Masonry Cleaner	1:4	100%	95%	90%
Custom Masonry Cleaner	1:6	100%	95%	90%
Burnished Custom Masonry Cleaner	1:2	95%	90%	80%
Burnished Custom Masonry Cleaner	1:3	95%	85%	50%
<b>“Desert Blend” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	90%	80%	70%
Burnished Custom Masonry Cleaner	1:3	90%	80%	70%
<b>“Mountain Blend” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	95%	90%
Custom Masonry Cleaner	1:4	100%	90%	90%
Custom Masonry Cleaner	1:6	95%	90%	90%
Burnished Custom Masonry Cleaner	1:2	95%	85%	70%
Burnished Custom Masonry Cleaner	1:3	95%	75%	70%
<b>“Woodland Blend” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	95%	95%	95%
Burnished Custom Masonry Cleaner	1:3	95%	95%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 11

**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“3776” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	95%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	99%	95%
Burnished Custom Masonry Cleaner	1:2	100%	90%	80%
Burnished Custom Masonry Cleaner	1:3	95%	85%	80%
<b>“3776” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	99%
Burnished Custom Masonry Cleaner	1:3	100%	100%	95%
<b>“4660” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	95%
Custom Masonry Cleaner	1:4	100%	95%	95%
Custom Masonry Cleaner	1:6	100%	95%	95%
Burnished Custom Masonry Cleaner	1:2	90%	80%	70%
Burnished Custom Masonry Cleaner	1:3	90%	80%	70%
<b>“4660” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	95%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%
<b>“4916” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	100%	90%
Burnished Custom Masonry Cleaner	1:2	95%	95%	80%
Burnished Custom Masonry Cleaner	1:3	95%	95%	80%
<b>“4916” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	99%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	95%	95%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 12

**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“4970” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	95%	95%
Burnished Custom Masonry Cleaner	1:2	100%	85%	75%
Burnished Custom Masonry Cleaner	1:3	95%	85%	75%
<b>“4970” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	99%
Burnished Custom Masonry Cleaner	1:2	99%	95%	95%
Burnished Custom Masonry Cleaner	1:3	95%	95%	90%
<b>“5558” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	95%	70%	70%
Burnished Custom Masonry Cleaner	1:3	95%	70%	70%
<b>“5558” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	95%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%
<b>“8539” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	90%
<b>“8539” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“8540” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	95%	95%
Custom Masonry Cleaner	1:4	100%	95%	95%
Custom Masonry Cleaner	1:6	100%	95%	90%
Burnished Custom Masonry Cleaner	1:2	95%	80%	70%
Burnished Custom Masonry Cleaner	1:3	95%	80%	70%
<b>“8540” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	99%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%
<b>“#191” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	95%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	95%	95%	90%
Burnished Custom Masonry Cleaner	1:2	95%	80%	80%
Burnished Custom Masonry Cleaner	1:3	95%	80%	80%
<b>“#191” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	95%	90%
Burnished Custom Masonry Cleaner	1:3	100%	95%	90%
<b>“#192” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	100%	95%	85%
Burnished Custom Masonry Cleaner	1:3	100%	95%	85%
<b>“#192” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	99%	99%
Burnished Custom Masonry Cleaner	1:3	100%	99%	99%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 14

**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>"#193" Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	99%
Custom Masonry Cleaner	1:4	100%	99%	99%
Custom Masonry Cleaner	1:6	100%	99%	99%
Burnished Custom Masonry Cleaner	1:2	99%	95%	80%
Burnished Custom Masonry Cleaner	1:3	99%	95%	80%
<b>"#193" Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	99%	99%
Burnished Custom Masonry Cleaner	1:3	100%	99%	99%
<b>"#197" Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	99%	95%
Custom Masonry Cleaner	1:4	100%	99%	95%
Custom Masonry Cleaner	1:6	100%	95%	95%
Burnished Custom Masonry Cleaner	1:2	99%	90%	80%
Burnished Custom Masonry Cleaner	1:3	95%	90%	80%
<b>"#197" Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	99%
Burnished Custom Masonry Cleaner	1:2	100%	100%	99%
Burnished Custom Masonry Cleaner	1:3	100%	99%	95%
<b>"#21" Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	100%	100%	85%
Burnished Custom Masonry Cleaner	1:3	100%	90%	85%
<b>"#21" Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	100%	95%	100%
Burnished Custom Masonry Cleaner	1:3	100%	95%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 15

**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“#33” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	90%
Custom Masonry Cleaner	1:6	100%	100%	90%
Burnished Custom Masonry Cleaner	1:2	95%	80%	80%
Burnished Custom Masonry Cleaner	1:3	95%	80%	80%
<b>“#33” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	90%	90%
Burnished Custom Masonry Cleaner	1:3	90%	90%	90%
<b>“#43” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	90%
Custom Masonry Cleaner	1:6	100%	100%	90%
Burnished Custom Masonry Cleaner	1:2	95%	80%	80%
Burnished Custom Masonry Cleaner	1:3	95%	80%	80%
<b>“#43” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	90%	90%
Burnished Custom Masonry Cleaner	1:3	90%	90%	90%
<b>“#53” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	95%	80%	80%
Burnished Custom Masonry Cleaner	1:3	95%	80%	80%
<b>“#53” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	95%	90%	95%
Burnished Custom Masonry Cleaner	1:3	95%	90%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“A-3” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	95%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	80%	80%
Burnished Custom Masonry Cleaner	1:3	90%	80%	80%
<b>“A-3” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	99%
Burnished Custom Masonry Cleaner	1:2	100%	99%	95%
Burnished Custom Masonry Cleaner	1:3	99%	95%	95%
<b>“A-7” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	99%
Custom Masonry Cleaner	1:4	100%	100%	99%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	95%	90%	80%
Burnished Custom Masonry Cleaner	1:3	95%	90%	80%
<b>“A-7” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%
<b>“Ivory” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	95%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	95%	90%	80%
Burnished Custom Masonry Cleaner	1:3	95%	90%	80%
<b>“Ivory” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	99%	99%
Burnished Custom Masonry Cleaner	1:3	99%	99%	95%





# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“Mohawk Orange” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	95%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	95%	85%	80%
Burnished Custom Masonry Cleaner	1:3	95%	85%	80%
<b>“Mohawk Orange” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	95%	95%	90%
Burnished Custom Masonry Cleaner	1:3	95%	95%	90%
<b>“Natural” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	95%	90%	90%
Burnished Custom Masonry Cleaner	1:3	95%	90%	90%
<b>“Natural” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%
<b>“Rose” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	95%	90%
Custom Masonry Cleaner	1:4	100%	95%	90%
Custom Masonry Cleaner	1:6	100%	95%	90%
Burnished Custom Masonry Cleaner	1:2	95%	80%	70%
Burnished Custom Masonry Cleaner	1:3	95%	80%	70%
<b>“Rose” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	100%	90%	95%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 18

**TEST RESULTS – Cleaning**

**% Removal of Type S Mortar**

<b>“Russet” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	95%	95%	85%
Burnished Custom Masonry Cleaner	1:3	95%	90%	85%
<b>“Russet” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	100%	100%
Burnished Custom Masonry Cleaner	1:3	100%	100%	100%
<b>“Std. White” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	99%
Custom Masonry Cleaner	1:6	100%	100%	95%
Burnished Custom Masonry Cleaner	1:2	95%	85%	85%
Burnished Custom Masonry Cleaner	1:3	95%	85%	85%
<b>“Std. White” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	99%	99%	99%
Custom Masonry Cleaner	1:4	99%	99%	99%
Custom Masonry Cleaner	1:6	99%	99%	99%
Burnished Custom Masonry Cleaner	1:2	99%	95%	90%
Burnished Custom Masonry Cleaner	1:3	99%	95%	90%
<b>“White” Split-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	90%
Burnished Custom Masonry Cleaner	1:2	100%	90%	85%
Burnished Custom Masonry Cleaner	1:3	100%	90%	85%
<b>“White” Smooth-face CMU</b>				
<b>Product</b>	<b>Dilution</b>	<b>3 day</b>	<b>7 day</b>	<b>14 day</b>
Custom Masonry Cleaner	1:2	100%	100%	100%
Custom Masonry Cleaner	1:4	100%	100%	100%
Custom Masonry Cleaner	1:6	100%	100%	100%
Burnished Custom Masonry Cleaner	1:2	100%	95%	95%
Burnished Custom Masonry Cleaner	1:3	100%	95%	95%



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 19

## PHOTOGRAPHS- Cleaning

"Rose" Split-face CMU; 3 Day Cleaning

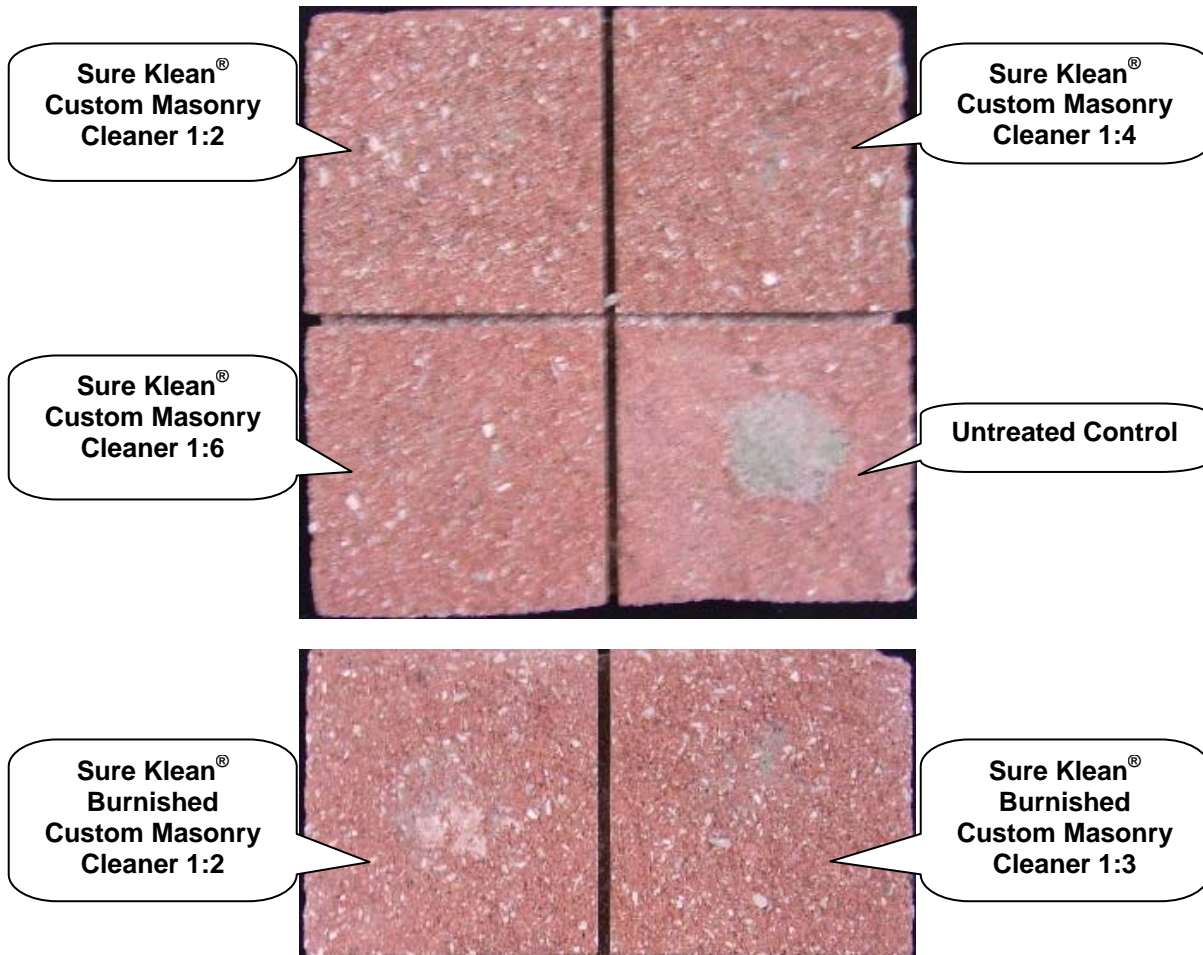



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 20


## PHOTOGRAPHS- Cleaning

"Rose" Smooth-face CMU; 3 Day Cleaning

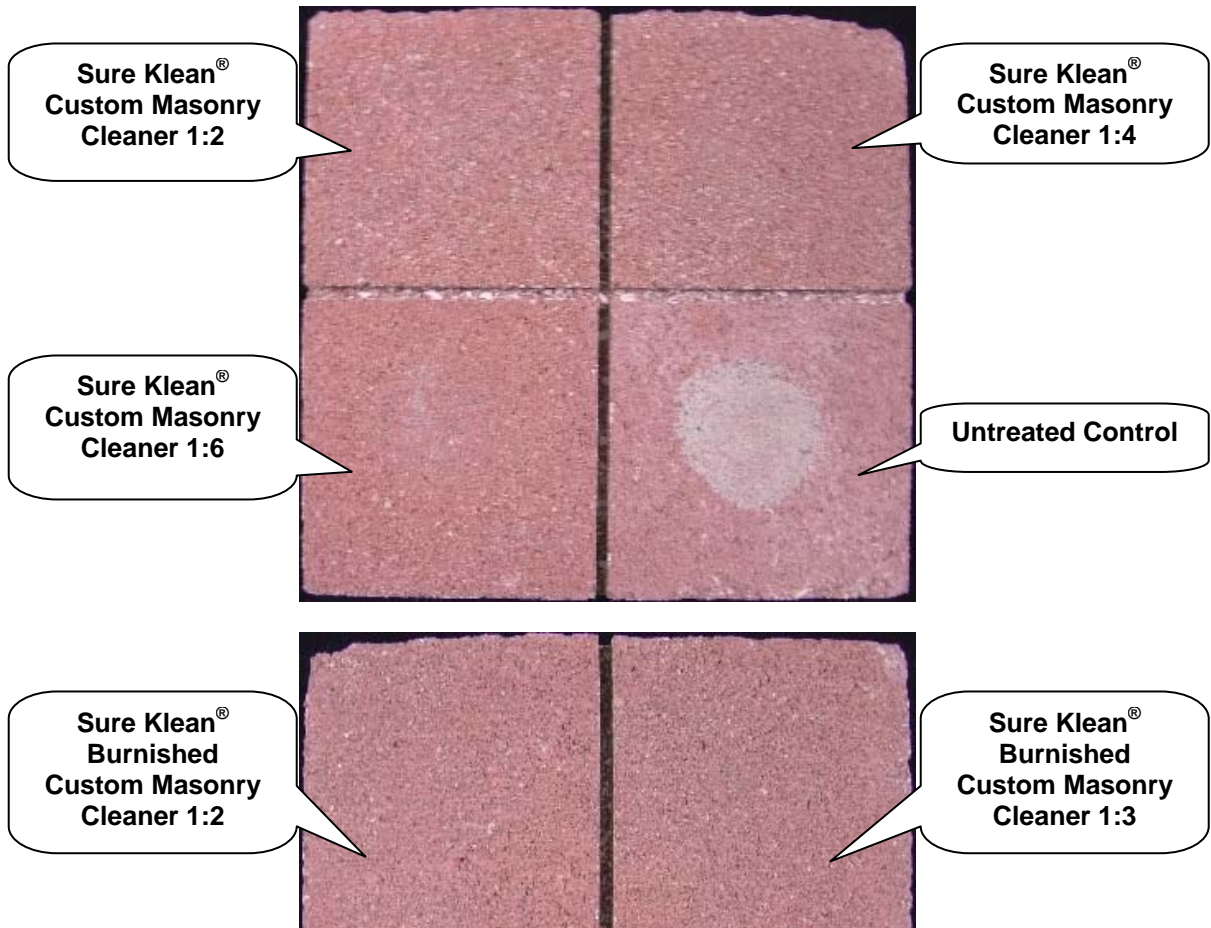



# PALLET TAG PROGRAM LABORATORY REPORT



PHOTOGRAPHS- Cleaning


“Springfield Blend-Spray” Smooth-face CMU; 3 Day Cleaning



Sure Klean<sup>®</sup>  
Custom Masonry  
Cleaner 1:2

Sure Klean<sup>®</sup>  
Custom Masonry  
Cleaner 1:4

Sure Klean<sup>®</sup>  
Custom Masonry  
Cleaner 1:6

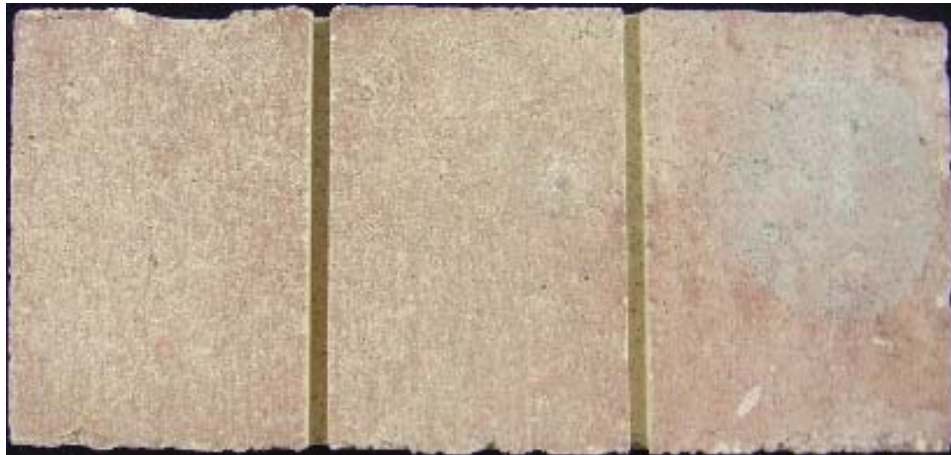

Sure Klean<sup>®</sup>  
Burnished  
Custom Masonry  
Cleaner 1:2

Sure Klean<sup>®</sup>  
Burnished  
Custom Masonry  
Cleaner 1:3

Untreated Control



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 22**

---

**PHOTOGRAPHS- Cleaning**

**“Buff” Ground-face CMU; 3 Day Cleaning**



**Sure Klean® Burnished  
Custom Masonry Cleaner 1:2**

**Sure Klean® Burnished Custom  
Masonry Cleaner 1:3**





# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 23


## PHOTOGRAPHS- Cleaning

"Rose" Split-face CMU; 7 Day Cleaning

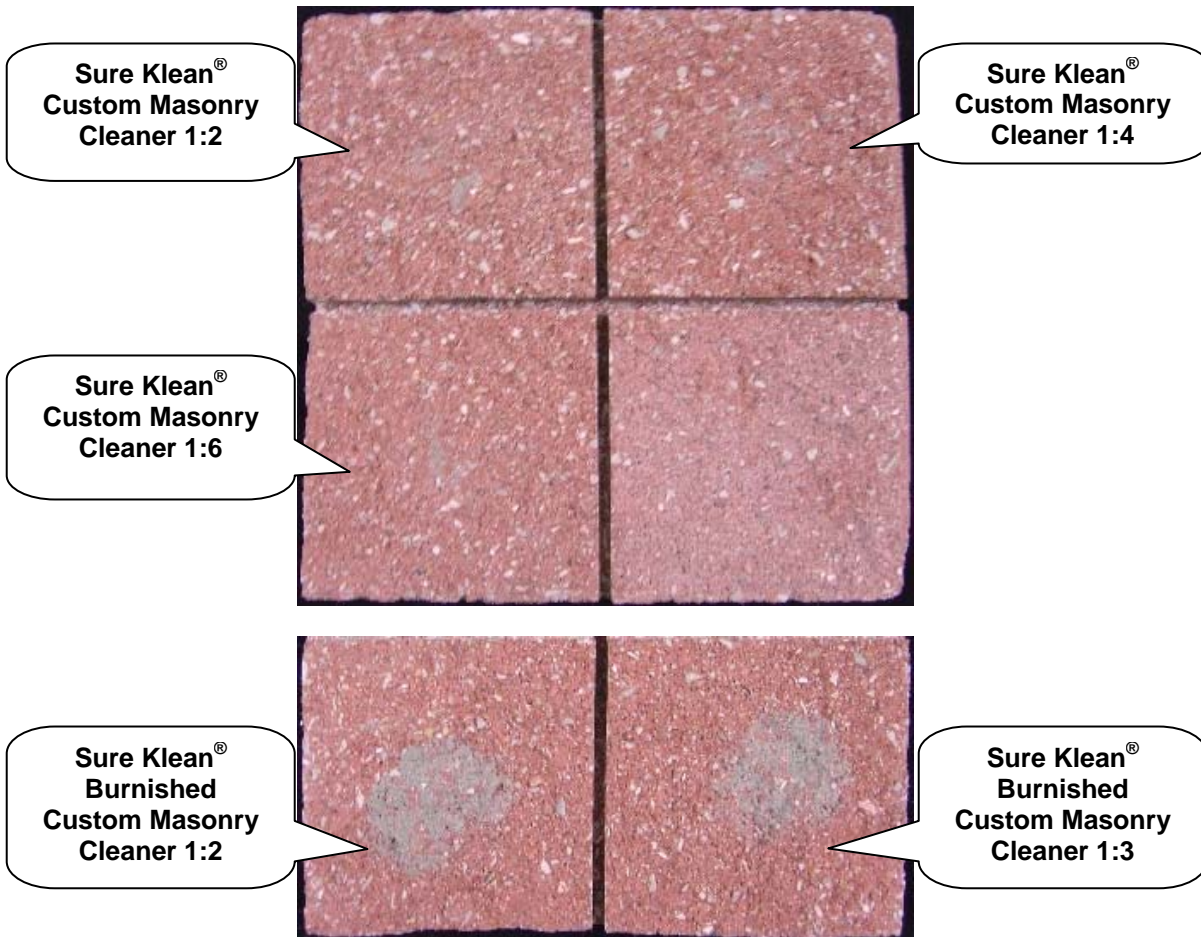



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 24

## PHOTOGRAPHS- Cleaning

"Rose" Smooth-face CMU; 7 Day Cleaning

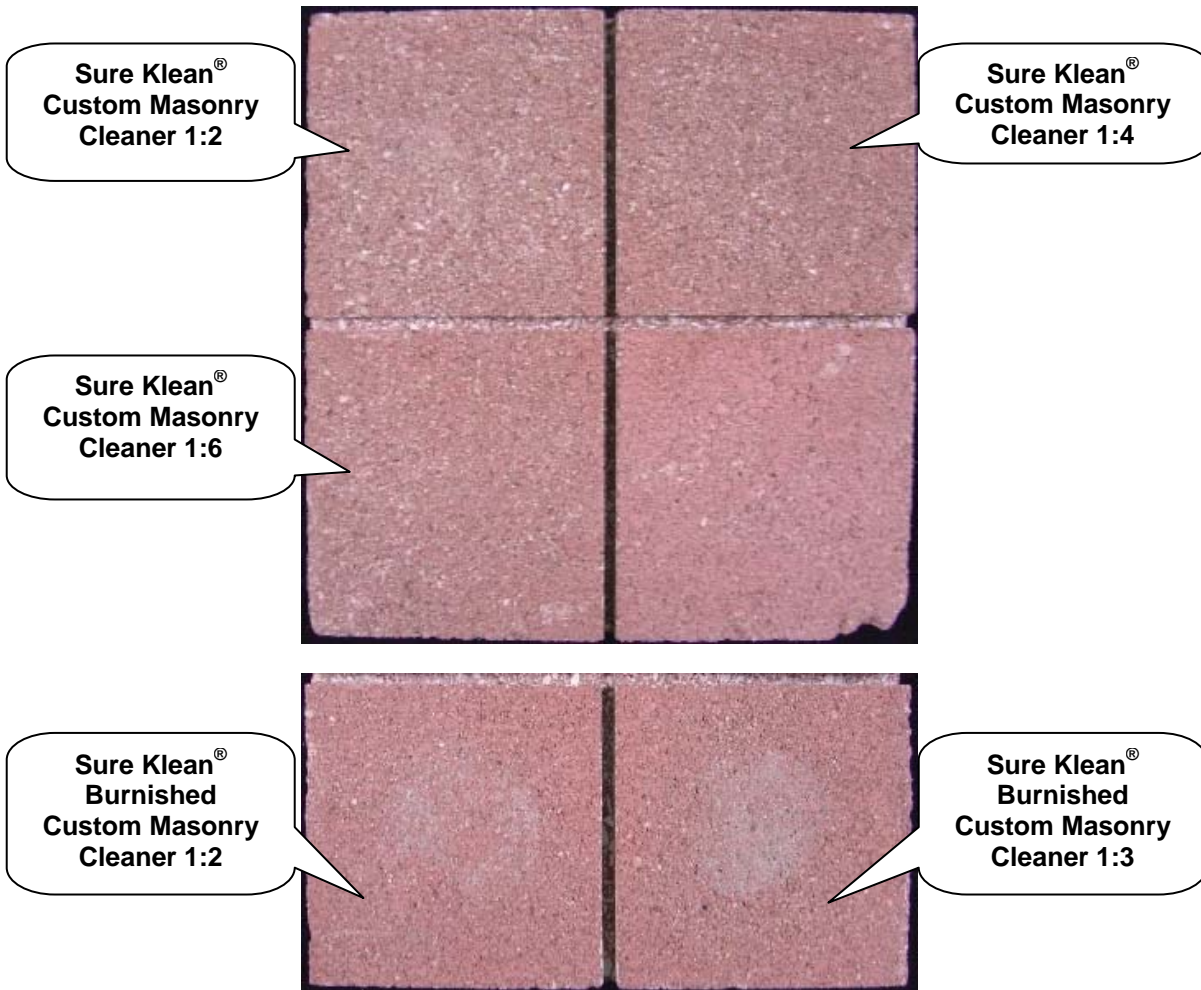





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 25

---

## PHOTOGRAPHS- Cleaning

**“Springfield Blend-Spray” Smooth-face CMU; 7 Day Cleaning**



**Sure Klean®  
Custom Masonry  
Cleaner 1:2**

**Sure Klean®  
Custom Masonry  
Cleaner 1:4**

**Sure Klean®  
Custom Masonry  
Cleaner 1:6**



**Sure Klean®  
Burnished  
Custom Masonry  
Cleaner 1:2**

**Sure Klean®  
Burnished  
Custom Masonry  
Cleaner 1:3**



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 26**

---

## PHOTOGRAPHS- Cleaning

**“Buff” Ground-face CMU; 7 Day Cleaning**



**Sure Klean® Burnished  
Custom Masonry Cleaner 1:2**

**Sure Klean® Burnished Custom  
Masonry Cleaner 1:3**



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 27

## PHOTOGRAPHS- Cleaning

“Rose” Split-face CMU; 14 Day Cleaning

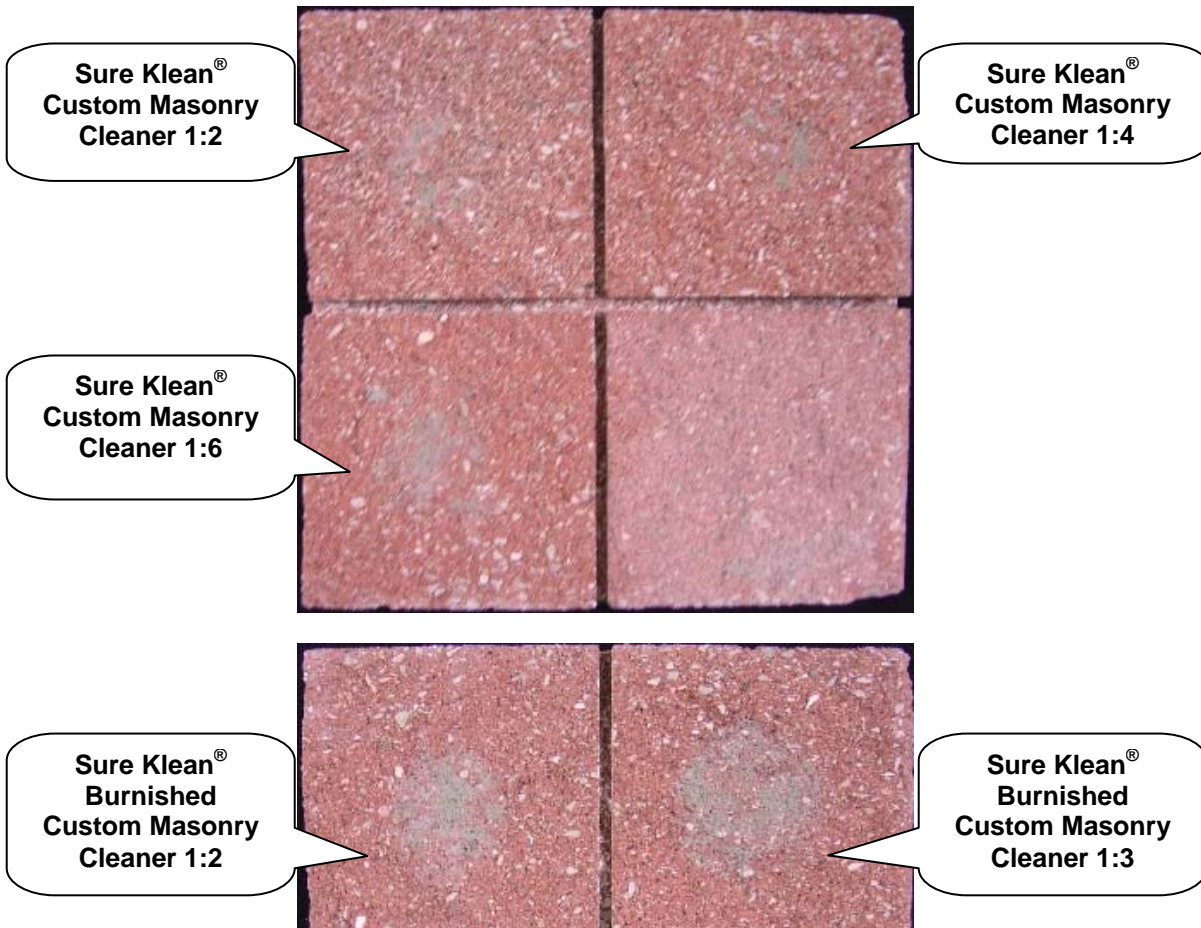



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 28

## PHOTOGRAPHS- Cleaning

"Rose" Smooth-face CMU; 14 Day Cleaning

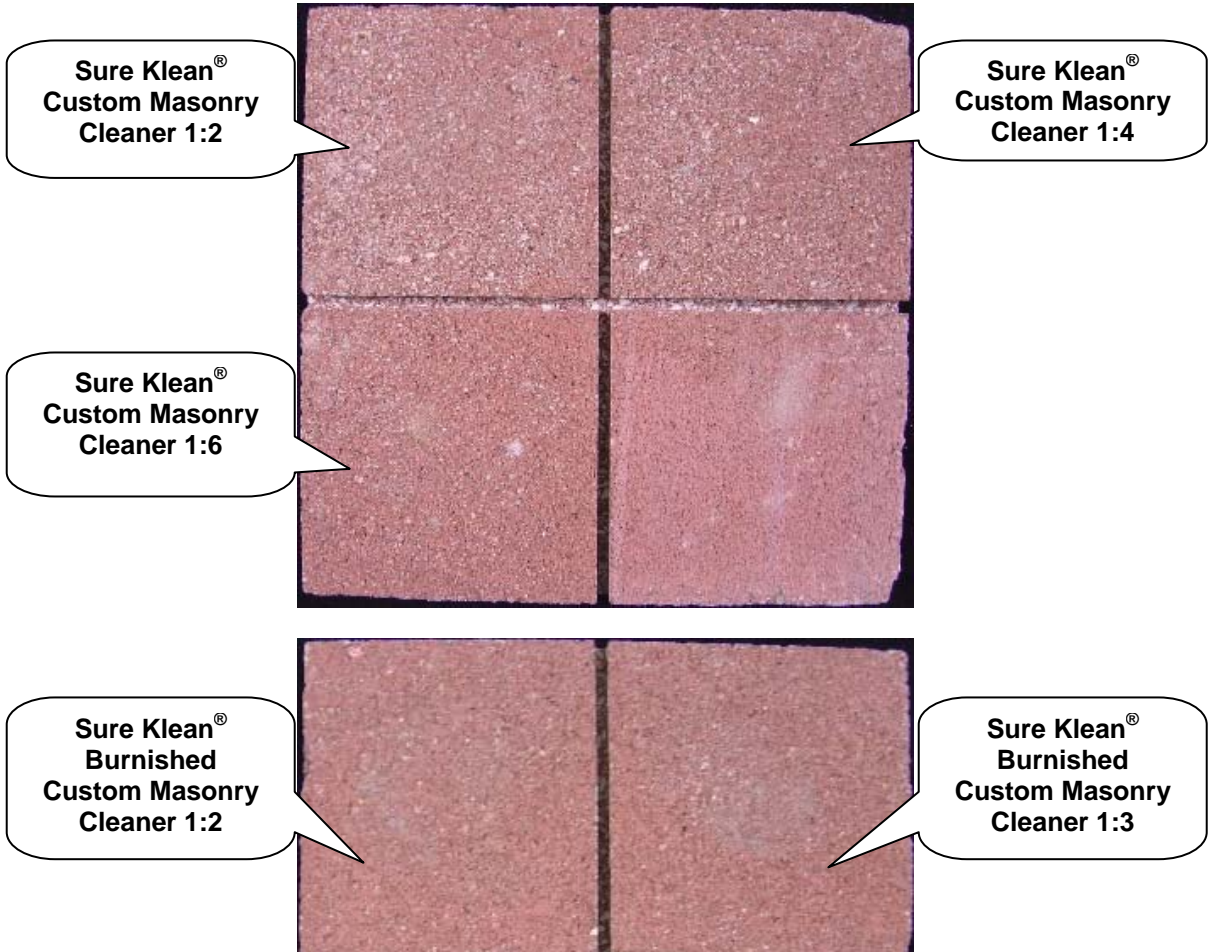



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 29

---

## PHOTOGRAPHS- Cleaning


“Springfield Blend-Spray” Smooth-face CMU; 14 Day Cleaning



**Sure Klean<sup>®</sup>  
Custom Masonry  
Cleaner 1:2**

**Sure Klean<sup>®</sup>  
Custom Masonry  
Cleaner 1:4**

**Sure Klean<sup>®</sup>  
Custom Masonry  
Cleaner 1:6**

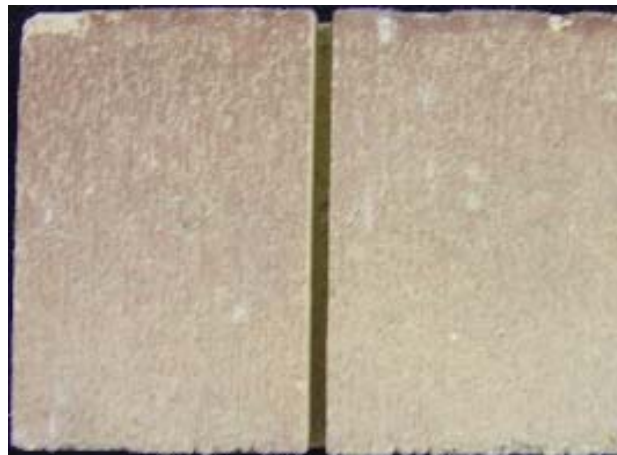

**Sure Klean<sup>®</sup>  
Burnished  
Custom Masonry  
Cleaner 1:2**

**Sure Klean<sup>®</sup>  
Burnished  
Custom Masonry  
Cleaner 1:3**





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 30**

---

## PHOTOGRAPHS- Cleaning

**“Buff” Ground-face CMU; 14 Day Cleaning**



**Sure Klean® Burnished  
Custom Masonry Cleaner 1:2**

**Sure Klean® Burnished Custom  
Masonry Cleaner 1:3**



# PALLET TAG PROGRAM LABORATORY REPORT



## CONCLUSIONS – Cleaning

Based on the test data, all of the submitted block samples were efficiently cleaned with a dilution of the selected PROSOCO Inc. cleaning product. Use higher concentrations and surface agitation to maximize aggregate exposure. Use low concentration and surface agitation to minimize aggregate exposure.

All dilutions of Sure Klean® Custom Masonry Cleaner and Sure Klean® Burnished Custom Masonry Cleaner tested affected most of the samples in a similar manner; removing slight to heavy concentrations of pigmented matrix from the CMU's, exposing small and large aggregate, and enhancing the natural appearance of the integrally colored concrete masonry unit.

**NOTE:** The following integrally colored CMU's exhibit a high concentration of pigment on the outer surface of the block: "Lawson Blend-Spray," "Promenade Blend-Spray," "Sandlewood Blend-Spray," and "Springfield Blend-Spray." All cleaning products and cleaning methods evaluated removed much of this surface pigment revealing the natural color of the underlying aggregate and integrally colored cement paste. Altering the original appearance of these "Blend Spray" units in this way was deemed undesirable.

To reduce the potential for altering the original appearance of these "Blend-Spray" units, precautions should be taken during construction to minimize accumulation of excess mortar and construction soiling on the exposed surface. Remove soiling that does accumulate on the exposed surface promptly using fresh water and gentle agitation with a soft bristled brush. Conduct all post construction cleaning in a controlled way that minimizes removal of the surface pigment.

## RECOMMENDED PRODUCTS AND DILUTIONS – CLEANING

Recommendations for cleaning for each type of CMU submitted by Northfield Block Company, Mundelein, IL, are provided in the chart below. Recommendations are based on the optimum dilution for complete removal of mortar.

Sample	New Construction Cleaning (Type S mortar, 14 day)
All Submitted Split-face CMU's	Sure Klean® Custom Masonry Cleaner (1:2) OR (1:4) OR (1:6)
All Submitted Smooth-face CMU's	Sure Klean® Custom Masonry Cleaner (1:2) OR (1:4) OR (1:6) OR Sure Klean® Burnished Custom Masonry Cleaner (1:2) OR (1:3)
All Submitted Ground-face CMU's	Sure Klean® Burnished Custom Masonry Cleaner (1:2) OR (1:3)
All Submitted "Blend-Spray" Smooth-face CMU's	No Recommendation (see note in Conclusions above)

The most appropriate cleaner and dilution should be determined on the specific job-site, and will be dependent primarily on the nature and severity of soiling present at that location. Pressure rinsing equipment providing at least 400 psi at 4-6 gpm delivered through a 15-40 degree fan spray often produces best cleaning results. Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate cleaning product and procedures for a particular project. See product literature for additional application and product information.



# PALLET TAG PROGRAM LABORATORY REPORT



**SECTION B – COLOR UNIFORMITY:**

**DESCRIPTION OF PRODUCTS EVALUATED – Color Uniformity:**

**Sure Klean® Custom Masonry Cleaner** – A general purpose, concentrated acidic cleaner for most custom masonry and colored concrete. Removes concrete splashes, excess mortar, mud, heavy efflorescence and surface soiling, leaving the masonry clean and uniform with no acid burning or streaking. Liquid concentrate for dilution with 2-6 parts water. Apply by brush or low-pressure spray.

**Sure Klean® Burnished Custom Masonry Cleaner** – Removes common construction and atmospheric staining from custom masonry and other architectural concrete surfaces. This general-purpose, non-etching acidic cleaner removes rust, mud, oil, atmospheric dirt, mortar smears and other stains without altering the surface texture. Burnished Custom Masonry Cleaner adds depth to colors and brightens white matrices and exposed aggregate.

**TEST METHOD – Color Uniformity Testing:**

Dilution ratios refer to mixtures of parts concentrated cleaner: parts fresh water. Chemical cleaners were evaluated using the following procedure:


1. Prewet the surface with water.
2. Apply each cleaner at the appropriate dilutions.
3. Allow appropriate dwell time, as specified.
  - Custom Masonry Cleaner..... 3 minutes
  - Burnished Custom Masonry Cleaner .....3-5 minutes
4. Reapply the products and moderately agitate with a brush.
5. Pressure rinse thoroughly.\*
6. Allow the sample to dry for at least 18 hours and visually examine.
7. Break the sample in half and compare the through-body surfaces to the cleaned surfaces for the best match.

\*Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.





# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Beldon Brick #25-Blend"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Heritage Blend #20-Blend"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Lawson Blend #5-Blend"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Lawson Blend-Spray" *	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	0
Custom Masonry Cleaner	1:4	4	0
Custom Masonry Cleaner	1:6	4	0
Burnished Custom Masonry Cleaner	1:2	3	1
Burnished Custom Masonry Cleaner	1:3	3	2
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Lockport #16-Blend"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body


1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**


<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Promenade Blend #18-Blend"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Promenade Blend-Spray" *	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	0
Custom Masonry Cleaner	1:4	4	0
Custom Masonry Cleaner	1:6	4	0
Burnished Custom Masonry Cleaner	1:2	3	1
Burnished Custom Masonry Cleaner	1:3	3	2
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Sandlewood Blend #6-Blend"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Sandlewood Blend-Spray" *	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	0
Custom Masonry Cleaner	1:4	4	0
Custom Masonry Cleaner	1:6	4	0
Burnished Custom Masonry Cleaner	1:2	3	1
Burnished Custom Masonry Cleaner	1:3	3	2
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Springfield Blend-Spray" *	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	0
Custom Masonry Cleaner	1:4	4	0
Custom Masonry Cleaner	1:6	4	0
Burnished Custom Masonry Cleaner	1:2	3	1
Burnished Custom Masonry Cleaner	1:3	3	2

Scale used for reporting results of both categories

- |  |                                       |
|--|---------------------------------------|
| 0 – <b>Worst</b> match to through-body | 3 – <b>Good</b> match to through-body |
| 1 – <b>Poor</b> match to through-body  | 4 – <b>Best</b> match to through-body |
| 2 – <b>Fair</b> match to through-body  |                                       |



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Ground-face CMU		<b>Pigment Color:</b> "Alabaster"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Burnished Custom Masonry Cleaner	1:2	4	4
Burnished Custom Masonry Cleaner	1:3	4	4
<b>Substrate:</b> Ground-face CMU		<b>Pigment Color:</b> "Buff"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Burnished Custom Masonry Cleaner	1:2	4	4
Burnished Custom Masonry Cleaner	1:3	4	4
<b>Substrate:</b> Ground-face CMU		<b>Pigment Color:</b> "Graphite"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Burnished Custom Masonry Cleaner	1:2	4	4
Burnished Custom Masonry Cleaner	1:3	4	4
<b>Substrate:</b> Ground-face CMU		<b>Pigment Color:</b> "Limestone"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Burnished Custom Masonry Cleaner	1:2	4	4
Burnished Custom Masonry Cleaner	1:3	4	4
<b>Substrate:</b> Ground-face CMU		<b>Pigment Color:</b> "Midnight (unsealed)"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Burnished Custom Masonry Cleaner	1:2	4	4
Burnished Custom Masonry Cleaner	1:3	4	4
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "Canyon Blend"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "Desert Blend"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

- |  |                                       |
|--|---------------------------------------|
| 0 – <b>Worst</b> match to through-body | 3 – <b>Good</b> match to through-body |
| 1 – <b>Poor</b> match to through-body  | 4 – <b>Best</b> match to through-body |
| 2 – <b>Fair</b> match to through-body  |                                       |



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "3776"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "3776"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "4660"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "4660"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "4916"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body


1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "4916"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "4970"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "4970"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "5558"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "5558"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body

1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "8539"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "8539"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "8540"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "8540"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "#191"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body


1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "#191"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "#192"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "#192"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "#193"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "#193"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body

1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> “#197”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> “#197”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> “#21”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> “#21”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> “#33”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body

1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body





# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> “#33”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> “#43”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> “#43”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> “#53”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> “#53”	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body


1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "A-3"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "A-3"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "A-7"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "A-7"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "Ivory"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body

1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**


<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Ivory"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "Mohawk Orange"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Mohawk Orange"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "Natural"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Natural"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

- |  |                                       |
|--|---------------------------------------|
| 0 – <b>Worst</b> match to through-body | 3 – <b>Good</b> match to through-body |
| 1 – <b>Poor</b> match to through-body  | 4 – <b>Best</b> match to through-body |
| 2 – <b>Fair</b> match to through-body  |                                       |



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Color Uniformity**

<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "Rose"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Rose"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "Russet"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Smooth-face CMU		<b>Pigment Color:</b> "Russet"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate:</b> Split-face CMU		<b>Pigment Color:</b> "Std. White"	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

0 – **Worst** match to through-body

3 – **Good** match to through-body

1 – **Poor** match to through-body

4 – **Best** match to through-body

2 – **Fair** match to through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 45**

**TEST RESULTS – Color Uniformity**


<b>Substrate: Smooth-face CMU</b>		<b>Pigment Color: "Std. White"</b>	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate: Split-face CMU</b>		<b>Pigment Color: "White"</b>	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3
<b>Substrate: Smooth-face CMU</b>		<b>Pigment Color: "White"</b>	
Product	Dilution	Aggregate Exposure	Surface Pigment Alteration/Removal
Custom Masonry Cleaner	1:2	4	4
Custom Masonry Cleaner	1:4	4	4
Custom Masonry Cleaner	1:6	4	4
Burnished Custom Masonry Cleaner	1:2	3	3
Burnished Custom Masonry Cleaner	1:3	3	3

Scale used for reporting results of both categories

- |  |                                       |
|--|---------------------------------------|
| 0 – <b>Worst</b> match to through-body | 3 – <b>Good</b> match to through-body |
| 1 – <b>Poor</b> match to through-body  | 4 – <b>Best</b> match to through-body |
| 2 – <b>Fair</b> match to through-body  |                                       |



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 46

## PHOTOGRAPHS – Color Uniformity

“Rose” Split-face CMU; Through-body

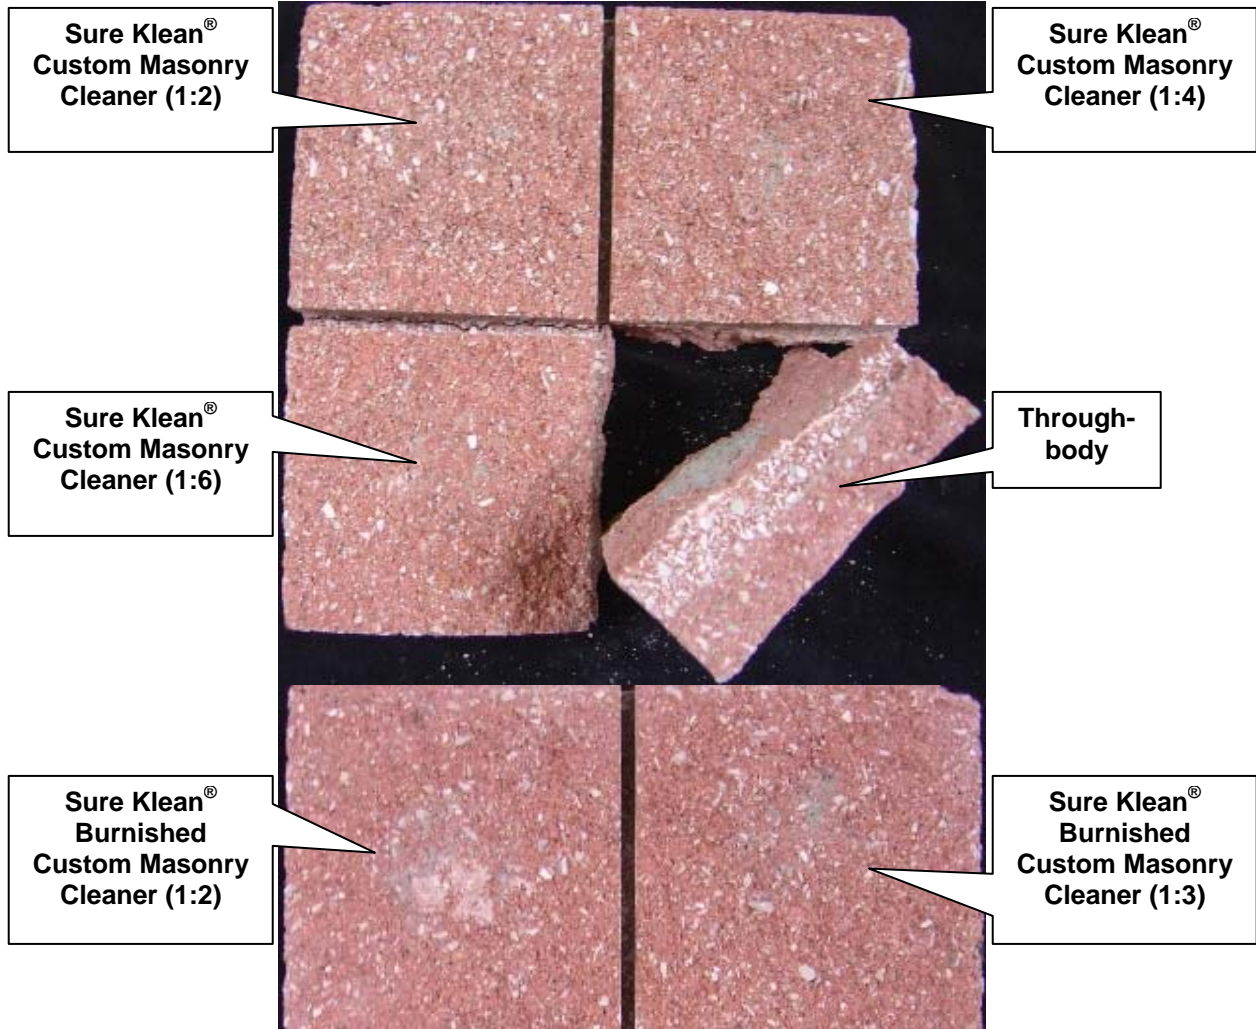



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 47

## PHOTOGRAPHS – Color Uniformity

“Rose” Smooth-face CMU; Through-body

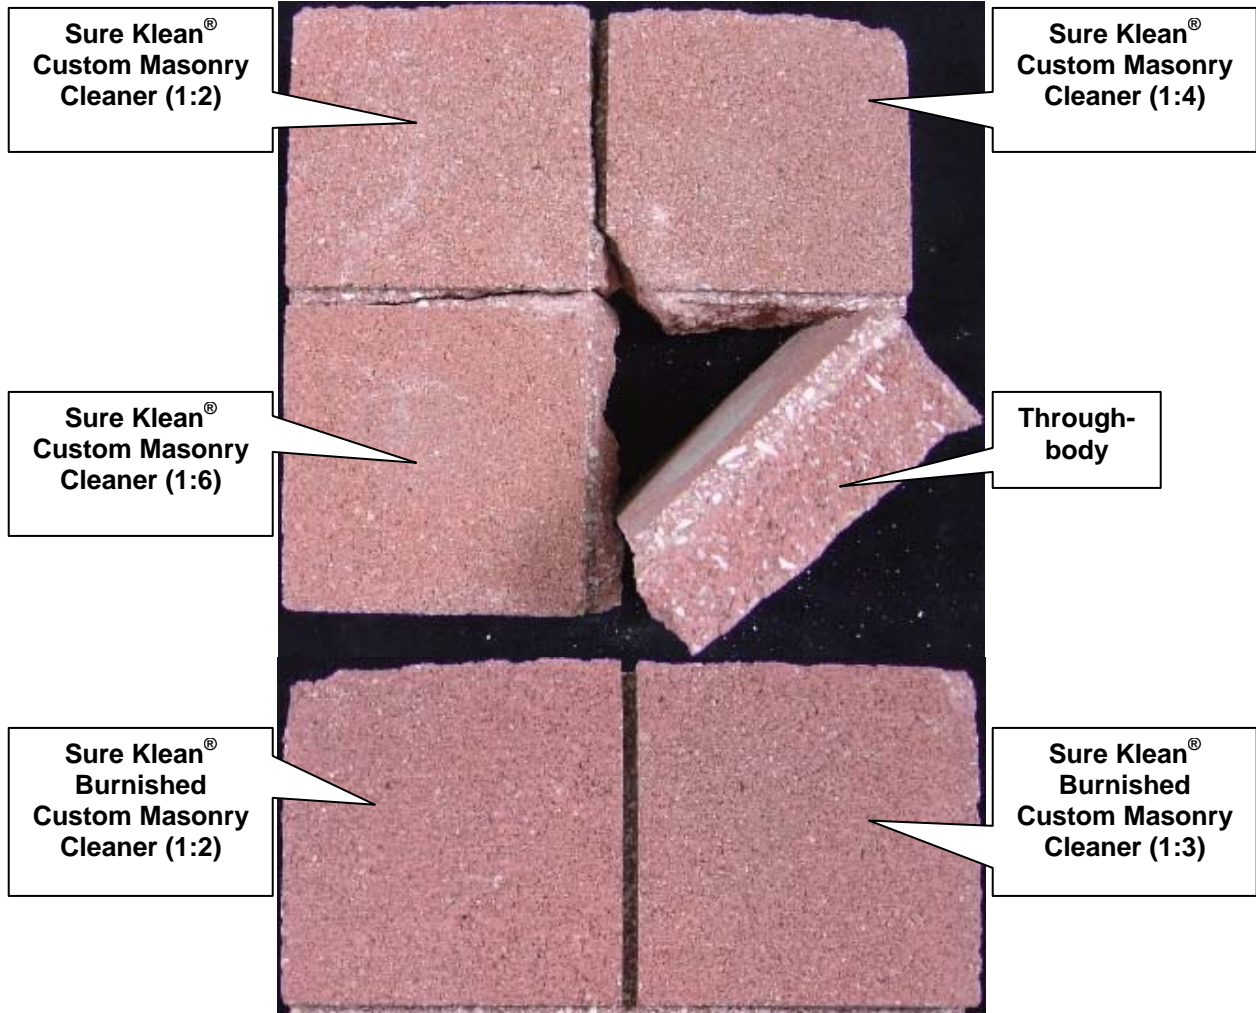





# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 48

---

## PHOTOGRAPHS – Color Uniformity


### “Springfield Blend-Spray” Smooth-face CMU



**Sure Klean®  
Custom Masonry  
Cleaner (1:2)**

**Sure Klean®  
Custom Masonry  
Cleaner (1:4)**

**Sure Klean®  
Custom Masonry  
Cleaner (1:6)**

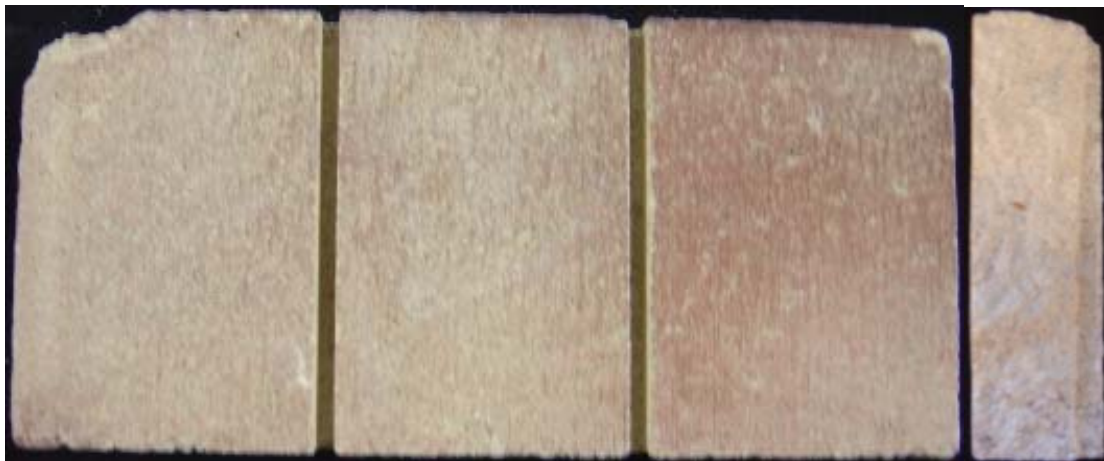

**Sure Klean®  
Burnished Custom  
Masonry Cleaner  
(1:2)**

**Sure Klean®  
Burnished Custom  
Masonry Cleaner  
(1:3)**

**Untreated  
Control**

**Through-  
body**





# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 49

---

## PHOTOGRAPHS – Color Uniformity

“Buff” Ground-face CMU; Through-body

Sure Klean® Burnished  
Custom Masonry Cleaner (1:2)

Sure Klean® Burnished  
Custom Masonry Cleaner (1:3)



Through-body



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 50**

---

## CONCLUSIONS: COLOR UNIFORMITY:

Most dilutions of Sure Klean® Custom Masonry Cleaner and Sure Klean® Burnished Custom Masonry Cleaner tested affected most of the substrates in a similar manner. Higher concentrations of cleaner removed moderate to heavy concentrations of pigmented matrix, exposing small and large aggregate. Lower concentrations of cleaner removed slight to moderate concentrations of pigmented matrix, exposing small and large aggregate. All dilutions enhanced the natural appearance of the integrally colored CMU's.

**NOTE:** The following integrally colored CMU's exhibit a high concentration of pigment on the outer surface of the block: "Lawson Blend-Spray," "Promenade Blend-Spray," "Sandlewood Blend-Spray," and "Springfield Blend-Spray." All cleaning products and cleaning methods evaluated removed much of this surface pigment revealing the natural color of the underlying aggregate and integrally colored cement paste. Altering the original appearance of these "Blend Spray" units in this way was deemed undesirable.

To reduce the potential for altering the original appearance of these "Blend-Spray" units, precautions should be taken during construction to minimize accumulation of excess mortar and construction soiling on the exposed surface. Remove soiling that does accumulate on the exposed surface promptly using fresh water and gentle agitation with a soft bristled brush. Conduct all post construction cleaning in a controlled way that minimizes removal of the surface pigment.

---

## RECOMMENDATIONS – COLOR UNIFORMITY

Recommendations for color uniformity for each type of CMU submitted by Northfield Block Company, Mundelein, IL, are provided in the chart below. Recommendations are based on the optimum dilution that provides the best color uniformity.

Sample	Color Uniformity
All Submitted Split-face CMU's	Sure Klean® Custom Masonry Cleaner (1:2) OR (1:4) OR (1:6)
All Submitted Smooth-face CMU's	Sure Klean® Custom Masonry Cleaner (1:2) OR (1:4) OR (1:6) OR Sure Klean® Burnished Custom Masonry Cleaner (1:2) OR (1:3)
All Submitted Ground-face CMU's	Sure Klean® Burnished Custom Masonry Cleaner (1:2) OR (1:3)
All Submitted "Blend-Spray" Smooth-face CMU's	No Recommendation (see note in Conclusions above)

The most appropriate cleaner and dilution should be determined on the specific job-site, and will be dependent primarily on the nature and severity of soiling present at that location. Pressure rinsing equipment providing at least 400 psi at 4-6 gpm delivered through a 15-40 degree fan spray often produces best cleaning results. Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate cleaning product and procedures for a particular project. See product literature for additional application and product information.



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 51

---

## SECTION C – PROTECTIVE WATER REPELLENTS:

The testing described below evaluates the suitability of water repellent treatments.

The surface treatments evaluated were selected for their suitability for application based on the following selection criteria:

1. Weatherproofing properties
2. Color change
3. Ease of application

---

## DESCRIPTIONS OF PRODUCTS EVALUATED – Protective Water Repellents:

**Sure Klean® Custom Masonry Sealer** – A clear, solvent-based silicone elastomer formulated to weatherproof custom masonry units, cast stone, architectural concrete block, pre-cast concrete, wood and porous masonry. Custom Masonry Sealer penetrates and fills pores to prevent water penetration through exterior walls exposed to normal weathering.

**Sure Klean® Weather Seal Siloxane WB Concentrate** – A concentrated water repellent designed for dilution with fresh water at the jobsite. This solvent-free blend of siloxanes and oligomeric alkoxy siloxanes mixes easily with water to produce a penetrating water repellent ideal for application to dense or porous masonry surfaces. An effective alternative to conventional solvent-based silanes or siloxanes, Siloxane WB penetrates and chemically bonds deep within the masonry substrate to provide long-lasting protection against water-related staining or deterioration. Will not darken, produce a surface film or impair the natural breathing characteristics of treated surfaces.

---

## SAMPLE PREPARATION – Protective Water Repellents:

The submitted blocks were scored, allowed to dry, and to reabsorb atmospheric humidity for 24 hours prior to treatment. The treatment method consisted of a wet-on-wet brush application. All treatments were allowed to cure at least 3 days prior to testing.

---

## TEST METHODS – Protective Water Repellents:

### **Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes**

The water absorption tube test simulating wind driven rain conditions was performed. This test simulates 60 mile per hour wind driven rain conditions for a period of 20 minutes. See Technical Services TECH Note RILEM Tube Test Procedures.



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 52

## TEST RESULTS – Protective Water Repellents:

### Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes

RESULTS	
"Beldon Brick #25-Blend" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Heritage Blend #20-Blend" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Lawson Blend #5-Blend" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Lawson Blend-Spray" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Lockport #16-Blend" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Promenade Blend #18-Blend" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Promenade Blend-Spray" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Sandlewood Blend #6-Blend" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 53

## TEST RESULTS – Protective Water Repellents:

### Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes

	RESULTS
"Sandlewood Blend-Spray" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Springfield Blend-Spray" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Alabaster" Ground-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Buff" Ground-face CMU	
Untreated Control	60 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Graphite" Ground-face CMU	
Untreated Control	60 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Limestone" Ground-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Midnight (unsealed)" Ground-face CMU	
Untreated Control	55 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Canyon Blend" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	59 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 54

## TEST RESULTS – Protective Water Repellents:

### Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes

	RESULTS
"Desert Blend" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Mountain Blend" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Woodland Blend" Split-face CMU	
Untreated Control	48 mph
Custom Masonry Sealer	59 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
"3776" Split-face CMU	
Untreated Control	52 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"3776" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"4660" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"4660" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"4916" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 55**

---

**TEST RESULTS – Protective Water Repellents:**

**Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes**

	<b>RESULTS</b>
"4916" Smooth-face CMU	
Untreated Control	58 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"4970" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
"4970" Smooth-face CMU	
Untreated Control	50 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"5558" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"5558" Smooth-face CMU	
Untreated Control	51 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
"8539" Split-face CMU	
Untreated Control	54 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"8539" Smooth-face CMU	
Untreated Control	58 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"8540" Split-face CMU	
Untreated Control	54 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 56

## TEST RESULTS – Protective Water Repellents:

### Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes

	RESULTS
"8540" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#191" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#191" Smooth-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#192" Split-face CMU	
Untreated Control	52 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#192" Smooth-face CMU	
Untreated Control	58 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#193" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
"#193" Smooth-face CMU	
Untreated Control	49 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#197" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph





# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Protective Water Repellents:**

**Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes**

<b>RESULTS</b>	
"#197" Smooth-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#21" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
"#21" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#33" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#33" Smooth-face CMU	
Untreated Control	57 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
"#43" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#43" Smooth-face CMU	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"#53" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Protective Water Repellents:**

**Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes**

<b>RESULTS</b>	
<b>"#53" Smooth-face CMU</b>	
Untreated Control	58 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
<b>"A-3" Split-face CMU</b>	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
<b>"A-3" Smooth-face CMU</b>	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
<b>"A-7" Split-face CMU</b>	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
<b>"A-7" Smooth-face CMU</b>	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
<b>"Ivory" Split-face CMU</b>	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
<b>"Ivory" Smooth-face CMU</b>	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
<b>"Mohawk Orange" Split-face CMU</b>	
Untreated Control	59 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 59


## TEST RESULTS – Protective Water Repellents:

### Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes

	RESULTS
"Mohawk Orange" Smooth-face CMU	
Untreated Control	60 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Natural" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
"Natural" Smooth-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Rose" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph
"Rose" Smooth-face CMU	
Untreated Control	52 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Russet" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Russet" Smooth-face CMU	
Untreated Control	56 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"Std. White" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	59 mph



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 60**

---

**TEST RESULTS – Protective Water Repellents:**

**Water Absorption Tube Test: RILEM II.4, 60 mph, 20 Minutes**

<b>RESULTS</b>	
"Std. White" Smooth-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"White" Split-face CMU	
Untreated Control	<40 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph
"White" Smooth-face CMU	
Untreated Control	47 mph
Custom Masonry Sealer	60 mph
Siloxane WB 1:9	60 mph
Siloxane WB 1:14	60 mph



# PALLET TAG PROGRAM LABORATORY REPORT




PROSOCO, Inc.

Page 61

## PHOTOGRAPHS- Protective Water Repellents

### "5558" Smooth-face CMU- RILEM Testing

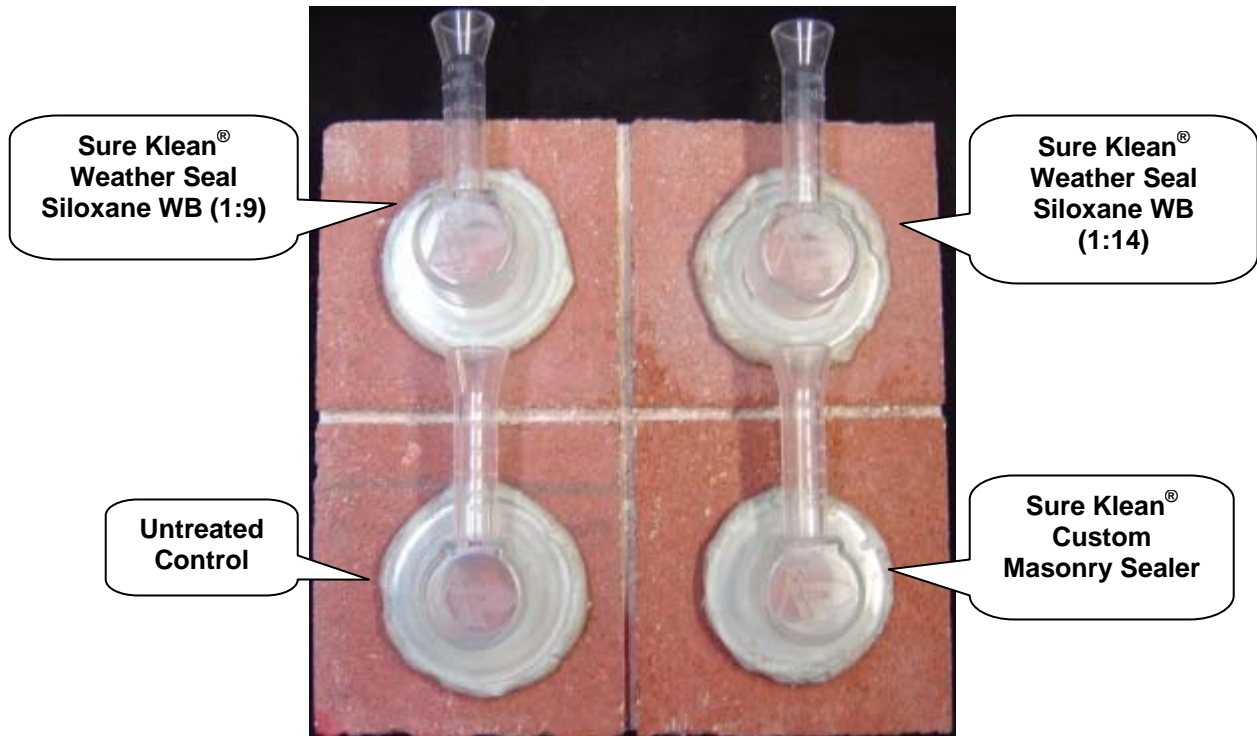



# PALLET TAG PROGRAM LABORATORY REPORT



---

## CONCLUSIONS - Protective Water Repellents

Based upon laboratory evaluations, Sure Klean® Custom Masonry Sealer and Sure Klean® Weather Seal Siloxane WB Concentrate diluted with nine and fourteen parts water provided excellent water repellency to all submitted samples. In addition, Sure Klean® Custom Masonry Sealer enhanced the appearance of each CMU.

---

## RECOMMENDATIONS - PROTECTIVE WATER REPELLENTS

Recommendations for water repellency treatment for each type of CMU submitted by Northfield Block Company, Mundelein, IL, are provided in the chart below. Recommendations are based on the treatment that proved most effective and can provide water repellency on all types submitted.

Block Type	Water Repellents
All Submitted CMU's	Sure Klean® Custom Masonry Sealer OR Sure Klean® Weather Seal Siloxane WB Concentrate (1:9), (1:14)

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. On-site testing should be conducted to determine the most appropriate water repellent product and procedures for a particular project. See product literature for additional application and product information.



# PALLET TAG PROGRAM LABORATORY REPORT



PROSOCO, Inc.

Page 63

---

## SECTION D – GRAFFITI CONTROL

### DESCRIPTION OF PRODUCTS EVALUATED

These trials were conducted to determine the optimal graffiti control treatment.

#### Graffiti Control Treatments

**Sure Klean® Custom Masonry Sealer** – A clear, solvent-based silicone elastomer formulated to weatherproof concrete block and other porous masonry material. Sure Klean® Custom Masonry Sealer protects masonry surfaces from repeated graffiti attacks without altering the natural appearance.

#### Products Evaluated for Graffiti Removal

**Defacer Eraser® Graffiti Wipe** – An easy-to-use graffiti remover that does not contain methanol, methylene chloride or other “halogenated” solvents prohibited on many projects. Graffiti Wipe removes a variety of graffiti stains from most smooth masonry, wood and metal surfaces.

**Sure Klean® Fast Acting Stripper** – A thixotropic stripping compound formulated specifically for removal of high strength paints and coatings such as epoxies, polyurethanes, and floor enamels. Additionally, Fast Acting Stripper dissolves most spray paints, marking pens, lacquers and other graffiti.

#### Graffiti Agents

Interior/Exterior Spray Paint (Red)  
Permanent Marker (Green)  
Permanent Marker (Red)  
Permanent Marker (Black)



# PALLET TAG PROGRAM LABORATORY REPORT



## **SAMPLE PREPARATION – Graffiti Control**

This evaluation compares the effectiveness in preventing staining of enamel spray paint and permanent markers.

Sections of the concrete samples were treated with one coat of Sure Klean® Custom Masonry Sealer, in accordance with PROSOCO, Inc.'s Product Guide application instructions and then allowed to cure for at least one day. At the end of the one-day cure period, a visual adverse effects evaluation was made and then the graffiti agents were applied to the substrates.

Spray paint and markers were applied as graffiti agents to all treated surfaces no sooner than one day following application of Sure Klean® Custom Masonry Sealer. Removal of the graffiti agents was attempted 24 hours after application of the graffiti agents, using Defacer Eraser® Graffiti Wipe and Sure Klean® Fast Acting Stripper.

## **TEST METHOD – Graffiti Control**

Chemical cleaners were evaluated using the following procedure:

1. Apply the product to a dry surface, soiled with graffiti.
2. Allow appropriate dwell time:
 

Graffiti Wipe.....	5 minutes
Fast Acting Stripper .....	20 minutes
3. Pressure rinse thoroughly until water runs clear. \*
4. Allow the surface to dry thoroughly and visually examine to determine effectiveness.

\* Pressure rinsing was conducted at approximately 1300 psi with a warm water flow rate of 1.9 gallons per minute.





# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Graffiti Control**

% Removal

<b>“Beldon Brick #25-Blend” Smooth-face CMU</b>					
<b>Untreated Control</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	95%	95%	70%	95%	<b>89%</b>
Graffiti Wipe	95%	50%	60%	80%	<b>71%</b>
<b>Custom Masonry Sealer</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	100%	99%	99%	99%	<b>99%</b>
Graffiti Wipe	100%	99%	99%	99%	<b>99%</b>
<b>“Heritage Blend #20-Blend” Smooth-face CMU</b>					
<b>Untreated Control</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	85%	90%	90%	90%	<b>89%</b>
Graffiti Wipe	90%	50%	60%	80%	<b>70%</b>
<b>Custom Masonry Sealer</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	100%	100%	99%	99%	<b>100%</b>
Graffiti Wipe	100%	100%	99%	99%	<b>100%</b>
<b>“Lawson Blend #5-Blend” Smooth-face CMU</b>					
<b>Untreated Control</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	95%	90%	60%	90%	<b>84%</b>
Graffiti Wipe	80%	50%	50%	80%	<b>65%</b>
<b>Custom Masonry Sealer</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	100%	99%	95%	99%	<b>98%</b>
Graffiti Wipe	100%	99%	95%	99%	<b>98%</b>
<b>“Lawson Blend-Spray” Smooth-face CMU</b>					
<b>Untreated Control</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	95%	90%	50%	70%	<b>76%</b>
Graffiti Wipe	85%	30%	50%	60%	<b>56%</b>
<b>Custom Masonry Sealer</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	100%	95%	90%	95%	<b>95%</b>
Graffiti Wipe	100%	90%	90%	95%	<b>94%</b>
<b>“Lockport #16-Blend” Smooth-face CMU</b>					
<b>Untreated Control</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	95%	90%	90%	95%	<b>93%</b>
Graffiti Wipe	95%	30%	50%	50%	<b>56%</b>
<b>Custom Masonry Sealer</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	100%	100%	95%	99%	<b>99%</b>
Graffiti Wipe	100%	100%	95%	99%	<b>99%</b>
<b>“Promenade Blend #18-Blend” Smooth-face CMU</b>					
<b>Untreated Control</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	95%	90%	90%	90%	<b>91%</b>
Graffiti Wipe	80%	30%	50%	70%	<b>58%</b>
<b>Custom Masonry Sealer</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	100%	100%	99%	99%	<b>100%</b>
Graffiti Wipe	100%	95%	95%	95%	<b>96%</b>



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Graffiti Control**

% Removal

“Promenade Blend-Spray” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	90%	95%	<b>94%</b>
Graffiti Wipe	80%	70%	80%	90%	<b>80%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	99%	100%	<b>100%</b>
Graffiti Wipe	100%	100%	99%	100%	<b>100%</b>
“Sandlewood Blend #6-Blend” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	90%	95%	<b>93%</b>
Graffiti Wipe	90%	30%	70%	90%	<b>70%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	99%	100%	<b>99%</b>
Graffiti Wipe	95%	100%	99%	100%	<b>99%</b>
“Sandlewood Blend-Spray” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	90%	95%	<b>94%</b>
Graffiti Wipe	85%	30%	90%	95%	<b>75%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	99%	100%	<b>100%</b>
Graffiti Wipe	100%	99%	99%	100%	<b>100%</b>
“Springfield Blend-Spray” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	90%	80%	<b>89%</b>
Graffiti Wipe	80%	30%	80%	80%	<b>68%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	95%	90%	95%	<b>95%</b>
Graffiti Wipe	100%	85%	90%	90%	<b>91%</b>
“Alabaster” Ground-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	60%	70%	<b>73%</b>
Graffiti Wipe	80%	50%	50%	50%	<b>58%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	90%	90%	<b>93%</b>
Graffiti Wipe	95%	95%	90%	90%	<b>93%</b>
“Buff” Ground-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	60%	70%	<b>73%</b>
Graffiti Wipe	80%	50%	50%	50%	<b>58%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	95%	95%	<b>95%</b>
Graffiti Wipe	95%	95%	90%	90%	<b>93%</b>



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 67

**TEST RESULTS – Graffiti Control**

% Removal

“Graphite” Ground-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	80%	80%	80%	<b>80%</b>
Graffiti Wipe	80%	50%	50%	50%	<b>58%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	100%	99%	99%	<b>99%</b>
Graffiti Wipe	99%	100%	99%	95%	<b>98%</b>
“Limestone” Ground-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	70%	70%	70%	<b>74%</b>
Graffiti Wipe	80%	50%	50%	50%	<b>58%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	99%	99%	99%	<b>98%</b>
Graffiti Wipe	90%	85%	85%	85%	<b>86%</b>
“Midnight (unsealed)” Ground-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	100%	90%	90%	<b>93%</b>
Graffiti Wipe	90%	20%	80%	85%	<b>69%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	99%	99%	<b>100%</b>
Graffiti Wipe	100%	100%	99%	99%	<b>100%</b>
“Canyon Blend” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	70%	60%	60%	<b>72%</b>
Graffiti Wipe	60%	50%	60%	60%	<b>58%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	99%	99%	100%	<b>99%</b>
Graffiti Wipe	100%	95%	95%	99%	<b>97%</b>
“Desert Blend” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	60%	80%	<b>81%</b>
Graffiti Wipe	70%	50%	50%	50%	<b>55%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	100%	100%	<b>99%</b>
Graffiti Wipe	99%	100%	99%	99%	<b>99%</b>
“Mountain Blend” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	60%	90%	<b>84%</b>
Graffiti Wipe	50%	50%	60%	90%	<b>63%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	100%	100%	100%	<b>100%</b>
Graffiti Wipe	100%	100%	100%	100%	<b>100%</b>



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Graffiti Control**

% Removal

“Woodland Blend” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	80%	85%	88%
Graffiti Wipe	30%	30%	80%	85%	56%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	99%	99%	98%
Graffiti Wipe	95%	100%	99%	99%	98%
“3776” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	80%	90%	89%
Graffiti Wipe	90%	30%	80%	80%	70%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	100%	100%	99%	100%
Graffiti Wipe	99%	100%	100%	99%	100%
“3776” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	95%	60%	90%	86%
Graffiti Wipe	99%	30%	60%	60%	62%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	100%	100%	100%	100%
Graffiti Wipe	100%	100%	100%	99%	100%
“4660” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	80%	90%	90%
Graffiti Wipe	50%	50%	80%	90%	68%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	99%	99%	100%
Graffiti Wipe	100%	100%	99%	99%	100%
“4660” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	80%	90%	90%
Graffiti Wipe	90%	50%	50%	90%	70%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	90%	100%	98%
Graffiti Wipe	100%	100%	90%	100%	98%
“4916” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	70%	95%	88%
Graffiti Wipe	50%	70%	50%	80%	63%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	100%	95%	99%	98%
Graffiti Wipe	99%	95%	95%	95%	96%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 69

**TEST RESULTS – Graffiti Control**

% Removal

“4916” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	60%	80%	80%
Graffiti Wipe	90%	50%	80%	80%	75%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	99%	90%	95%	96%
Graffiti Wipe	100%	95%	90%	90%	94%
“4970” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	60%	95%	85%
Graffiti Wipe	80%	60%	50%	90%	70%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	95%	100%	99%
Graffiti Wipe	100%	100%	95%	100%	99%
“4970” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	80%	90%	90%
Graffiti Wipe	85%	30%	80%	90%	71%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	95%	90%	100%	96%
Graffiti Wipe	100%	85%	85%	95%	91%
“5558” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	30%	50%	50%	90%	55%
Graffiti Wipe	30%	50%	50%	90%	55%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	100%	100%	100%
Graffiti Wipe	100%	100%	100%	100%	100%
“5558” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	95%	80%	95%	92%
Graffiti Wipe	99%	85%	80%	95%	90%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	100%	100%	100%
Graffiti Wipe	100%	100%	100%	100%	100%
“8539” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	90%	95%	93%
Graffiti Wipe	30%	50%	50%	60%	48%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	100%	100%	99%
Graffiti Wipe	100%	100%	99%	99%	100%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 70

**TEST RESULTS – Graffiti Control**

% Removal

“8539” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	60%	80%	80%
Graffiti Wipe	80%	30%	50%	60%	55%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	85%	100%	95%
Graffiti Wipe	100%	90%	85%	95%	93%
“8540” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	60%	90%	84%
Graffiti Wipe	30%	30%	50%	80%	48%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	100%	95%	99%	98%
Graffiti Wipe	99%	100%	95%	99%	98%
“8540” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	60%	95%	85%
Graffiti Wipe	80%	30%	50%	80%	60%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	99%	100%	100%
Graffiti Wipe	100%	100%	99%	100%	100%
“#191” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	80%	50%	90%	78%
Graffiti Wipe	30%	70%	80%	85%	66%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	95%	100%	98%
Graffiti Wipe	95%	100%	95%	100%	98%
“#191” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	85%	70%	80%	83%
Graffiti Wipe	80%	30%	60%	70%	60%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	95%	85%	95%	94%
Graffiti Wipe	100%	85%	85%	90%	90%
“#192” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	90%	60%	90%	81%
Graffiti Wipe	30%	30%	50%	80%	48%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	95%	99%	97%
Graffiti Wipe	95%	100%	95%	99%	97%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 71

**TEST RESULTS – Graffiti Control**

% Removal

<b>“#192” Smooth-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	90%	80%	80%	<b>84%</b>
Graffiti Wipe	80%	30%	80%	70%	<b>65%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	90%	95%	<b>95%</b>
Graffiti Wipe	95%	90%	90%	95%	<b>93%</b>
<b>“#193” Split-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	50%	90%	<b>80%</b>
Graffiti Wipe	30%	30%	50%	50%	<b>40%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	90%	95%	<b>94%</b>
Graffiti Wipe	95%	90%	85%	90%	<b>90%</b>
<b>“#193” Smooth-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	60%	80%	<b>83%</b>
Graffiti Wipe	90%	30%	50%	60%	<b>58%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	80%	95%	<b>91%</b>
Graffiti Wipe	95%	90%	80%	90%	<b>89%</b>
<b>“#197” Split-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	90%	90%	<b>90%</b>
Graffiti Wipe	70%	30%	70%	80%	<b>63%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	99%	100%	99%	<b>99%</b>
Graffiti Wipe	99%	99%	100%	99%	<b>99%</b>
<b>“#197” Smooth-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	80%	50%	90%	<b>78%</b>
Graffiti Wipe	80%	30%	50%	60%	<b>55%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	99%	90%	99%	<b>97%</b>
Graffiti Wipe	100%	95%	90%	95%	<b>95%</b>
<b>“#21” Split-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	70%	95%	<b>86%</b>
Graffiti Wipe	60%	70%	70%	85%	<b>71%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	99%	95%	95%	<b>96%</b>
Graffiti Wipe	95%	99%	90%	95%	<b>95%</b>



# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Graffiti Control**

% Removal

<b>“#21” Smooth-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	50%	80%	<b>79%</b>
Graffiti Wipe	80%	30%	50%	50%	<b>53%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	99%	80%	95%	<b>93%</b>
Graffiti Wipe	99%	90%	80%	90%	<b>90%</b>
<b>“#33” Split-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	80%	50%	90%	<b>78%</b>
Graffiti Wipe	50%	50%	50%	95%	<b>61%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	100%	100%	<b>99%</b>
Graffiti Wipe	95%	100%	100%	100%	<b>99%</b>
<b>“#33” Smooth-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	85%	90%	80%	<b>88%</b>
Graffiti Wipe	50%	50%	70%	70%	<b>60%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	99%	100%	99%	<b>99%</b>
Graffiti Wipe	99%	99%	100%	99%	<b>99%</b>
<b>“#43” Split-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	90%	95%	<b>94%</b>
Graffiti Wipe	70%	50%	70%	70%	<b>65%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	99%	99%	99%	<b>99%</b>
Graffiti Wipe	99%	95%	95%	95%	<b>96%</b>
<b>“#43” Smooth-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	80%	95%	<b>90%</b>
Graffiti Wipe	70%	85%	80%	90%	<b>81%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	100%	100%	<b>99%</b>
Graffiti Wipe	95%	100%	100%	100%	<b>99%</b>
<b>“#53” Split-face CMU</b>					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	50%	90%	<b>78%</b>
Graffiti Wipe	80%	70%	30%	80%	<b>65%</b>
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	100%	99%	99%	<b>99%</b>
Graffiti Wipe	99%	100%	95%	95%	<b>97%</b>





# PALLET TAG PROGRAM LABORATORY REPORT



**TEST RESULTS – Graffiti Control**

% Removal

“#53” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	50%	90%	78%
Graffiti Wipe	85%	30%	30%	80%	56%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	90%	80%	95%	91%
Graffiti Wipe	99%	80%	80%	90%	87%
“A-3” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	80%	50%	85%	76%
Graffiti Wipe	30%	30%	50%	50%	40%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	99%	99%	99%	98%
Graffiti Wipe	95%	95%	95%	95%	95%
“A-3” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	30%	85%	70%
Graffiti Wipe	80%	30%	30%	50%	48%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	80%	90%	90%
Graffiti Wipe	95%	80%	70%	80%	81%
“A-7” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	70%	60%	70%	73%
Graffiti Wipe	50%	60%	60%	60%	58%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	85%	85%	85%	88%
Graffiti Wipe	95%	85%	85%	80%	86%
“A-7” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	70%	50%	70%	71%
Graffiti Wipe	70%	30%	30%	30%	40%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	95%	85%	95%	94%
Graffiti Wipe	99%	85%	85%	90%	90%
“Ivory” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	70%	60%	60%	69%
Graffiti Wipe	70%	50%	50%	80%	63%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	95%	85%	90%	90%
Graffiti Wipe	95%	85%	85%	90%	89%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 74

**TEST RESULTS – Graffiti Control**

% Removal

“Ivory” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	70%	70%	70%	70%
Graffiti Wipe	50%	30%	30%	30%	35%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	90%	90%	91%
Graffiti Wipe	95%	90%	80%	80%	86%
“Mohawk Orange” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	70%	95%	89%
Graffiti Wipe	95%	70%	70%	95%	83%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	100%	100%	100%
Graffiti Wipe	100%	100%	100%	100%	100%
“Mohawk Orange” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	80%	90%	89%
Graffiti Wipe	95%	85%	80%	80%	85%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	100%	100%	99%	100%	100%
Graffiti Wipe	100%	100%	95%	100%	99%
“Natural” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	80%	70%	90%	81%
Graffiti Wipe	30%	50%	70%	80%	58%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	100%	95%	95%	96%
Graffiti Wipe	99%	100%	95%	95%	97%
“Natural” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	80%	70%	70%	78%
Graffiti Wipe	30%	50%	50%	50%	45%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	90%	95%	94%
Graffiti Wipe	99%	90%	85%	90%	91%
“Rose” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	90%	80%	95%	86%
Graffiti Wipe	30%	50%	70%	90%	60%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	90%	100%	95%
Graffiti Wipe	95%	90%	90%	95%	93%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

Page 75

**TEST RESULTS – Graffiti Control**

% Removal

“Rose” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	80%	85%	30%	90%	71%
Graffiti Wipe	80%	30%	30%	80%	55%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	99%	95%	90%	99%	96%
Graffiti Wipe	99%	90%	90%	99%	95%
“Russet” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	50%	80%	78%
Graffiti Wipe	90%	50%	50%	80%	68%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	99%	99%	100%	98%
Graffiti Wipe	95%	95%	95%	100%	96%
“Russet” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	90%	90%	30%	90%	75%
Graffiti Wipe	90%	30%	30%	80%	58%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	95%	100%	96%
Graffiti Wipe	95%	95%	95%	100%	96%
“Std. White” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	85%	80%	80%	83%
Graffiti Wipe	70%	50%	50%	50%	55%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	95%	95%	95%	95%
Graffiti Wipe	95%	95%	90%	90%	93%
“Std. White” Smooth-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	80%	80%	80%	81%
Graffiti Wipe	30%	50%	60%	70%	53%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	95%	90%	85%	95%	91%
Graffiti Wipe	99%	90%	85%	90%	91%
“White” Split-face CMU					
Untreated Control	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	70%	60%	50%	60%	60%
Graffiti Wipe	70%	50%	50%	50%	55%
Custom Masonry Sealer	Red Paint	Black Marker	Green Marker	Red Marker	% Avg. Removal
Fast Acting Stripper	85%	95%	95%	90%	91%
Graffiti Wipe	95%	95%	90%	90%	93%



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 76**

---

**TEST RESULTS – Graffiti Control**

**% Removal**

<b>“White” Smooth-face CMU</b>					
<b>Untreated Control</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	70%	60%	60%	60%	<b>63%</b>
Graffiti Wipe	50%	30%	50%	60%	<b>48%</b>
<b>Custom Masonry Sealer</b>	<b>Red Paint</b>	<b>Black Marker</b>	<b>Green Marker</b>	<b>Red Marker</b>	<b>% Avg. Removal</b>
Fast Acting Stripper	90%	95%	90%	95%	<b>93%</b>
Graffiti Wipe	90%	90%	85%	95%	<b>90%</b>



# PALLET TAG PROGRAM LABORATORY REPORT



**PROSOCO, Inc.**

**Page 77**

---

## PHOTOGRAPHS – Graffiti Control


**“5558” Split-face CMU Before Graffiti Removal**



**Untreated  
Control**

**Sure Klean® Custom  
Masonry Sealer**

**“5558” Split-face CMU After Graffiti Removal**

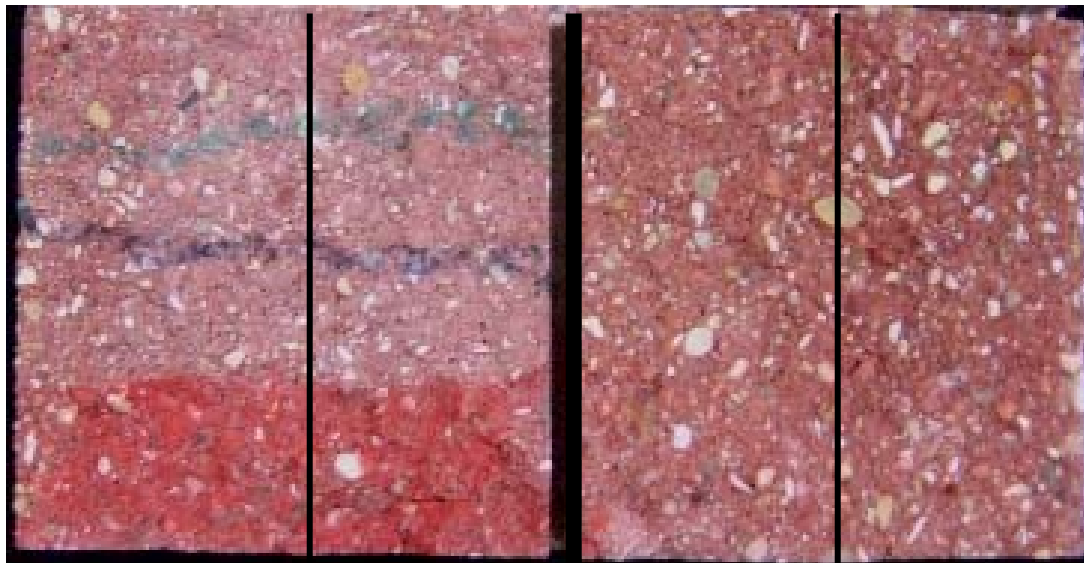

**Sure Klean® Fast  
Acting Stripper**

**Defacer Eraser®  
Graffiti Wipe**

**Sure Klean® Fast  
Acting Stripper**

**Defacer Eraser®  
Graffiti Wipe**



# PALLET TAG PROGRAM LABORATORY REPORT



## CONCLUSIONS – Graffiti Control

Based upon laboratory evaluations, graffiti removal was improved when the submitted samples were treated with Sure Klean® Custom Masonry Sealer prior to graffiti application. In addition, Sure Klean® Custom Masonry Sealer enhanced the appearance of the CMU's.

## RECOMMENDATIONS – GRAFFITI CONTROL

Recommendations for graffiti control treatment for each type of CMU submitted by Northfield Block Company, Mundelein, IL, are provided in the chart below. Recommendations are based on the treatment that proved most effective for providing graffiti repellency and the product that was most effective at removing the graffiti on all types submitted.


Block Type	Graffiti Repellent	Graffiti Removers
All Submitted CMU's	Sure Klean® Custom Masonry Sealer	Sure Klean® Fast Acting Stripper OR Defacer Eraser® Graffiti Wipe

Apply all products in accordance with the manufacturer's recommendation provided on container labels and product data sheets. Because the severity of graffiti varies from location to location, on-site testing should be conducted to determine the most appropriate graffiti control product and procedure for a particular project.

For the most severe graffiti cases Sure Klean® Fast Acting Stripper is recommended for job-site testing. For mild graffiti cases, Defacer Eraser® Graffiti Wipe is recommended for job-site testing. See product literature for additional application and product information.

Christopher A. Moore  
Project Testing Laboratory Technician

CAM



---

***Laboratory Report***

**Pallet Tag Program Evaluation**

**Northfield Block Company  
Mundelein, IL**

***Project No. 0412-09 PTP***

***Prepared For:***

**Northfield Block Company  
One Hunt Ct.  
Mundelein, IL 60060**

***Prepared By:***



***PROSOCO, Inc.  
February 2005***